

F/G 8/7

F04704-80-C-0006

FN-TR-37-F


NL

1.2

1. 2. 3.

—

1

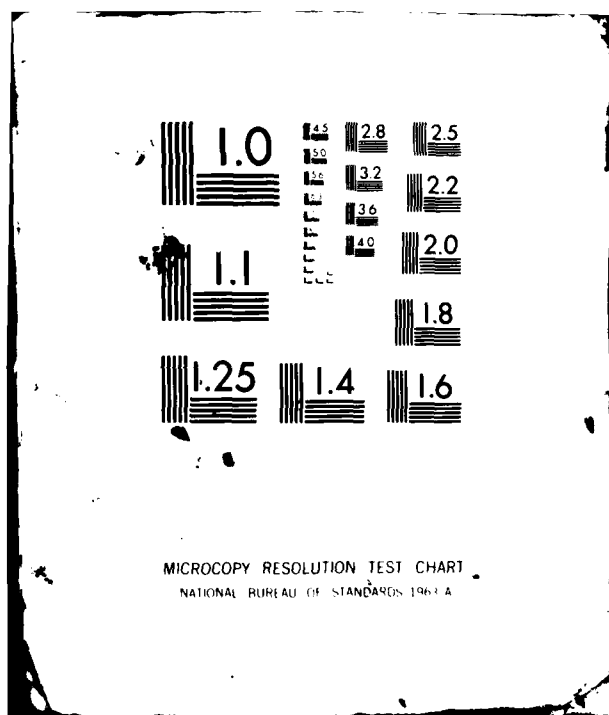

**MX SITING INVESTIGATION
GEOTECHNICAL EVALUATION**

ADA 112705

**AGGREGATE RESOURCES STUDY
LAKE VALLEY
NEVADA**


**PREPARED FOR
BALLISTIC MISSILE OFFICE (BMO)
NORTON AIR FORCE BASE, CALIFORNIA**

FUGRO
INTERNATIONAL, INC.
Consulting Engineers and Geologists

PHOTOGRAPH THIS SHEET

AD-A112 705

DTIC ACCESSION NUMBER



LEVEL



INVENTORY


FN-TR-37-F
DOCUMENT IDENTIFICATION

This document has been approved
for public release and sale; its
distribution is unlimited.

DISTRIBUTION STATEMENT

ACCESSION FOR	
NTIS	GRA&I <input checked="" type="checkbox"/>
DTIC	TAB <input type="checkbox"/>
UNANNOUNCED	<input type="checkbox"/>
JUSTIFICATION	
BY	
DISTRIBUTION /	
AVAILABILITY CODES	
DIST	AVAIL AND/OR SPECIAL
A	

DISTRIBUTION STAMP

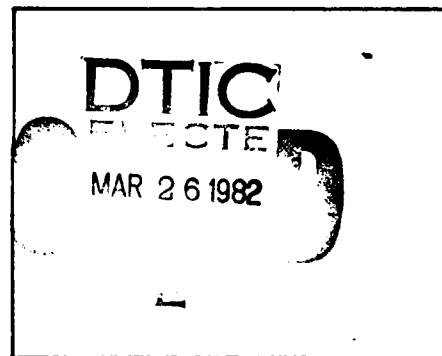

DATE ACCESSIONED



"Original contains color
plates: All DTIC reproduct-
ions will be in black and
white" ✓

82 03 10 110

DATE RECEIVED IN DTIC

PHOTOGRAPH THIS SHEET AND RETURN TO DTIC-DDA-2

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER FN-TR-37-F	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER
4. TITLE (and Subtitle) Aggregate Resources Study Lake Valley, Nevada		5. TYPE OF REPORT & PERIOD COVERED Final
7. AUTHOR(s) Fugro National, Inc.		6. PERFORMING ORG. REPORT NUMBER FN-TR-37-F
9. PERFORMING ORGANIZATION NAME AND ADDRESS Entec Western Inc. (Formerly Fugro National) PO Box 7765 Long Beach CA 90807		8. CONTRACT OR GRANT NUMBER(s) F04704-80-C-0006
11. CONTROLLING OFFICE NAME AND ADDRESS U.S. Department of the Air Force Space and Missile Systems Organization Wright-Patterson AFB OH 45409 (SAMSO)		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS 64312 F
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office)		12. REPORT DATE 27 Feb 81
		13. NUMBER OF PAGES 44
		15. SECURITY CLASS. (of this report)
		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
16. DISTRIBUTION STATEMENT (of this Report) Distribution Unlimited		
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report) Distribution Unlimited		
18. SUPPLEMENTARY NOTES		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Geology setting, potential Aggregate, soils petrography, grain size, trench logs, caliche		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) This report contains the Valley-Specific Aggregate Resources Study for Lake Valley and surrounding areas in Nevada. It is the sixth in a series of reports that contain aggregate information on the location and suitability of basin-fill and rock sources for concrete and road-base construction materials on a valley specific basis. The findings presented are based on field reconnaissance and limited laboratory testing; existing data from the State of Nevada Department of Highways, and a previous regional aggregate investigation and Verification studies conducted by Fugro.		

DD FORM 1 JAN 73 1473 EDITION OF NOV 65 IS OBSOLETE

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

AGGREGATE RESOURCES STUDY

LAKE VALLEY

NEVADA

Prepared for:

U.S. Department of the Air Force
Ballistic Missile Office (BMO)
Norton Air Force Base, California 92409

Prepared by:

Fugro National, Inc.
3777 Long Beach Boulevard
Long Beach, California 90807

27 February 1981

FOREWORD

This report was prepared for the Department of the Air Force, Ballistic Missile Office (BMO), in compliance with Contract No. F04704-80-C-0006, CDRL Item No. 004A6. It presents the results of Valley-Specific Aggregate Resources studies within and adjacent to selected areas in Nevada that are under consideration for siting the MX system.

This volume contains the results of the aggregate resources study in Lake Valley. It is the sixth of several Valley-Specific Aggregate Resources investigations which will be prepared as separate volumes. Results of this report are presented as text, appendices, and two drawings.

TABLE OF CONTENTS

	<u>Page</u>
FOREWORD	i
<u>EXECUTIVE SUMMARY</u>	iv
1.0 <u>INTRODUCTION</u>	1
1.1 Study Area	1
1.2 Background	1
1.3 Objectives	3
1.4 Scope	3
2.0 <u>STUDY APPROACH</u>	6
2.1 Existing Data	6
2.2 Supplemental Fugro National Data	6
2.3 Data Analysis	8
2.4 Presentation of Results	8
2.5 Preliminary Classification of Potential Aggregate Sources	11
3.0 <u>GEOLOGIC SETTING</u>	14
3.1 Physiography	14
3.2 Location and Description of Geologic Units	14
3.2.1 Rock Units	16
3.2.2 Basin-Fill Units	19
4.0 <u>POTENTIAL AGGREGATE SOURCES</u>	22
4.1 Basin-Fill Sources	23
4.1.1 Coarse Aggregate	23
4.1.2 Fine Aggregate	26
4.2 Crushed Rock Sources	28
4.2.1 Potentially Suitable Concrete Aggregate and Road-Base Material Sources - Class I	28
4.2.2 Possibly Unsuitable Concrete Aggregate/ Potentially Suitable Road-Base Material Sources - Class II	32
4.2.3 Unsuitable Concrete Aggregate or Road- Base Material Sources - Class III	32
5.0 <u>CONCLUSIONS</u>	33
5.1 Potential Basin-Fill Aggregate Sources	33
5.1.1 Coarse Aggregate	33
5.1.2 Fine Aggregate	34
5.2 Potential Crushed Rock Aggregate Sources	34

TABLE OF CONTENTS (Cont.)

	<u>Page</u>
6.0 BIBLIOGRAPHY	36

LIST OF APPENDICES

APPENDIX

A	Fugro National Field Station and Supplementary Test Data and Existing Test Data Summary Tables - Lake Valley
B	Summary of Caliche Development
C	Unified Soil Classification System
D	Lake Valley Study Area Photographs
E	Fugro National Geologic Unit Cross Reference

LIST OF TABLES

Table
Number

1	Aggregate Resources Study, Aggregate Tests - Lake Valley, Nevada	9
2	Preliminary Aggregate Classification System, Valley-Specific Aggregate Resources Study	12

LIST OF FIGURES

Figure
Number

1	Valley-Specific, Aggregate Resources Study Areas, Nevada-Utah	2
2	Utah-Nevada Regional Aggregate Studies	4

LIST OF DRAWINGS

Drawing
Number

1	Fugro National Field Station and Existing Data Site Locations Lake Valley	In Pocket at end of Section
2	Aggregate Resources Map Lake Valley	

EXECUTIVE SUMMARY

This report contains the Valley-Specific Aggregate Resources Study (VSARS) for Lake Valley and surrounding areas in Nevada. It is the sixth in a series of reports that contain aggregate information on the location and suitability of basin-fill and rock sources for concrete and road-base construction materials on a valley-specific basis. The findings presented are based on field reconnaissance and limited laboratory testing, existing data from the State of Nevada Department of Highways, and a previous regional aggregate investigation and Verification studies conducted by Fugro.

A classification system based on aggregate type and potential use was developed to rank the suitability of all basin-fill and rock aggregate sources. Four aggregate types have been designated: coarse, fine, and coarse and fine (multiple) aggregates derived from basin-fill sources, and crushed rock aggregates derived from rock sources. Each aggregate type was then classified using the following definitions:

- Class I Potentially suitable concrete aggregate and road-base material source;
- Class II Possibly unsuitable concrete aggregate/potentially suitable road-base material source; and
- Class III Unsuitable concrete aggregate or road-base material source.

Decisions on assigning a particular aggregate source to one of the three classes were determined from existing and Fugro

National laboratory aggregate tests performed as part of this study (abrasion resistance, soundness, and alkali reactivity), and, to a lesser degree, from field visual observations.

Emphasis in this study is placed on the identification and delineation of Class I basin-fill coarse aggregate. These deposits are considered to be the primary sources of concrete and road-base construction materials. Results of the study are presented on a 1:125,000-scale aggregate resources map (Drawing 2) and are summarized as follows:

1. Coarse Aggregate - Major Class I coarse aggregate basin-fill sources are located in alluvial fan (Aafc, Aafg,) and older lacustrine shoreline (Aolg, Aols) deposits east of the Schell Creek Range. Additional Class I coarse aggregate sources whose boundaries generally could not be delineated are also located in alluvial fan (Aafg, Aafs, Aaf) deposits in the northeastern and southern portion of the study area.

Potentially suitable Class II coarse aggregate sources are widespread and extensive in the study area. Although boundaries of specific deposits could not be delineated, they are typically located within alluvial fans (Aafg, Aaf, Aafs) flanking Class I and/or Class II rock sources and in older lacustrine (Aol, Aols) deposits.

2. Fine Aggregate - Most coarse aggregate basin-fill sources are also potential multiple sources (coarse and fine) that will supply varying quantities of fine aggregate either from the natural deposit or during processing. Specific Class I fine aggregate sources were identified and delimited in older lacustrine deposits (Aolg) located east of the Schell Creek Range.

Potential Class II fine aggregate sources are widespread and extensive in the study area. Specific deposit boundaries could not be delineated but typically occur basinward of most Class I and Class II coarse aggregate deposits and/or rock exposures.

3. Crushed Rock - Prominent Class I crushed rock aggregate sources and their locations within the study area follow.

- a. Undifferentiated carbonate rocks (Cau) composed primarily of limestone and dolomite from the Highland Peak and Guilmette formations and undifferentiated upper Cambrian deposits. Extensive deposits are located along the western margin (Schell Creek, Bristol, Highland, and Chief ranges, Dutch John and Grassy mountains at the north end of the Fairview Range, and the Pioche Hills) and southeastern portion (Wilson Creek Range and White Rock Mountains) of the study area;
- b. Prospect Mountain Quartzite (QTz) exposed in the northwestern (Schell Creek Range) and southwestern (Pioche Hills and Chief Range) parts of the study area;
- c. Unnamed Mississippian and Pennsylvanian limestones (Ls) primarily exposed in the northwestern part of the valley (Dutch John and Grassy mountains at the north end of the Fairview Range, and Schell Creek Range); and
- d. Laketown, Sevy, and Simonson dolomites (Do) exposed primarily in the Schell Creek Range.

The useability of any of these rock units as crushed rock aggregate sources will depend on their location and accessibility within the study area and their minability.

Additional aggregate testing and field investigations will be required to further refine the lateral and vertical extents of classification boundaries and to define exact physical and chemical characteristics of a particular basin-fill or rock source within the valley area.

1.0 INTRODUCTION

1.1 STUDY AREA


This report presents the results of the Valley-Specific Aggregate Resources Study (VSARS) completed for Lake Valley (Figure 1). Located in eastern Lincoln County, Nevada, the area contains a north-south trending alluvial basin flanked chiefly by carbonate and volcanic rock mountain ranges. The Schell Creek, Fairview, Bristol, Highland, and Chief ranges border the site on the west, and the Fortification and Wilson Creek ranges and the White Rock and Mahogany mountains mark the eastern boundary.

U.S. Highway 93 provides access to the western side of the study region, and State Highways 25 and 83 provide access to areas along the southern border. A network of unpaved roads and four-wheel drive trails crisscross the study area (Drawing 1).

The valley area is mainly comprised of undeveloped desert rangeland administered by the Bureau of Land Management (BLM). The towns of Pioche and Panaca, Nevada, lie just within the southwestern border of the valley-specific study area and are serviced by a spurline of the Union Pacific Railroad from Caliente, Nevada.

1.2 BACKGROUND

The MX aggregate program began in 1977 with the investigation of Department of Defense (DoD) and BLM lands in California, Nevada, Arizona, New Mexico, and Texas (FN-TR-20D). Refinement of the MX siting area added portions of Utah and Nevada that were not

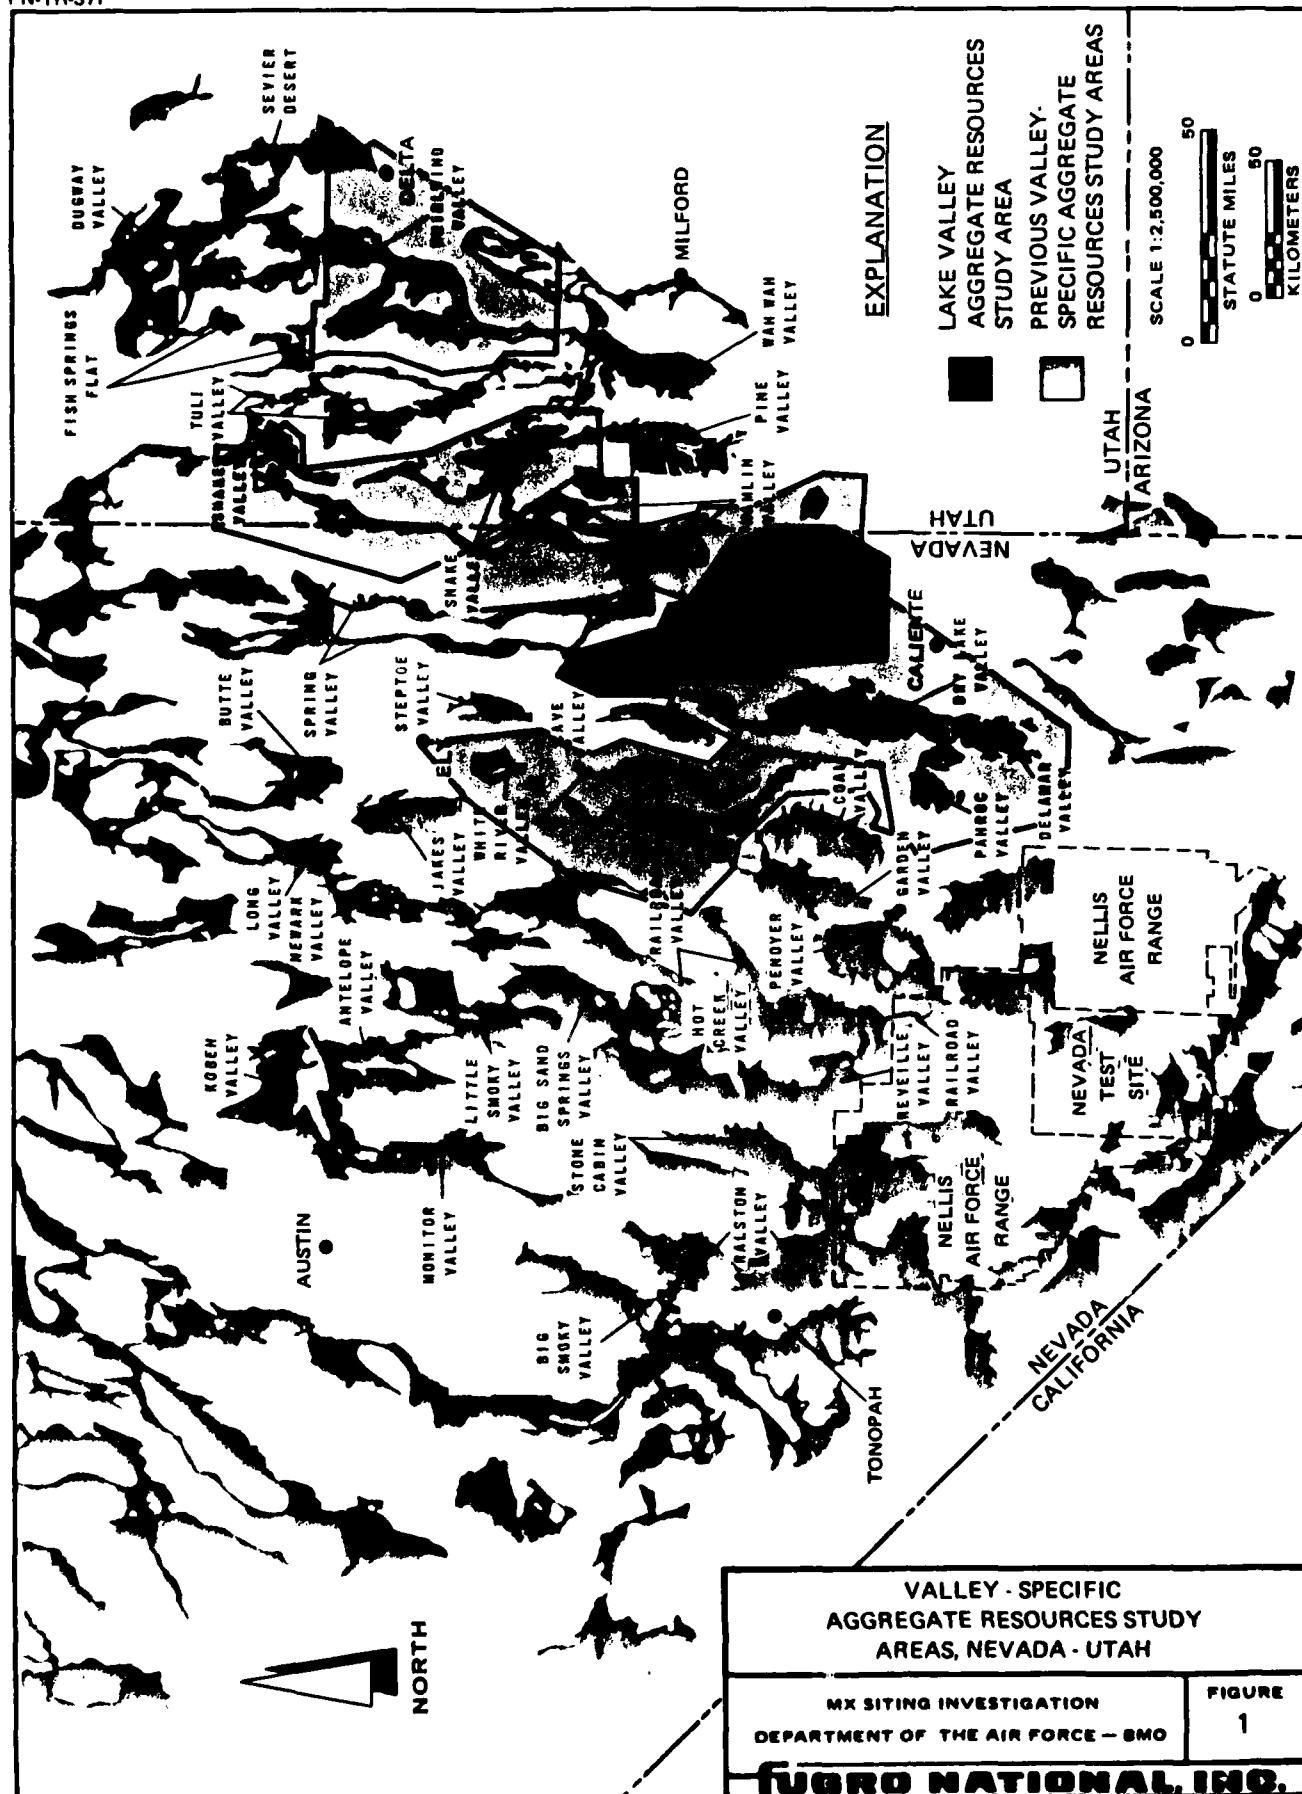

studied in the initial Aggregate Resources Evaluation Investigation (AREI). This additional area (Figure 2), defined as the Utah Aggregate Resources Study Area (UARSA), was evaluated in the fall of 1979, and a second general aggregate resources report (FN-TR-34) was submitted on 3 March 1980. Both general aggregate investigations were designed to provide regional information of the general location, quality, and quantity of aggregates that could be used in the construction of the MX system.

Subsequent to the general studies, VSARS were developed in FY 79 and continued in FY 80 to provide more-detailed information on potential aggregate sources in specified valley areas (Figure 1).


1.3 OBJECTIVES

The primary objective of the VSARS program is to classify, on a valley basis, basin-fill and rock deposits for suitability as concrete and road-base construction materials. The VSARS format is designed to select and present the locations of the most acceptable aggregate sources for preliminary construction planning and follow-on, detailed aggregate investigations.

1.4 SCOPE

The scope of this investigation required office and field investigations and included the following:

1. Collection and analysis of available existing data on the quality and quantity of potential concrete aggregate and road-base material sources. American Society of Testing and Materials (ASTM) standards and Standard Specifications for Public Works Construction (SSPWC) were used to evaluate quality.

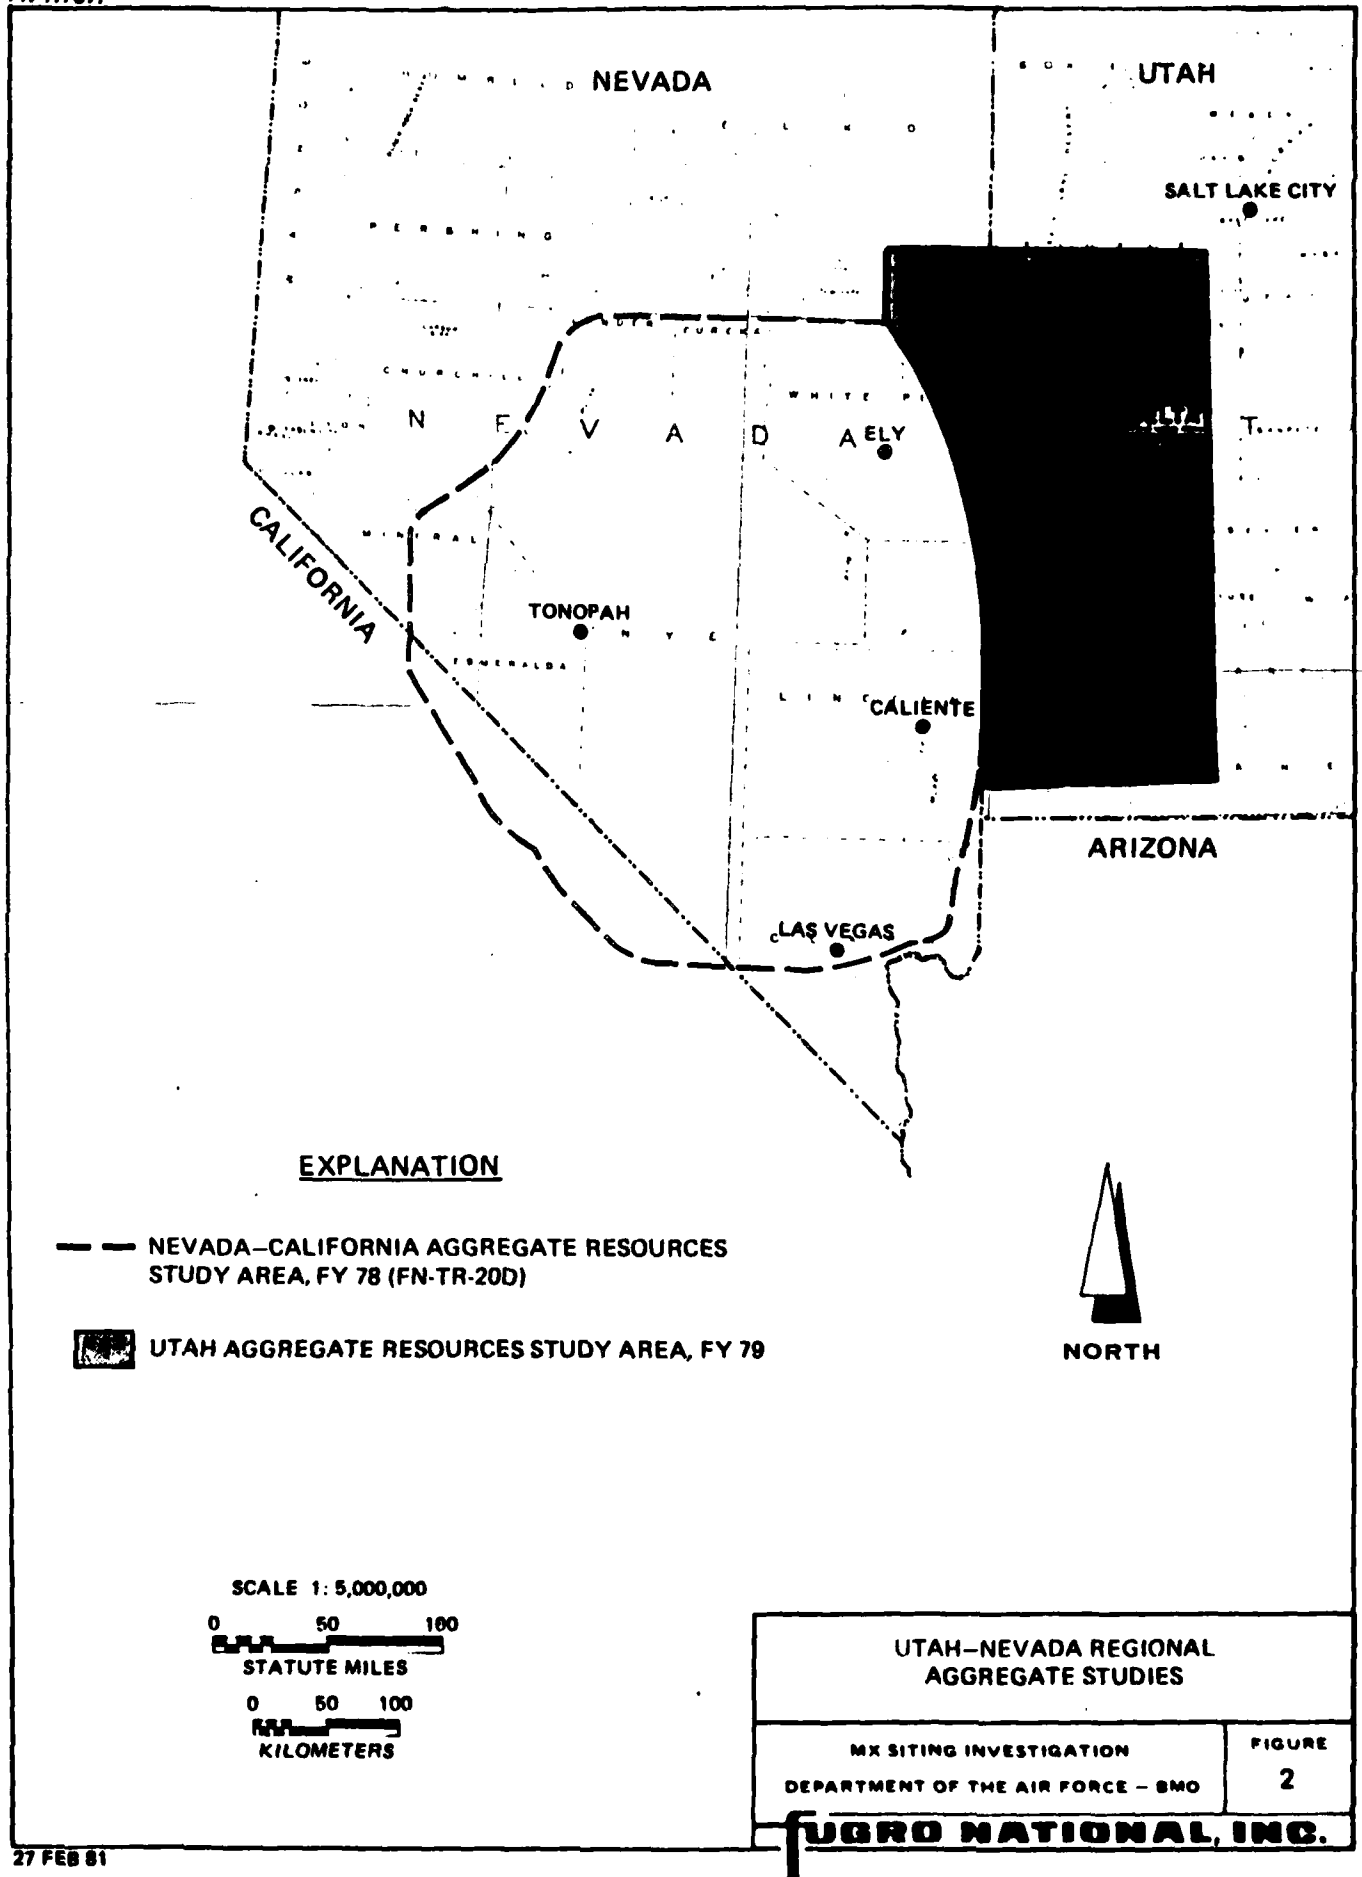

2. Aerial and ground reconnaissance of all identified potential aggregate sources in the valley area, with more detailed investigation and sample collection of likely basin-fill (coarse and fine aggregates) and rock- (crushed rock aggregates) construction material sources.
3. Laboratory testing to supplement available existing data and to provide detailed information to assist in determining the suitability of specific basin-fill or rock deposits as construction material sources within the valley area.
4. Development and application of an aggregate classification system (Section 2.5) that emphasizes aggregate type (coarse, fine, or crushed rock) and potential construction use (concrete and/or road base).

2.0 STUDY APPROACH

2.1 EXISTING DATA

Collection of existing test data from available sources was an important factor in the VSARS program. The principal source of existing data directly pertaining to aggregate construction materials was the State of Nevada Department of Highways (Appendix A). The majority of this information is related to the use of aggregate material for asphaltic concrete, base course in road construction, or ballast material. However, many of the suitability tests for these types of construction materials are similar to those for concrete and were applicable to this investigation (Appendix A).

2.2 SUPPLEMENTAL FUGRO NATIONAL DATA

Supplemental Fugro National data were obtained from: 1) field data and supplementary test data compiled during the general aggregate resources study (FN-TR-20D), 2) Lake Valley Verification study (in progress), and 3) the current Valley-Specific Aggregate Resources Study (Appendix A).

The primary objective of the initial general aggregate study was a regional evaluation and ranking of all potential aggregate sources. Twelve data points from the general aggregate study were located within the VSARS area (Drawing 1). These data stops supplied specific aggregate information which included two 150-pound samples collected for limited laboratory testing (Appendix A).

Verification geologic maps were an initial source of information on the type and extent of basin-fill units within specific valley areas. In addition, Verification study data included information from 11 trench locations distributed throughout the study area (Drawing 1). Depths of the selected trenches ranged from 5 to 14 feet (1.5 to 4.3 m). While the Verification studies are not specifically designed to generate aggregate data, the sampling techniques and testing procedures (Appendix A) are applicable to the aggregate evaluation.

The VSARS program required aerial and ground reconnaissance of the study area to collect additional information to verify conditions determined during the data review. Included in the 51 field station data stops was the collection of 27 samples for laboratory testing. Potential coarse and fine aggregate basin-fill samples were collected by channel sampling stream cuts or man-made exposures. Potential crushed rock aggregate samples were obtained from exposures of fresh or slightly weathered material whenever possible. The weight of all laboratory samples collected ranged between 100 and 150 pounds. Rock hand samples, which generally did not exceed five pounds in weight, were collected for office analyses.

Identification of basin-fill materials in all field studies followed ASTM D 2488-69, Description of Soils (Visual-Manual Procedure), and the Unified Soil Classification System (Appendix C). Rock identifications followed procedures described in the Quarterly of the Colorado School of Mines (1955) and

Standard Investigative Nomenclature of Constituents of Natural Mineral Aggregates (ASTM C 294-69).

2.3 DATA ANALYSIS

Geologic and engineering criteria were used in the evaluation of potential aggregate sources within the study area. This was supplemented by laboratory analysis of selected samples during the valley-specific aggregate testing program (Table 1). Coarse aggregate is defined as predominantly plus 0.185 inch (4.75 mm) fine gravel- to boulders-basin-fill material. Fine aggregate is defined as less than 0.375 inch (9.5 mm) and predominantly less than 0.185 inch (4.75 mm) and plus 0.0029 inch (0.074 mm) coarse to fine sand basin-fill material. While all laboratory tests supplied definitive information, the soundness, abrasion, and alkali reactivity results were considered the most critical in determining the use and acceptability of a potential aggregate source.

2.4 PRESENTATION OF RESULTS

Study results are presented in text, tables, two 1:125,000 scale maps, and appendices. Drawing 1 presents the location of the 76 existing test data and supplemental Fugro data sites within the study area. Drawing 2 presents the location of all Fugro National laboratory sample sites and all potential basin-fill and rock aggregate sources within the valley area. In addition, these potential aggregate sources are classified according to proposed aggregate use and type (Section 2.5).

ASTM TEST	SAMPLE TYPE AND NUMBER OF TESTS		
	COARSE	FINE	ROCK
ASTM C-88; SOUNDNESS BY USE OF MAGNESIUM SULFATE	14	16	11
ASTM C-131; RESISTANCE TO ABRASION BY USE OF THE LOS ANGELES MACHINE	14		11
ASTM C-136; SIEVE ANALYSIS	16	16	
ASTM C-289; POTENTIAL REACTIVITY OF AGGREGATE (CHEMICAL METHOD)	5	3	3
ASTM C-127 AND C-128; SPECIFIC GRAVITY AND ABSORPTION	7	5	4

AGGREGATE RESOURCES STUDY
AGGREGATE TESTS
LAKE VALLEY, NEVADA

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - BMO

TABLE
1

FUGRO NATIONAL, INC.

Geologic unit symbols utilized in Drawing 2 relate to standard geological nomenclature whenever possible. Undifferentiated basin-fill and rock units were established primarily to accommodate accuracy of data and map scale and may contain deposits which could supply significant quantities of high quality materials. A conversion table to relate these geologic symbols to the geologic unit nomenclature used in the Fugro National Verification studies is contained in Appendix E.

All contacts which represent distinct boundaries between geologic units are shown as solid lines in Drawing 2. The contacts are dashed where the depicted data were extrapolated beyond the limits of the source data or where accuracy of the data may be questionable. Local small deposits of one geologic unit may be found in close association with a larger deposit of a different geologic unit. Due to the reconnaissance level of the field investigation or scale limitations, these smaller deposits could not be depicted on the aggregate resources map and have been combined with the more prevalent material. Similarly, potential aggregate source classifications are preliminary and may contain lesser amounts of material of another use or type. Therefore, all classification lines are dashed and delimit the best aggregate evaluations possible at this level of investigation. In cases of highly variable rock or basin-fill units and limited aggregate tests, boundaries could not be drawn, and information is presented as point data in Drawing 2.

Appendices contain tables summarizing the basic data collected during Fugro National's supplemental field investigations, the

results of Fugro National's supplemental testing programs, and existing test data gathered from various outside sources (Appendix A). Also included in appendices are an explanation of caliche development (Appendix B), the Unified Soil Classification System (Appendix C), photographs of typical aggregate sources within the study area (Appendix D), and a geologic unit cross reference table (Appendix E).

2.5 PRELIMINARY CLASSIFICATION OF POTENTIAL AGGREGATE SOURCES

A system was developed to preliminarily classify all potential aggregate sources in the study area. This classification is designed to present the best potential sources of coarse, fine, coarse and fine (multiple source), and crushed rock aggregate types within a valley-specific area (Drawing 2) based on potential aggregate use (Table 2). Concrete aggregate parameters are the principal consideration in this report since materials suitable for use as concrete aggregate are generally acceptable for use as road-base material. Therefore, the three classifications described below were based primarily on results of the abrasion, soundness, and alkali reactivity tests.

Class I Potentially suitable concrete aggregate and road base material source. Coarse and crushed rock aggregates which either passed abrasion, soundness, and alkali reactivity tests or passed abrasion and soundness tests and were not tested for alkali reactivity; fine aggregates which either passed soundness and alkali reactivity tests or passed soundness tests and were not tested for alkali reactivity.

Class II Possibly unsuitable concrete aggregate/potentially suitable road-base material source. Coarse, fine, and crushed rock aggregates which either failed the soundness and/or alkali reactivity tests or were classified only by field visual observations or other test data.

AGGREGATE CHARACTERISTIC ¹			AGGREGATE USE CLASSIFICATION		
			CLASS I	CLASS II	CLASS III
ABRASION RESISTANCE, PERCENT WEAR ²			< 50	< 50	> 50
SOUNDNESS, PERCENT LOSS ³	COARSE AGGREGATE	Na SO ₄	< 12	> 12	> 12
		Mg SO ₄	< 18	> 18	> 18
	FINE AGGREGATE	Na SO ₄	< 10	> 10	> 10
		Mg SO ₄	< 15	> 15	> 15
POTENTIAL ALKALI REACTIVITY ⁴			INNOCUOUS TO POTENTIALLY DELETERIOUS	DELETERIOUS	DELETERIOUS

1. AGGREGATE CHARACTERISTIC BASED ON STANDARD TEST RESULTS
2. ASTM C131 (500 REVOLUTIONS)
3. ASTM C88 (5 CYCLES)
4. ASTM C289

PRELIMINARY AGGREGATE CLASSIFICATION
SYSTEM, VALLEY-SPECIFIC
AGGREGATE RESOURCES STUDY

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - SMO

TABLE
2

FUGRO NATIONAL, INC.

Class III Unsuitable concrete aggregate or road base material source. Coarse and crushed rock aggregates which failed the abrasion test and were excluded from further testing. Fine, and rarely coarse aggregates composed of significant amounts of clay- and silt-sized particles.

Sources not specifically identified as Class I, II, or III from the three critical test results or have high clay- and silt-sized particle (less than .0029 inch [.074 mm]) content are designated as Class II sources. All classifications are preliminary with additional field reconnaissance, testing, and case history studies needed to confirm adequacy, delimit areal boundaries, and define exact physical and chemical characteristics.

The following publications/sources were used in defining the three use classifications:

1. ASTM C33-74A Standard Specifications for Concrete Aggregate;
2. SSPWC Part II Construction Sections 200-1.1, 1.4, 1.5, and 1.7;
3. Literature applicable to concrete aggregates;
4. Industrial producers of concrete aggregates; and
5. Consultants in the field of concrete aggregates.

3.0 GEOLOGIC SETTING

3.1 PHYSIOGRAPHY

The study area lies entirely within the Basin and Range physiographic province. Primary physiographic features are controlled by block faulting which has produced the uplifted north-south trending mountains and intervening down-dropped, alluvial-filled basins.

Elevations within the valley range from more than 6600 feet (2012 m) near the northern end of Lake Valley to approximately 4700 feet (1433 m) near the town of Panaca in the extreme southern section of the study area.

Eight mountain ranges bound the study area. These ranges include the Highland, Bristol, Fairview, and Schell Creek ranges on the western side and the Mohogany and White Rock mountains and Fortification and Wilson Creek ranges on the eastern side of the study area (Drawing 2). The Pioche Hills form a partial topographic divide at the southern end of the study area between Lake and Meadow valleys. Topographic relief between mountain ridges and basins is generally greatest along the northwest valley margin where it averages approximately 3000 feet (914 m). Drainage is open in the main valley with surface water flowing south into Meadow Valley Wash which connects with the Muddy River near Moapa, Nevada.

3.2 LOCATION AND DESCRIPTION OF GEOLOGIC UNITS

Rocks representing the Paleozoic, Mesozoic, and Cenozoic eras occur within and adjacent to the valley area. These rocks are

of various igneous (intrusive and extrusive), metamorphic, and sedimentary lithologies (Drawing 2).

Paleozoic sedimentary rocks consist predominantly of thin- to very thick-bedded quartzites, limestones, and dolomites with interbedded sandstone, shale, and siltstone. They occur extensively in the western half of the study area within the Schell Creek, Bristol, and Highland ranges.

Unconformably overlying Paleozoic rocks within the study region are Mesozoic deposits consisting predominantly of undifferentiated volcanic rocks principally composed of flows, mud flows, breccias, and tuffs of rhyolitic to andesitic composition. These rocks occur most extensively in the White Rock and Mahogany mountains and the Wilson Creek Range on the eastern margin and in the Fairview Range along the west-central border of Lake Valley.

Cenozoic rocks, where present, unconformably overlie older rocks. Tertiary volcanic rocks are comprised of welded and nonwelded tuffs and lava flows of basaltic to rhyolitic composition. These volcanics predominantly occur as isolated units in mountain ranges on the eastern side of the valley.

Unconformably overlying all older units are unconsolidated Cenozoic basin-fill deposits. The basin-fill units consist of alluvial fan, lacustrine, and stream-channel and terrace material. These deposits reach a combined thickness of many hundreds to thousands of feet in the valley axis.

Geologic deposits have been grouped into six rock and four basin-fill geologic units for use in discussing potential aggregate sources. The grouping of these units was based on similarities in physical and chemical characteristics and map-scale limitations. The resulting units simplify discussion and presentation without altering the conclusions of the study.

3.2.1 Rock Units

Geologic rock units were grouped into six categories (see Drawing 2): quartzite (Qtz), limestone (Ls), dolomite (Do), carbonate rocks undifferentiated (Cau), sedimentary rocks undifferentiated (Su), and volcanic rocks undifferentiated (Vu).

3.2.1.1 Quartzite - Qtz

The Prospect Mountain Quartzite, of Cambrian age, crops out in the Chief and Schell Creek ranges and within the Pioche Hills (Drawing 2). This formation consists of reddish-brown to white, thin- to thick-bedded, well-indurated, fine-grained quartzite containing up to 10 percent feldspar grains. It contains interbeds of less resistant quartzite, micaceous shale, pebble conglomerate, and arkosic sandstone layers. Diabase dikes and sills of basaltic appearance may locally intrude this formation.

The Eureka Quartzite crops out as a small unit in the northwest portion of the study area within the central Schell Creek Range and in the east-central part of Lake Valley within the Wilson Creek Range (Drawing 2). It is generally less than 500 feet (150 m) thick and is closely associated with and often mapped as

dolomitic rock (Do). The formation is white or light-gray in appearance, vitreous, fine- to medium-grained, and massive orthoquartzite. Sandstone and dolomitic sandstone are exposed at the top and bottom of the formation.

3.2.1.2 Limestone - Ls

Limestone is a carbonate rock which is hard, durable, medium- to thick-bedded, and forms resistant outcrops within the study area. Mapped units represent upper Paleozoic sediments principally of Mississippian, Pennsylvanian, and Permian age. Units represented include the unnamed Mississippian, Pennsylvanian, and Permian limestones. The limestones are typically medium- to dark-gray, fine- to medium-grained, fossiliferous, and sparsely cherty with well-developed bedding and jointing. This unit is mapped chiefly in the northern portion of the study area with major deposits occurring in Grassy and Dutch John mountains in the northern Fairview Range and in the Schell Creek and Fortification ranges.

3.2.1.3 Dolomite - Do

Dolomite is a high magnesium content carbonate rock that is characteristically dark- to medium-gray in appearance, medium-grained, sparsely to moderately cherty, and hard with well-developed bedding and jointing. Principal formations that comprise the bulk of this unit are the lower Paleozoic Ely Springs, Laketown, Sevy, and Simonson dolomites. Small units are mapped in the Schell Creek Range at the northern end of the site area.

3.2.1.4 Carbonate Rocks Undifferentiated - Cau

Materials classified as undifferentiated carbonate rocks include thick, complex sequences of limestone and dolomite with thin interbeds of sandstone, shale, and siltstone. Individual units are not delineated separately due to map-scale limitations and the highly interbedded nature of these units. Principal formations in this unit include the Highland Peak, Guilmette, and undifferentiated upper Cambrian units. These cliff forming rocks are chiefly limestone and are typically light- to dark-gray in appearance, thinly to thickly bedded, hard, durable, cherty, and fossiliferous. Undifferentiated carbonate units are the most extensive of the mapped sedimentary rock units within the study area. The Bristol and Highland ranges along the southwestern margins of the site are almost entirely mapped as undifferentiated carbonate rocks. Major units also are located in the Pioche Hills and the Fairview and Schell Creek ranges and White Rock Mountains.

3.2.1.5 Sedimentary Rocks Undifferentiated - Su

Geologic formations mapped as undifferentiated sedimentary rocks include interbedded sandstone, shale, dolomite, limestone, and quartzite. These deposits are characterized by poorly indurated material with complex bedding. The highly interbedded nature of these units prevents separation into individual rock types. Principal geologic formations included within this unit are the Pioche Shale, Chainman Shale, and Arcturus Formation which principally crop out at the northern end of the site in the Schell Creek, Fairview, and Fortification ranges (Drawing 2).

3.2.1.6 Volcanic Rocks Undifferentiated - Vu

Undifferentiated volcanic rocks form the most extensive rock units in the study area and are principally located in the Mahogany and White Rock mountains and the Wilson Creek, Fairview, and Fortification ranges (Drawing 2). These rocks are Cretaceous to Pliocene and consist predominantly of welded and nonwelded pyroclastics (air falls, ash flows, ignimbrites) of andesitic to rhyolitic composition. Individual rock units have not been delineated separately because of map-scale limitations and complex composition.

3.2.2 Basin-Fill Units

Four basin-fill units are mapped within the study area (Drawing 2). These consist of older lacustrine (Aol), alluvial fan (Aaf), stream channel and terrace (Aal), and undifferentiated alluvial deposits (Au). Coarse (c) (primarily composed of cobble-sized material), gravel (g), and sand (s) grain-size designations (e.g., Aafg) have been assigned to basin-fill units in the Verification mapped areas. Fine-grained stream channel and older lake deposits (silts and clays) that have been mapped in the central portion of the basin and labeled as unsuitable aggregate sources will not be discussed in the text.

3.2.2.1 Older Lacustrine Deposits - Aol

Older lacustrine deposits were formed from late Pliocene to early Pleistocene time in response to a much wetter climate. These deposits are widely distributed throughout the study area and are usually interbedded with or overlain by alluvial fan

deposits (Drawing 2). Observed size gradations range from coarse gravel to sand, silt, and clay. Older lacustrine shoreline deposits (sandbars, sand spits, deltas) of Pleistocene Lake Carpenter in northern Lake Valley typically consist of sand and gravel and are particularly well developed at elevations of approximately 5900 to 6000 feet (1798 to 1829 m) above mean sea level. Older lacustrine deposits at the southern end of the site area typically composed of sand and gravel units with high percentages of fine-grained material (silt and clay).

3.2.2.2 Alluvial Fan Deposits - Aaf

Alluvial fans bordering the mountain fronts and extending out into the valley basins are the most extensive potential basin-fill aggregate deposits mapped and labeled within the study area (Drawing 2). They are typically homogeneous to poorly stratified mixtures of boulders, cobbles, gravel, sand, silt, and clay that grade from very coarse grained near the rock/alluvium contact to fine grained near the valley centers.

Individual fan units contain poorly to well-graded, angular to subangular particles that exhibit considerable lateral and vertical textural variation. Composition of the surrounding source rock strongly controls the textural properties of material formed in alluvial fan deposits. Fan units formed at the base of carbonate or quartzitic rocks are characteristically coarse grained, whereas fans developed from volcanic sources tend to be fine grained. Caliche development in soils (Appendix B), a natural process of soil development in arid climates, ranges from none in younger fans to Stage III in older units.

3.2.2.3 Stream Channel and Terrace Deposits - Aal

Stream-channel and terrace deposits within the study area are associated with primary and secondary ephemeral streams (Drawing 2). Secondary ephemeral streams commonly transect alluvial fan deposits and trend normal to the ranges toward the valley axis. Most are too small or indistinct to be depicted on Drawing 2 and have been grouped with adjacent, more prominent units (i.e., alluvial fan, undifferentiated alluvium). Secondary streams join the primary ephemeral drainage system in the central basin, which drains southward into Meadow Valley Wash. These deposits vary from homogeneous to poorly stratified mixtures of sand, gravel, cobbles, and boulders near mountain fronts to sand, silt, and clay near valley centers.

3.2.2.4 Alluvial Deposits Undifferentiated - Au

Undifferentiated alluvial deposits consist primarily of combinations of basin-fill units in areas that were not examined and mapped during the Verification program. Located predominantly in the southern portion of the study area, this group includes alluvial fan, older lacustrine, and stream-channel and terrace deposits. These alluvial deposits are unstratified to stratified mixtures of boulders, cobbles, gravel, sand, silt, and clay derived from a wide range of rock types. Composition varies according to the characteristics of the individual units and the lithology of the source rock.

4.0 POTENTIAL AGGREGATE SOURCES

Based on the results of field visual observations and aggregate testing, potential basin-fill and rock sources were divided into three basic material types (i.e., coarse, fine, and crushed rock) and classified into one of the three use categories (Section 2.5). Basin-fill deposits tested in the study area may also be placed within a multiple-type category (coarse and fine aggregate source). Coarse aggregate (gravel to boulders) included material predominantly retained on the No. 4 sieve (greater than 0.185 inch [4.75 mm]). Fine aggregate (predominantly sand) includes material entirely passing the 3/8-inch sieve (less than 0.375 inch [9.5 mm]) and almost entirely passing the No. 4 sieve (0.185 inch; 4.75 mm) and retained on the No. 200 sieve (0.0029 inch [0.074 mm]).

Boundaries (Drawing 2) of basin-fill aggregate sources were generalized and will require additional studies to accurately define their location. Boundaries of identified crushed rock sources are based on the aerial map extent of the geologic formations tested (i.e., Prospect Mountain Quartzite, Fish Haven Dolomite) and not on the aggregate geologic unit (i.e., Qtz, Do) described in Section 3.2.1.

In the following discussion, the best potential coarse, fine, or crushed rock source within each Class I and Class II category is presented first, followed by sources with successively lower potential. This ranking of deposits is preliminary and based upon an analysis of Fugro National and existing data.

4.1 BASIN-FILL SOURCES

4.1.1 Coarse Aggregate

4.1.1.1 Potentially Suitable Concrete Aggregate and Road Base Mineral Sources - Class I

Extensive Class I coarse aggregate sources are located in the northern end of Lake Valley within alluvial fans (Aafc, Aafg, Aafs) deposits that border the Schell Creek and northern Fairview (Dutch John and Grassy mountains) and Fortification ranges (Drawing 2). Alluvial units consist predominantly of loose to medium dense, crudely stratified sand, gravel, and cobbles composed of subangular carbonate and quartzite clasts. Laboratory test data indicate these deposits have acceptable abrasion and soundness values for Class I coarse material (Table 2). An alkali reactivity test was performed on one sample with innocuous test results. Sieve analyses for these samples suggest that the fan deposits are moderately well graded and generally have sufficient material for crushing, especially the Aafc deposit east of the Schell Creek Range. Fine-aggregate material comprises as much as 42 percent of the tested deposits. Overburden averages 1.5 to 3 feet (0.5 to 1 m) thick and consists predominantly of slightly cemented gravel (Stage II).

Access to these deposits is provided by U.S. Highway 93 which traverses the area and by numerous unpaved roads. Minability is considered good to excellent in these sources. Additional field reconnaissance and testing will be necessary to accurately define the boundaries of these potential sources.

Class I coarse aggregate sources were also identified in alluvial fan (Aafg, Aafs, Aaf) deposits at the southern end of Lake Valley east of the Bristol and Highland ranges (Drawing 2). Field observations indicate that the deposits consist of loose to dense, poor to moderately well-graded, crudely stratified gravelly sand or sandy gravel. Gravel comprises as much as 75 percent of the examined units and consists predominantly of subangular to subrounded carbonate and volcanic clasts. The coarse fraction of these sources passed the soundness and abrasion tests for Class I coarse aggregate. Alkali reactivity tests were performed on three samples with innocuous to potentially deleterious test results. Fine aggregate material comprises 14 to 60 percent of these deposits. Overburden thickness ranges from 1.5 to 3 feet (1 to 2 m), consisting of slightly cemented gravel (Stage I to III). Boundaries of some of these sources are tentatively depicted and will require additional field investigations for accurate definition. The access and minability of these deposits are considered excellent.

Class I aggregate sources were identified in older lacustrine shoreline (Aolg, Aols) deposits east of the Schell Creek Range within the central valley basin (Drawing 2). Field observations indicate these deposits consist of poorly to moderately well-graded, crudely stratified to stratified, loose to medium dense gravelly sand or sandy gravel. Gravel comprises from 34 to 67 percent of these sources and consists primarily of subrounded carbonate, quartzite, sandstone, and volcanic clasts. These deposits passed abrasion and soundness requirement for a Class I

source. Innocuous test results were obtained from the one alkali reactivity test performed. Overburden ranged from 1.5 to 3 feet (0.5 to 1 m) consisting of slightly cemented gravel (Stage II). Boundaries of these units are tentative where shown and will require additional field investigations to accurately define. The access and minability of these sources are considered excellent.

Field observations suggest that most alluvial fan units and older lacustrine shoreline units located basinward from the rock/alluvium contact of Class I and possibly Class II carbonate or quartzitic rocks may qualify as Class I coarse aggregate sources.

4.1.1.2 Possibly Unsuitable Concrete Aggregate/Potentially Suitable Road-Base Material Sources - Class II

A Class II coarse aggregate source was identified in older lacustrine (Aol) deposits west of the White Rock Mountains at the southern end of the site (Drawing 2). This deposit consists of medium-dense, moderately well-graded, crudely stratified, gravelly sand. Gravels comprise 44 percent of the source and consist predominantly of subangular to subrounded volcanic clasts. The coarse aggregate passed the abrasion test but had unacceptable soundness losses. Overburden averages about 3 feet (1 m) in thickness, and the access and minability of this unit are considered to be very good.

Based on field observations, other Class II coarse sources are present in alluvial fan (Aaf, Aafs) deposits near the rock/alluvium contact of nearly all mountain ranges. The access and

minability of these units will vary but should generally be good.

4.1.1.3 Unsuitable Concrete Aggregate or Road-Base
Material Sources - Class III

No unsuitable coarse aggregate sources were identified in the Lake Valley valley-specific study area.

4.1.2 Fine Aggregate

4.1.2.1 Potentially Suitable Concrete Aggregate and Road-
Base Material Sources - Class I

Class I fine aggregate sources were identified in older lacustrine shoreline deposits (Aolg) in northern Lake Valley (Drawing 2). These deposits consist of loose- to medium-dense, poorly to moderately well-graded, crudely stratified sandy gravel with gravels comprising from 52 to 67 percent of the material. Silt and clay comprise between two and 17 percent of these deposits. Abrasion, soundness, and alkali reactivity tests for coarse and fine fractions are within Class I standards. The high percentage of acceptable gravel (Section 4.1.1.1) and sand makes these deposits potentially excellent multiple sources. Overburden consists of 3 feet (1 m) or less of slightly cemented soil. Good access to these deposits is provided by U.S. Highway 93 which parallels the shoreline deposits at the northern end of Lake Valley. Minability is considered excellent for these sources. Boundaries of Class I fine aggregate sources are tentative where shown and will require additional field investigations for accurate delimitation.

Based on field observations, other potential Class I fine aggregate sources may exist in alluvial fans adjacent to Class I and/or possibly Class II crushed rock sources and within older lacustrine shoreline deposits.

4.1.2.2 Possibly Unsuitable Concrete Aggregate/Potentially Suitable Road-Base Materials Sources - Class II

Class II fine aggregates were identified within alluvial fan (Aafc, Aafg, Aafs, Aaf) deposits bordering the central valley basin and in older lacustrine (Aolg, Aols, Aol) and stream channel (Aal) deposits throughout the study area (Drawing 2). Field observations indicate these deposits are poorly to moderately well-graded, crudely stratified to stratified, loose- to medium dense gravelly sand and sandy gravel. Gravel ranges from 15 to 75 percent of the tested units' multiple type source and generally consist of carbonate rock clasts with some intermediate volcanic, quartzite, and sandstone clasts. Where tested, the coarse fraction passed requirements for Class I coarse aggregate (Section 4.1.1.1). Soundness losses for the fine fractions were excessively high resulting in a Class II ranking. Samples tested for alkali reactivity proved innocuous to potentially deleterious for both the coarse and fine fractions. Due to the scope of this investigation, boundaries of the fine aggregate sources could not be delineated and will require further field studies for accurate definition.

Based on field observations, additional Class II fine aggregate sources may be available from most Class I and Class II basin-fill areas shown in Drawing 2.

4.1.2.3 Unsuitable Concrete Aggregate or Road-Bass Material Sources - Class III

Class III fine aggregate sources were not specifically identified during testing but generally coincide with the distribution of stream channel deposits of the Lake Valley drainage system and within older lacustrine (Aol) and alluvial fan (Aaf) deposits in the central valley basin (Drawing 2). These sediments are typically composed of interbedded and stratified to cross-bedded, loose to moderately dense fine sand and soft to moderately stiff silt and clay.

4.2 CRUSHED ROCK SOURCES

4.2.1 Potentially Suitable Concrete Aggregate and Road-Base Material Sources - Class I

Class I crushed rock sources are distributed predominantly in the western half of the study area within the Schell Creek, Fairview, Bristol, and Highland ranges, and the Pioche Hills. Smaller, isolated units occur in the White Rock Mountains and in the Wilson Creek Range. These sources consist of: undifferentiated carbonate rocks (Cau) from the Highland Peak Formation, undifferentiated upper Cambrian deposits, and the Guilmette Formation; Prospect Mountain Quartzite (Qtz), unnamed Mississippian and Pennsylvanian limestones (Ls), Simonson, Sevy, and Laketown dolomites (Do); and undifferentiated volcanic rocks (Vu).

The Highland Peak Formation (Cau) forms extensive rock units in the Bristol, Highland, and Chief ranges and the Pioche Hills in

the southwestern part of Lake Valley. This formation also provides Class I crushed rock aggregate material in the southern White Rock Mountains. Field observations indicate that splitting characteristics are favorable for crushing, and laboratory testing indicates abrasion and soundness losses are within Class I crushed rock standards (Table 2). Alkali reactivity tests have not been completed on this formation. Limestone from this rock unit has been previously quarried at the south end of the Highland Range and used in road construction.

Undifferentiated upper Cambrian rocks (limestones and dolomites), although not as extensive as the Highland Peak Formation, are also present as major deposits in the Highland and Bristol ranges and as a small isolated unit in the southern Wilson Creek Range. Limited field observations suggest that the limestones within this formation are hard and have good splitting characteristics. Test results show no undesirable aggregate characteristics for a Class I rock unit (Table 2), however, alkali reactivity has not been determined for this source.

The Guilmette Formation (Cau) crops out at Dutch John Mountain at the northern end of the Fairview Range and in the Schell Creek and northern Bristol ranges (Drawing 2). The formation consists primarily of moderately hard to hard, dark-gray to grayish-black limestone that is thin to thick-bedded and has favorable splitting characteristics for crushing. Although not tested during this investigation, laboratory tests performed in Dry Lake and Hamlin valleys (FN-TR-37-a, FN-TR-37-d) indicate

that abrasion, soundness, and alkali reactivity tests are within Class I crushed rock aggregate requirements.

The Highland Peak Formation, undifferentiated upper Cambrian deposits, and the Guilmette Formation, because of their close proximity to major transportation arteries (U.S. Highway 93 and State Highway 83), would provide good to excellent accessible and minable sources of Class I crushed rock aggregate for the southern part of the study area.

The Prospect Mountain Quartzite (Qtz) was identified as a Class I crushed rock source within the Pioche Hills and Chief Range at the southern end of Lake Valley and in the Schell Creek Range at the northern end of the site. Field observations indicate that the quartzite is very hard, has slabby splitting characteristics, and no deleterious materials. Abrasion, soundness, and alkali reactivity tests are within Class I standards for crushed rock aggregate. Access to this source, at the southern end of Lake Valley, is excellent and is provided by U.S. Highway 93. Minability should be good to excellent.

Limited laboratory tests on unnamed Mississippian and Pennsylvanian limestones (Ls) located at the northern end of the Fairview Range (Dutch John and Grassy mountains) and in the Schell Creek Range at the north end of the valley (Drawing 2) indicate that abrasion, soundness, and alkali reactivity are well within Class I standards (Table 2). Field observations indicate the limestones are typically very hard, fine-grained, thin- to thick-bedded and have favorable splitting characteristics for

crushing. These units have very good to excellent access, which is provided by U.S. Highway 93 and unpaved roads. Minability is very good especially in those units exposed in the small hills located east of the Schell Creek Range near the valley basin.

Laketown, Simonson, and Sevy dolomites (Do) form isolated small rock units in the Schell Creek Range (Drawing 2). They consist primarily of dolomites with thin interbeds of sandstone and sedimentary breccia. Splitting characteristics of the dolomites are favorable for crushing, and both abrasion and soundness tests indicate these units are within Class I standards for crushed rock aggregate (Simonson and Sevy dolomites tested in Hamlin Valley, FN-TR-37-d). No alkali reactivity tests were performed on these units; however, potentially deleterious reactions may result from chert observed during field reconnaissance. The access and minability of the Laketown Dolomite is good to excellent especially in the small hills east of the Schell Creek Range.

Undifferentiated volcanic rock (Vu) was identified as a Class I crushed rock aggregate source in the Fortification and Wilson Creek ranges on the eastern side of the study area (Drawing 2). Boundaries could not be drawn due to lateral and vertical lithologic variations (see Section 4.2.2). Acceptable abrasion, soundness, and alkali reactivity test results indicate that volcanic rocks of andesitic and rhyodacitic composition could make

potentially suitable crushed rock sources in areas where boundaries can be defined. Alkali reactivity tests proved potentially deleterious and further testing should be completed in these sources (Table 2). Field observations indicate splitting characteristics are generally favorable for crushing, and access and minability are good.

4.2.2 Possible Unsuitable Concrete Aggregate/Potentially Suitable Road-Base Material Sources - Class II

No Class II crushed rock aggregate sources were specifically identified from the laboratory testing program. Extensive rock units indicated on Drawing 2 as Class II crushed rock sources were classified only by field visual observations. The predominant types of rock in this category are undifferentiated volcanics (Vu) of highly variable lithologic composition, certain Paleozoic carbonates (Ls, Do), and undifferentiated sedimentary (Su) rocks.

4.2.3 Unsuitable Concrete Aggregate or Road-Base Material Sources - Class III

No Class III crushed rock aggregate sources were identified within the Lake Valley study area during this investigation.

5.0 CONCLUSIONS

Results of the valley-specific aggregate investigation indicate that potentially good to high quality (Classes I and II) basin-fill and crushed rock aggregate sources are present within the Lake Valley valley-specific area to meet construction requirements of the MX system (Drawing 2).

5.1 POTENTIAL BASIN-FILL AGGREGATE SOURCES

5.1.1 Coarse Aggregate

Major Class I coarse aggregate deposits listed in order of potential suitability, have been identified within the following areas:

1. Extensive alluvial fan deposits (Aafc, Aafg) east of the Schell Creek Range in the northern part of the study area; and
2. Older lacustrine shoreline deposits (Aolg, Aols) in the north central valley, east of the Schell Range.

Field observations and laboratory testing indicate additional sources of Class I coarse aggregate are available in alluvial fan deposits (Aafg, Aafs, Aaf) adjacent to Class I and/or Class II crushed rock sources in the northeastern and southern portions of the site.

Based on field observation and limited test results, potentially suitable Class II coarse aggregate sources are widespread and extensive in the study area. Although boundaries of specific deposits could not be delineated, they are typically located within older lacustrine deposits (Aol) or alluvial fans (Aaf, Aafs) flanking Class I and/or Class II rock sources.

5.1.2 Fine Aggregate

While most coarse aggregate sources will supply quantities of fine aggregate (multiple source) either from the natural deposits or during processing, several fine aggregate sources were sampled and tested. Class I fine aggregate sources were identified within older lacustrine deposits (Aolg) east of the Schell Creek Range in the northern portion of Lake Valley.

Further field reconnaissance will be required to identify and delineate additional Class I fine aggregate sources, however, based on field observations, potential sources may exist in alluvial fan units (Aafg, Aafs, Aaf) derived from Class I and/or Class II rock sources and in older lacustrine shoreline units (Aols, Aol).

Potential Class II fine aggregate sources are widespread and extensive throughout the study area. Specific boundaries could not be delineated but typically occur in alluvial fan (Aaf, Aafs, Aafg, Aafc) and older lacustrine (Aolg, Aols, Aol) deposits basinward of most Class I and Class II rock exposures.

5.2 POTENTIAL CRUSHED ROCK AGGREGATE SOURCES

Class I crushed rock sources exist in several sections of the study area. The most suitable deposits and their corresponding locations are as follows:

- a. Prospect Mountain Quartzite (QTz), Guilmette Formation (Cau), Laketown, Sevy, and Simonson dolomites (Do), unnamed Mississippian and Pennsylvanian carbonates (Cau), and undifferentiated upper Cambrian carbonates (Cau) - Northern Lake Valley study area (Schell Creek Range, and the Dutch John and Grassy mountains at the north end of the Fairview Range).

- b. Guilmette and Highland Peak formations (Cau), Prospect Mountain Quartzite (QTz), and undifferentiated upper Cambrian carbonates (Cau). - Southwestern Lake Valley study area (Bristol, Highland, and Chief ranges, and the Pioche Hills).
- c. Highland Peak Formation and undifferentiated upper Cambrian carbonates (Cau). - Southeastern Lake Valley study area (White Rock Mountains and the Wilson Creek Range).

Quartzite (QTz) and carbonate (Cau, Do, Ls) Class I crushed rock sources, exposed within the Pioche Hills and small hills east of Schell Creek Range, could provide crushed rock material for much of the study area because of their close proximity to the valley basin and good to excellent minability.

Undifferentiated volcanic rocks (Vu), limestone (Ls), dolomite (Do), and undifferentiated carbonate (Cau) and sedimentary rocks (Su), which are widely distributed throughout the study area, compose most of the Class II crushed rock sources classified by field visual observations and delineated in Drawing 2.

6.0 BIBLIOGRAPHY

- American Concrete Association, 1975, Durability of concrete: American Concrete Institute Publication, SP-47, 385 p.
- American Concrete Institute, 1977, Recommended practice for selecting proportions for normal and heavyweight concrete: American Concrete Institute, 20 p.
- _____, 1978, Cement and concrete terminology: American Concrete Institute Publications, SP. 19 (78), 50 p.
- American Public Works Assoc., 1970, Standard specifications for public works construction: Part 2 - Construction Materials, Sec. 200 Rock Materials, p. 62-70.
- American Society for Testing and Materials, 1975, Significance of tests and properties of concrete and concrete-making materials: American Society for Testing and Materials, Special Technical Publication No. 169-A, 571 p.
- _____, 1978, Annual book of ASTM standards, Part 14: Concrete and Mineral Aggregates, 814 p.
- Bates, R. L., 1969, Geology of the industrial rocks and minerals: Dover Publications, Inc., New York, 459 p.
- Blanks, R., and Kennedy, H., 1955, The technology of cement and concrete, v. 1: John Wiley & Sons, Inc., 422 p.
- Borup, H. J., and Bagley, D. G., 1976, Soil survey of Meadow Valley area, Nevada-Utah, parts of Lincoln County, Nevada, and Iron County, Utah: U.S. Dept. Agriculture, Soil Conservation Service, 174 p.
- Brokaw, A., and Heidrick, T., 1960, Geologic map and section of the Girou Wash quadrangle, White Pine County, Nevada: U.S. Geological Survey Map, GQ-476.
- Brokaw, A. L., and Barosh, P. J., 1968, Geologic map of the Rieptown quadrangle, White Pine County, Nevada: U.S. Geological Survey Map, GQ-750.
- Brokaw, A. L., Bauer, H. L., and Breitrick, R. A., 1973, Geologic map of the Ruth quadrangle, White Pine County, Nevada: U.S. Geological Survey Map, GQ-1085.
- Brokaw, A. L., and Shawe, D. R., 1965, Geologic map and sections of the Ely SW quadrangle, White Pine County, Nevada: U.S. Geological Survey Map, I-449.
- Brown, L., 1959, Petrography of cement and concrete: Portland Cement Research Dept., Bulletin 111.

- Carr, W. J., 1966, Geology and test potential of Timber Mountain Caldera area, Nevada: U.S. Geological Survey, Technology Letter NTS-174.
- Erlin, B., 1966, Methods used in petrographic studies of concrete: Portland Cement Association, Research Department Bulletin 193, 17 p.
- Freedman, S., 1971, High strength concrete, Portland Cement Association, concrete Information Reprint, 17 p.
- Fritz, W. H., 1968, Geologic map and sections of the southern Cherry Creek and northern Egan Ranges, White Pine County, Nevada: Nevada Bureau of Mines Map, 35.
- Fugro National, Inc., 1978, Aggregate resources report, Department of Defense and Bureau of Land Management lands, southwestern United States: Conservation Report for SAMSO, 85 p.
- _____, 1980, Aggregate resources report. Utah-Nevada Study Area: Fugro National Report FN-TR-34, 36 p.
- _____, Aggregate resources studies Dry Lake Valley, Mule-shoe Valley, Delamar Valley, Pahroc Valley, Nevada: Fugro National Technical Report FN-TR-37-a, 45 p.
- _____, Aggregate resources studies Hamlin Valley: Fugro National Technical Report FN-TR-37-d, 44p.
- Gile, L. H., 1961, A classification of Ca horizons in soils in a desert region, Dona Ana County, New Mexico: Soil Science Society America Procedures, v. 25, no. 1, p. 52-61.
- Hadley, D. W., 1961, Alkalai reactivity of carbonate rocks--expansion and dedolomitization: Research and Development Laboratories of the Portland Cement Association, Bulletin 139, p. 462-474.
- _____, 1964, Alkalai reactivity of dolomitic carbonate rocks: Research and Development Laboratories of the Portland Cement Association, Bulletin. 176, 19 p.
- _____, 1968, Field and laboratory studies on the reactivity of sand-gravel aggregates: Research and Development Laboratories of the Portland Cement Association, Bulletin 221, p. 17-33.
- Hose, R. K., Blake, M. C., Jr., and Smith, R., 1976, Geology and mineral resources of White Pine County, Nevada: Nevada Bureau of Mines and Geology, Bulletin 85, 105 p.
- Howard, E. L., compiler, 1978, Geologic map of the eastern Great Basin, Nevada and Utah: Terra Scan Group LTD., 3 sheets.

- Ketner, K. B., 1976, Map showing high-purity quartzite in California, Nevada, Utah, Idaho and Montana: U.S. Geological Survey Map, MF-821.
- Lerch, W., 1959, A cement-aggregate reaction that occurs with certain sand-gravel aggregates: Research and Development Laboratories of the Portland Cement Association, Bulletin 122, p. 42-50.
- McKee, E. D., and Weir, G. W., 1953, Terminology for stratification and cross-stratification in sedimentary rocks: Geological Society. America Bulletin, v. 64, p. 381-389.
- Murphy, J. B., Nichols, S. L., and Schilling, J. H., No date, Rockhound map of Nevada: Nevada Bureau of Mines and Geology, special publication 1.
- National Ready Mixed Concrete Association, 1961, Selection and use of aggregate for concrete: National Ready Mixed Concrete Association, Publication no. 101, p. 513 - 542.
- National Sand & Gravel Association, 1977, Compilation of ASTM standards relating to sand, gravel and concrete: NSGA Circular No. 113, NRMCA Publication No. 137.
- Nevada Department of Highways, No date, Materials and research laboratory, aggregate test data: Unpublished.
- Nolan, T., et al., 1971, Geologic map of the Eureka Quadrangle, Eureka and White Pine Counties, Nevada: U.S. Geological Survey Map, I-612.
- Office of State Inspector of Mines, 1977, Directory of Nevada mine operations active during calander year 1976: Nevada Industrial Commission, 59 p.
- Papke, G. K., 1973, Industrial mineral deposits of Nevada: Nevada Bureau of Mines and Geology, map 46.
- Pickett, G., 1956, Effect of aggregate on shrinkage of concrete and hypothesis concerning shrinkage: Portland Cement Association, Research Dept., Bulletin 66, 5 p.
- Powers, T. C., and Steinour, H. H., 1955, An interpretation of published researches on the alkai-aggregate reaction: Research and Development Laboratorie of the Portland Cement Association, Bulletin 55, Part I and II, p. 497, 785.
- Reid, J. A.. 1904, Preliminary report on the building stones of Nevada, including a brief chapter on road metal: Univ. of Nevada Dept. of Geology and Mining, v. 1, no. 1, 57 p.
- Roper, H., 1960, Volume changes of concrete affected by aggregate type: Portland Cement Association, Research Dept. Bulletin 123, 4 p.

Synder, C. T., Hardman, George, and Zdenek, F. F., 1964, Pleistocene lakes in the Great Basin: U.S. Geological Survey Map, I-416.

Steinour, H. H., 1960, Concrete mix water--how impure can it be? Research and Development Laboratories of the Portland Cement Association, Bulletin 119, p. 33-50.

Steven, T. A., 1978, Geologic map of the Sevier SW quadrangle, west-central Utah: U.S. Geological Survey Map MF 962.

Stewart, H., and Carlson, J. E., 1978, Geologic Map of Nevada: U.S. Geological Survey, scale 1:500,000.

Teichert, J. A., 1959, Geology of the southern Stansbury Range: Utah Geol. and Mineral. Survey, Bulletin 65, 75 p.

Travis, R. B., 1955, Classification of rocks: Quarterly of the Colorado School of Mines, v. 50, no. 1, 98 p.

Tschanz, C. M., and Pamoeyan, E. H., 1970, Geology and mineral deposits of Lincoln County, Nevada: Nevada Bureau of Mines, Bull. 73, 188 p.

U. S. Army Corps of Engineers, 1953, Test data, concrete aggregate in continental U.S.: U. S. Army Corps of Engineers v. 1, areas 2 and 3.

U. S. Bureau of Land Management, 1974, Nevada BLM Statistics (1974): U. S. Dept. of Interior, 20 p.

U. S. Department of Agriculture, 1959, Soil survey, east Millard area, Utah: U. S. Dept. of Agriculture, 101 p.

_____, 1960, Soil survey, Beryl-Enterprise Area, Utah: U. S. Dept. of Agriculture, 75 p.

U. S. Department of the Interior, 1975, Concrete Manual: Water Resources Technical Publication, 627 p.

U. S. Department of the Interior, Bureau of Mines, 1974, The Mineral Industry of Nevada.

U. S. Department of the Interior, Bureau of Reclamation, 1966, Concrete Manual: A Manual for the Control of Concrete Construction, 642 p.

_____, Lower Colorado Regional Office, Nevada Aggregate Data, Unpublished.

_____, 1974, Earth Manual: U. S. Department of the Interior, Bureau of Reclamation, 810 p.

_____, 1975, Concrete Manual: U. S. Department of the Interior, Bureau of Reclamation, 627 p.

U. S. Geological Survey, 1964, Mineral and water resources of Nevada: U. S. Government Printing Office, Washington, 314 p.

Voskuil, W. H., 1966, Selected readings in mineral economics: Nevada Bureau of Mines, Report 12, 18 p.

Waddell, J., 1976, Concrete inspection manual: International Conference of Building Officials, 332 p.

Womack, J. C., et al., 1963, Materials manual: California Highway Transportation Agency, v. I and II.

APPENDIX A

Fugro National Field Station and Supplementary
Test Data and Existing Test Data Summary Tables -
Lake Valley

EXPLANATION OF FUGRO NATIONAL
FIELD STATION AND SUPPLEMENTARY
TEST DATA

Fugro National field stations were established at locations throughout the valley-specific study area where detailed descriptions of potential basin-fill or rock aggregate sources were recorded (Drawing 1). All field observations and laboratory test data on samples collected at selected stations are presented in Table A-1. Data entries record conditions at specific field station locations that have been generalized in the text and Drawing 2. Detailed explanations for the column headings in Table A-1 are as follows:

<u>Column Heading</u>	<u>Explanation</u>
Map Number	This sequentially arranged numbering system was established to facilitate the labeling of Fugro National field station locations and existing data sites on Drawing 1 and to list the correlating information on Tables A-1 and A-2 in an orderly arrangement.
Field Station	<p>Fugro National field station data are comprised of information collected during:</p> <ul style="list-style-type: none"> o The Valley-Specific Aggregate Resources Study; sequentially numbered field stations were completed by two investigative teams (A and B); o The general aggregate investigation in Nevada (NV); R and H indicate ground and aerial reconnaissance stops, respectively; and o The Verification study in Lake Valley (LV); trench data (T) were restricted to information below the soil horizon (1 to 6 feet).
Location	Lists major physiographic or cultural feature in or near which field stations or existing data sites are situated.

Column HeadingExplanation

Geologic Unit

Generalized basin-fill or rock geologic units at field station or existing data locations. Thirteen classifications, emphasizing age and lithologic distinctions, were developed from existing geologic maps to accomodate map scale of Drawing 2.

Material
Description

Except in cases where soil or rock samples were classified on laboratory results, the descriptions are based on field visual observations utilizing the Unified Soil Classification System (see Appendix C for detailed USCS information).

Field Observations

Boulders
and/or
Cobbles,
Percent

The estimated percentage of boulders and cobbles is based on an appraisal of the entire deposit. Cobbles have an average diameter between 3 and 12 inches (8 and 30 cm); boulders have an average diameter of 12 inches (30 cm) or more.

Gravel

Particles that will pass a 3-inch (76-mm), and are retained on No. 4 (4.75 mm), sieve.

Sand

Particles passing No. 4 sieve and retained on No. 200 (0.075 mm) sieve.

Fines

Silt or clay soil particles passing No. 200 sieve.

Plasticity
Index

Plasticity index (PI) is the range of water content, expressed as percentage of the weight of the oven-dried soil, through which the soil is plastic. It is defined as the liquid limit minus the plastic limit. Field classification followed standard descriptions and their ranges are as follows:

None	- Nonplastic (NP)	(PI, 0 - 4)
Low	- Slightly plastic	(PI, 4 - 15)
Medium	- Medium plastic	(PI, 15 - 30)
High	- Highly plastic	(PI, > 31)

Hardness

A field test to identify materials that are soft or poorly bonded by estimating their resistance to impact with a rock hammer; classified as either soft, moderately hard, hard, or very hard.

Column HeadingExplanation

Weathering

Changes in color, texture, strength, chemical composition or other properties of rock outcrops or rock particles due to the action of weather; field classified as either fresh, slight(ly), moderate(ly), or very weathered.

Deleterious Materials

Substances potentially detrimental to concrete performance that may be present in aggregate; includes organic impurities, low density material, (ash, vesicules, pumice, cinders), amorphous silica (opal, chert, chalcedony), volcanic glass, caliche coatings, clay coatings, mica, gypsum, pyrite, chlorite, and friable materials, also, aggregate that may react chemically, or be affected chemically, by other external influences.

Laboratory Test Data

Sieve Analysis
(ASTM C 136)

The determination of the proportions of particles lying within certain size ranges in granular material by separation on sieves of different size openings; 3 inch, 1 1/2 inch, 3/4 inch, 3/8 inch, No. 4, No. 8, No. 16, No. 30, No. 50, No. 100, and No. 200.

No. 8, No. 50

Asterisked entries used No. 10 and No. 40 sieves, respectively.

Abrasion Test
(ASTM C 131)

A method for testing abrasion resistance of an aggregate by placing a specified amount in a steel drum (the Los Angeles testing machine), rotating it 500 times, and determining the material worn away.

Soundness Test
(ASTM C 88)
CA, FA

CA = Coarse Aggregate
FA = Fine Aggregate

The testing of aggregates to determine their resistance to disintegration by saturated solutions of magnesium sulfate. It furnishes information helpful in judging the soundness of aggregates subject to weathering action, particularly when adequate information is not available from service records c. the material exposed to actual weathering conditions.

<u>Column Heading</u>	<u>Explanation</u>
Specific Gravity and Absorption (ASTM C 127 and 128)	Methods to determine the Bulk Specific Gravity, Bulk SSD Specific Gravity (Saturated - Surface Dry Basis), and Apparent Specific Gravity and Absorption as defined in ASTM E 12- and ASTM C 125, respectively.
Alkali Reactivity (ASTM C 289)	This method covers chemical determination of the potential reactivity of an aggregate with alkalis in portland cement concrete as indicated by the amount of reaction during 24 hours at 80° C between 1 N sodium hydroxide solution and aggregate that has been crushed and sieved to pass a No. 50 (300-μm) sieve and be retained on a No. 100 (150-μm) sieve.
Aggregate Use	<p>I = Class I; potentially suitable concrete aggregate and road-base material source.</p> <p>II = Class II; possibly unsuitable concrete aggregate/potentially suitable road-base material source.</p> <p>III = Class III; unsuitable concrete aggregate or road base material source.</p> <p>c = coarse aggregate</p> <p>f = fine aggregate</p> <p>f/c = fine and coarse aggregate</p> <p>cr = crushed rock</p> <p>All sources not specifically identified as Class I, II, or III from the abrasion, soundness, or alkali reactivity tests or the content of clay- and silt-sized particles, are designated as Class II sources.</p>

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES, PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT	
							GRAVEL	SAND
1	LV-A1	Lake Valley	Aals	Silty Gravelly Sand	SP-SM			
2	LV-A2	Lake Valley	Aaf	Silty Gravelly Sand	SP-SM	T	40	55
3	LV-A3	Wilson Creek Mountains	Vu	Rhyodacite				
4	LV-A4	Wilson Creek Mountains	Vu	Rhyodacite				
5	LV-A5	Lake Valley	Aafs	Sandy Gravel	GW			
6	LV-A6	Lake Valley	Vu	Rhyolite Tuff				
7	LV-A7	Lake Valley	Vu	Rhyolite				
8	LV-A8	Lake Valley	Aaf	Sandy Gravel	GP			
9	LV-A9	Rose Valley	Aal	Gravelly Sand	SW			
10	LV-A10	Eagle Valley Canyon	Aal	Silty Gravelly Sand	SP-SM	3	25	63
11	LV-A11	Eagle Valley	Ls	Limestone				
12	LV-A12	Little Spring Valley	Aol	Gravelly Sand	SP			

FIELD OBSERVATIONS

DISTRIBUTION OF
MATERIAL FINER
THAN COBBLES,
PERCENTGRAVEL
SAND
FINES

PLASTICITY

HARDNESS

WEATHERING

DELETERIOUS
MATERIALS

SIEVE ANALYSIS, PERCENT PASSING (ASTM)

3" 1½" ¾" ⅜" NO. 4 NO. 8 NO. 16 NO. 30

40	55	5	None			Caliche Coatings, Volc. Ash		100	97.6	92.8	84.6	78.7	66.9	47.1
			None			Caliche Coatings, Volc. Ash and Pumice								
				Hard	Slight to Moderate	Volc. Ash and Pumice								
				Mod.Hard	Moderate	Chalcedony, Volc. Ash, Pumice, glass and Vesicules								
			None			Volc. Ash and Glass, Silt Lenses	100	83.9	65.2	47.7	34.6	27.7	22.3	17.8
				Mod.Hard	Slight	Volc. Glass and Pumice								
25	65	10		Mod.Hard	Slight to Moderate	Volc. Glass and Pumice								
			None			Volc. Glass and Pumice	97.1	88.2	73.0	57.8	46.4	38.8	30.6	19.4
			None			Volc. Glass and Pumice		100	98.9	95.9	84.2	72.2	52.6	31.4
			None			Volc. Glass and Pumice								
			None	Hard	Slight	Chert, Friable Material								
			None			Caliche Coatings, Volc. Glass	100	93.0	81.0	68.1	55.7	42.6	29.8	17.8

LABORATORY TEST DATA

PASSING (ASTM C 136)					ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		SPECIFIC GRAVITY AND ABSORPTION (ASTM C 127 AND C 128)								AP- PEAR- ANCE (ASTM C 136)	
								COARSE AGGREGATE				FINE AGGREGATE					
								SPECIFIC GRAVITY			PERCENT ABSORPTION	SPECIFIC GRAVITY			PERCENT ABSORPTION		
NO. 16	NO. 30	NO. 50	NO. 100	NO. 200	PERCENT WEAR	PERCENT LOSS		BULK	BULK SSD	APPAR- ENT		BULK	BULK SSD	APPAR- ENT		PERCENT ABSORPTION	CA
66.9	47.1	20.3	8.8	5.1			29.3										
					27.7	2.6			2.41		1.1						Potentially Deleterious
22.3	17.8	12.0	6.7	3.4	29.0	10.5	20.5										
30.6	19.4	8.7	4.7	3.1	30.7	14.3	30.7		2.46		4.4						Potentially Deleterious
52.6	31.4	15.0	7.3	4.6			26.5										
					25.9	0.6			2.73		0.3						
29.8	17.8	9.1	5.1	3.3	30.7	20.1	38.1										

OPTION					AGGREGATE USE
AGGREGATE GRAVITY			ALKALI REACTIVITY (ASTM C 289)		
APPAR- ENT	PERCENT ABSORPTION	CA	FA		
		Potentially Deleterious		II f II f/c II cr I cr Ic II f II cr II cr Ic II f II f II f/c I cr II f/c	

FUGRO NATIONAL FIELD STATION
AND SUPPLEMENTARY TEST DATA
LAKE VALLEY, NEVADA

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - ONO

TABLE
A-1
PAGE 1 OF 6

FUGRO NATIONAL INC.

4

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES, PERCENT	DISTRIBUTION MATERIAL THAN CO PERCENT	
							GRAVEL	SAND
13	LV-A13	White Rock Mountains	Cau	Limestone				
14	LV-A14	Little Spring Valley	Aol	Silty Gravelly Sand	SP-SM	5	20	70
15	LV-A15	Meadow Valley	Aaf	Silty Sandy Gravel	GP-GM			
16	LV-A16	Lake Valley	Aafs	Silty Sandy Gravel	GP-GM	T	75	15
17	LV-A17	Grassy Mountain	Ls	Limestone				
18	LV-A18	Lake Valley	Aalg	Silty Sandy Gravel	GP-GM			
19	LV-A19	Lake Valley	Aafc	Silty Sandy Gravel	GW-GM			
20	LV-A20	Lake Valley	Aols	Gravelly Sand	SP	2	40	56
21	LV-A21	Lake Valley	Aafs	Silty Sandy Gravel	GM			
22	LV-A22	Lake Valley	Aalf	Sandy Silt	ML	0	10	40
23	LV-B1	Lake Valley	Cau	Limestone				
24	LV-B2	Lake Valley	Aafs	Silty Sandy Gravel	GW-GM			
25	LV-B3	Lake Valley	Aafs	Silty Sandy Gravel	GM			
26	LV-B4	Lake Valley	Aafs	Silty Sandy Gravel	GM	T	70	15
27	LV-B5	Fairview Range	Vu	Rhyolite Tuff				

FIELD OBSERVATIONS															
PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT			PLASTICITY	HARDNESS	WEATHERING	DELETERIOUS MATERIALS	SIEVE ANALYSIS, PERCENT PASSING (ASTM)							
	GRAVEL	SAND	FINES					3"	1½"	¾"	⅜"	NO. 4	NO. 8	NO. 16	NO. 30
	20	70	10	None	Hard	Slight	Chert, Friable Material								
							Volc. Glass and Pumice								
				None			Caliche Coatings	97.6	84.4	52.5	34.1	25.0	20.1	17.8	16.2
	75	15	10	Low			Caliche Coatings								
					Hard	Slight	None								
				None			None	97.2	93.4	80.4	56.9	37.0	24.5	16.9	12.3
				Med.			Caliche coatings, Clay Coatings	95.0	88.1	60.2	38.2	25.8	18.9	15.0	13.0
	40	56	4	None			Caliche Coatings, Nodules								
				None			Caliche Coatings	100	97.7	66.7	46.3	34.7	27.3	22.9	21.0
	10	40	50	Med.			Volc. Glass, Ash and Pumice, Mica								
					Hard	Slight	None								
				None			Caliche Coatings, and Nodules	100	97.4	86.3	62.9	42.2	33.0	25.6	20.7
				Low			None	100	97.0	78.9	54.3	45.8	37.4	32.2	
	70	15	15	Low			Clay Coatings								
					Mod. Hard	Mod.	Volc. Ash, Glass, and Pumice, Mica								

LABORATORY TEST DATA

SOUNDNESS (ASTM C 136)					ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		SPECIFIC GRAVITY AND ABSORPTION (ASTM C 127 AND C 128)								ALUMINA REACT (ASTM C 159)
								COARSE AGGREGATE				FINE AGGREGATE				
								SPECIFIC GRAVITY			PERCENT ABSORPTION	SPECIFIC GRAVITY			PERCENT ABSORPTION	
NO. 16	NO. 30	NO. 50	NO. 100	NO. 200	PERCENT WEAR	PERCENT LOSS		BULK	BULK SSD	APPAR- ENT		BULK	BULK SSD	APPAR- ENT		CA
							CA	FA								
17.8	16.2	14.6	12.8	11.0	27.1	2.5	26.2		2.70		0.7		2.47		5.8	Innocuous
					27.4	1.2										
16.9	12.3	9.3	7.8	6.7	31.3	4.0	27.9									
15.0	13.0	11.7	10.6	8.9	28.7	1.8	22.5									
22.9	21.0	19.8	18.1	14.3	32.8	10.0	23.5									
					26.9	1.9										
25.6	20.7	15.2	9.7	6.2	29.9	5.5	32.9									
37.4	32.2	28.2	24.0	19.2	32.0	9.5	33.5		2.64		2.4					Innocuous

DEPA

DESCRIPTION					AGGREGATE USE
AGGREGATE GRAVITY			ALKALI REACTIVITY (ASTM C 289)		
TEST ID	APPAR- ENT	PERCENT ABSORPTION			
			CA	FA	
47		5.8	Innocuous	Innocuous	IIcr
					IIcr
					Ic IIc
					Icr
					Ic IIc Ic IIc
					IIc/c
					Ic IIc IIIf
					Icr
					Ic IIc
					Ic IIc
					IIc
					IIcr
			Innocuous		

FUGRO NATIONAL FIELD STATION
AND SUPPLEMENTARY TEST DATA
LAKE VALLEY, NEVADA

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - DMO

TABLE
A-1
PAGE 2 OF 6

FUGRO NATIONAL, INC.

4

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES, PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES	
							GRAVEL	SAND
28	LV-B6	Lake Valley	Aafs	Gravelly Sand	SP	T	30	70
29	LV-B7	Lake Valley	Aafs	Silty Sandy Gravel	GP-GM	T	50	40
30	LV-B8	Lake Valley	Cau	Limestone				
31	LV-B9	Lake Valley	Aols	Gravelly Sand	SP	0	30	66
32	LV-B10	Lake Valley	Aols	Gravelly Sand	SP			
33	LV-B11	Schell Creek Range	Ls	Limestone				
34	LV-B12	Schell Creek Range	Ls	Limestone				
35	LV-B13	Lake Valley	Aolg	Silty Sandy Gravel	GP-GM			
36	LV-B14	Lake Valley	Aolg	Silty Sandy Gravel	GP-GM			
37	LV-B15	Schell Creek Range	Su	Limestone				
38	LV-B16	Lake Valley	Do	Dolomite				
39	LV-B17	Schell Creek Range	Ls	Limestone				
40	LV-B18	Schell Creek Range	Ls	Limestone				
41	LV-B19	Fortification Range	Ls	Limestone				

FIELD OBSERVATIONS														
COBBLES AND/OR COBBLES, PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT			PLASTICITY	HARDNESS	WEATHERING	DELETERIOUS MATERIALS	SIEVE ANALYSIS, PERCENT PASSING						
	GRAVEL	SAND	FINES					3"	1½"	¾"	3/8"	NO. 4	NO. 8	NO. 16
T	30	70	T				Caliche Coatings, Volc. Ash and Pumice							
T	50	40	10				None							
					Hard	Slight	Calcite Veins							
0	30	66	4	None			Volc. Glass and Pumice							
				None			Volc. Glass, Ash and Pumice	100	99.1	91.7	66.4	37.8	13.7	
					Hard	Slight	Chert							
					Hard	Slight	None							
				None			Volc. Glass, Ash Pumice, Mica	100	91.6	78.6	66.9	47.6	36.3	19.7
				Low			Volc. Glass, Ash, Pumice, Mica	100	93.5	74.0	39.8	22.2	16.4	
					Hard	Slight	None							
					Hard	Slight	None							
					Mod. Hard	Mod.	Chert							
					Hard	Slight	Chert							
					Mod. Hard	Moderate	Chert							

LABORATORY TEST DATA

PERCENT PASSING (ASTM C 136)						ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		SPECIFIC GRAVITY AND ABSORPTION (ASTM C 127 AND C 128)								REMARKS (A)
									COARSE AGGREGATE				FINE AGGREGATE				
									SPECIFIC GRAVITY			PERCENT ABSORPTION	SPECIFIC GRAVITY			PERCENT ABSORPTION	
									BULK	BULK SSD	APPAR- ENT		BULK	BULK SSD	APPAR- ENT		
NO. 8	NO. 16	NO. 30	NO. 50	NO. 100	NO. 200	PERCENT WEAR	PERCENT LOSS		BULK	BULK SSD	APPAR- ENT	PERCENT ABSORPTION	BULK	BULK SSD	APPAR- ENT	PERCENT ABSORPTION	CA
						24.8	0.4										
7.8	13.7	5.0	3.8	3.0	2.6	27.2	13.9	28.3		2.63		1.8		2.48		2.9	
						28.7	0.7										
3.3	19.7	11.6	8.0	6.2	5.2	23.5	2.2	11.0		2.63		1.2		2.61		2.0	Innocuous
2.2	16.4	13.7	12.4	11.2	9.2	26.7	3.7	24.2									
						31.1	0.8										

GRAVITY AND ABSORPTION (C 127 AND C 128)					ALKALI REACTIVITY (ASTM C 289)		AGGREGATE USE
TYPE	FINE AGGREGATE			PERCENT ABSORPTION			
	SPECIFIC GRAVITY						
PERCENT ABSORPTION	BULK	BULK SSD	APPAR- ENT	PERCENT ABSORPTION	CA	FA	
1.8		2.48		2.9			IIIf/c IIc/f Icr IIIf/c IIIf Ic IIcr Icr
1.2		2.61		2.0	Innocuous	Innocuous	Ic/f Ic IIIf IIcr Icr IIcr IIcr IIcr

FUGRO NATIONAL FIELD STATION
AND SUPPLEMENTARY TEST DATA
LAKE VALLEY, NEVADA

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - DMO

TABLE
A-1
PAGE 3 OF 6

FUGRO NATIONAL INC.

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES PERCENT	DISTRIBUTION MATERIAL FINER THAN COBBLES PERCENT	
							GRAVEL	SAND
42	LV-B20	Lake Valley	Aolq	Sandy Gravel	GW			
43	LV-B21	Fortification Range	Vu	Rhyodacite				
44	LV-B22	Fortification Range	Vu	Andesite Tuff				
45	LV-B23	Pioche Hills	Qtz	Quartzite				
46	LV-B24	Meadow Valley	Au	Sandy Clay	CL	0	20	35
47	LV-B25	Meadow Valley	Aols	Gravelly Sand	SP	0	35	61
48	LV-B26	Pioche Hills	Cau	Limestone				
49	DL-A29	Highland Range	Cau	Limestone				
50	DL-A49	Dutch John Mountain	Aolq	Silty Sandy Gravel	GM			
51	DL-A50	Bristol Pass	Aafs	Gravelly Sand	SP	T	40	60
52	NV-H-10	Bristol Range	Cau	Limestone				
53	NV-H-10	Meadow Valley	Aaf	Silty Sandy Gravel	GM-SM		50	40
54	NV-H-11	Bristol Range	Cau	Limestone				
55	NV-H-15	Lake Valley	Aafs	Silty Gravelly Sand	SM		35	50

FIELD OBSERVATIONS													
DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT		PLASTICITY	HARDNESS	WEATHERING	DELETERIOUS MATERIALS	SIEVE ANALYSIS, PERCENT PASSING (A)							
SAND	FINES					3"	1½"	¾"	¾"	NO. 4	NO. 8	NO. 16	NO. 30
		None			Caliche Coatings, Volc. Ash	100	94.7	72.6	48.8	33.2	24.3	19.9	16.0
			Mod. Hard	Moderate	Volc. Ash and Vesicles, Mica								
			Hard	Slight	Volc. Glass and Ash								
			Very Hard	Slight	None								
35	45	High			Clay Coatings								
61	4	None			Caliche Coatings and Nodules								
			Hard	Slight	None								
			Hard	Slight	None								
		None			Caliche Coatings, 10% Chert		100	96.4	73.7	38.2	28.2	23.5	21.0
60	T	None			Chert, Pumice								
					None								
40	10	None			Caliche Coatings								
					None								
50	15	Low			Caliche Coatings, Chert								

LABORATORY TEST DATA

PASSING (ASTM C 136)					ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		SPECIFIC GRAVITY AND ABSORPTION (ASTM C 127 AND C 128)								ALKALY REACTIVITY (ASTM C 159)	
								COARSE AGGREGATE				FINE AGGREGATE					
								SPECIFIC GRAVITY			PERCENT ABSORPTION	SPECIFIC GRAVITY			PERCENT ABSORPTION		
								BULK	BULK SSD	APPAR- ENT		BULK	BULK SSD	APPAR- ENT			
NO. 16	NO. 30	NO. 50	NO. 100	NO. 200	PERCENT WEAR	PERCENT LOSS										CA	
						CA	FA										
19.9	16.9	13.4	5.1	2.0	22.2	1.0	11.0		2.63		0.7		2.58		2.0	Innocuous	
					33.0	2.3										Potentially Deleterious	
					29.7	0.3			2.64		0.4					Innocuous	
					27.3	1.91											
23.5	21.1	20.3	19.6	17.6	25.6	5.10	8.00	2.63	2.67	2.75	1.56	2.56	2.61	2.68	1.79		
					27.5	5.30		2.60	2.65	2.73	1.84						

ABSORPTION (128)					AGGREGATE USE
FINE AGGREGATE			ALKALI REACTIVITY (ASTM C 289)		
SPECIFIC GRAVITY		PERCENT ABSORPTION			
BULK SSD	APPARENT			CA	
2.58		2.0	Innocuous	Innocuous	Ic/f
					IIcr
			Potentially Deleterious		Icr
			Innocuous		Icr
					IIIf
					IIIf/c
					IIcr
					Icr
2.61	2.68	1.79			Ic/f
					Ic
					IIIf
					IIcr
					IIc/f
					IIcr
					IIIf/c

FUGRO NATIONAL FIELD STATION
AND SUPPLEMENTARY TEST DATA
LAKE VALLEY, NEVADA

MX SITING INVESTIGATION /
DEPARTMENT OF THE AIR FORCE - DMO

TABLE
A-1
PAGE 4 OF 6

FUGRO NATIONAL INC.

4

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES, PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT	
							GRAVEL	SAND
56	NV-H-15	Bristol Range	Cau	Limestone				
57	NV-H-16	Grassy Mountains	Cau	Limestone				
58	NV-H-17	Dutch John Mountain	Cau	Limestone				
59	NV-R-30	Pioche Hills	Aaf	Sandy Gravel	GP-GM		60	35
60	NV-R-31	Lake Valley	Aafs	Clayey Sand	SC		5	60
61	NV-R-32	Lake Valley	Vu	Rhyolite Tuff				
62	NV-R-33	Grassy Mountain	Aafs	Silty Sandy Gravel	GP-GM			
63	NV-R-34	Lake Valley Summit	Ls	Limestone				
64	LV-T1	Lake Valley	Aolg	Sandy Gravel	GM		45	40
65	LV-T3	Lake Valley	Aafs	Silty Gravelly Sand	SM		25	60
66	LV-T4	Lake Valley	Aafs	Silty Sand	SM		15	56
67	LV-T5	Lake Valley	Aafs	Silty Sandy Gravel	GM		60	25
68	LV-T6	Lake Valley	Aafs	Gravelly Silty Sand	SM		10	75
69	LV-T7	Lake Valley	Aafs	Gravelly Silty Sand	SM		10	75
70	LV-T8	Lake Valley	Aafs	Gravelly Silty Sand	SM		10	75

FIELD OBSERVATIONS																						
NO. / OR PERCENT	DISTRIBUTION OF MATERIAL FINER THAN COBBLES, PERCENT			PLASTICITY	HARDNESS	WEATHERING	DELETERIOUS MATERIALS	SIEVE ANALYSIS, PERCENT PASSING (AS														
	GRAVEL	SAND	FINES					3"	1½"	¾"	¾"	NO. 4	NO. 8	NO. 16	NO. 30							
							Chert															
							1 to 2% Chert															
							1 to 2% Chert															
60	35	5	Low				Chert, Caliche, Clay															
5	60	35	Low				80% Volc. Glass															
							Volc. Glass															
							Chert, Caliche	100	92.7	80.5	62.3	49.2	42.0	37.3	30.0							
							5% Chert Nodules and Lenses															
45	40	15	Low				Caliche Coatings, Clay															
25	60	15	Low				Caliche Coatings															
15	56	29	Low				Caliche Coatings															
60	25	15	Low				Caliche Coatings and Nodules															
10	75	15	Low				Caliche Coatings and Nodules															
10	75	15	Low to Med.				Clay															
10	70	20	Low																			

2

LABORATORY TEST DATA

SING (ASTM C 136)					ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		SPECIFIC GRAVITY AND ABSORPTION (ASTM C 127 AND C 128)								ALK REACT (ASTM C 159)
								COARSE AGGREGATE				FINE AGGREGATE				
								SPECIFIC GRAVITY			PERCENT ABSORPTION	SPECIFIC GRAVITY			PERCENT ABSORPTION	
NO. 18	NO. 30	NO. 50	NO. 100	NO. 200	PERCENT WEAR	PERCENT LOSS		BULK	BULK SSD	APPAR- ENT		BULK	BULK SSD	APPAR- ENT		CA
					18.7	4.6										
7.3	30.5			6.8	26.0	5.3										

DEPA

PERCENT ABSORPTION	ALKALI REACTIVITY (ASTM C 289)		AGGREGATE USE
	CA	FA	
			Icr
			IIcr
			IIcr
			IIc/f
			IIf
			IIcr
			Ic
			IIf
			IIcr
			IIc/f
			IIf/c
			IIf
			IIc/f
			IIf
			IIf
			IIf

MAP NUMBER	FIELD STATION	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL	BOULDERS AND/OR COBBLES PERCENT	PERCENT	
							GRAVEL	SAND
71	LV-T9	Lake Valley	Aafs	Silty Sand	SM		3	75
72	LV-T10	Lake Valley	Aols	Silty Sand	SM		3	50
73	LV-T11	Lake Valley	Aafs	Silty Sand	SM		5	55
74	LV-T14	Lake Valley	Aafs	Sand	SP		7	80

FIELD OBSERVATIONS

DISTRIBUTION OF
MATERIAL FINER
THAN COBBLES,
PERCENT

DELETERIOUS
MATERIALS

SIEVE ANALYSIS, PERCENT PASSING (ASTM C 136)

SAND	FINES	PLASTICITY	HARDNESS	WEATHERING	DELETERIOUS MATERIALS	3"	1½"	¾"	¾"	NO. 4	NO. 8	NO. 16	NO. 30	NO. 50
75	22	Low			Caliche Coatings and Nodules									
50	47	Med.			Clay									
55	40	Low			Caliche Coatings and Nodules									
89	4	None			Caliche Coatings and Nodules									

2

EXPLANATION OF EXISTING DATA

Existing data pertaining to aggregates were extracted from the State of Nevada Department of Highways. These reports are compilations of available site data from existing files and records and are intended to accurately locate, investigate, and catalog materials needed for highway construction. Explanations for column headings which appear in Table A-2, that have not been previously discussed in Table A-1, are given below:

Column HeadingExplanation

Site Number

State of Nevada Department of Highways pit or site number. Locations correspond to map numbers listed on this table and placed on Drawing 1.

MAP NUMBER	SITE NUMBER	DATA SOURCE	LOCATION	GEOLOGIC UNIT	MATERIAL DESCRIPTION	USCS SYMBOL			
							> 6"	3-6"	1½"
75	NV-LN6	NVHD	Lake Valley	Aols	Sandy Gravel				100
76	NV-LN08-1	NVHD	Lake Valley	Aafs	Gravelly Sand				


SIEVE ANALYSIS														ABRASION TEST (ASTM C 131)	SOUNDNESS TEST (ASTM C 88)		
3-6"	1½"	1"	¾"	½"	¼"	⅜"	NO. 4	NO. 10	NO. 16	NO. 40	NO. 50	NO. 100	NO. 200		PERCENT WEAR	PERCENT LOSS	
															CA	FA	BULK
	100	97.7	95.4	88.0		80.3	53.7						5	24.0	7.39		
			90			75								24.5			

APPENDIX B

Summary of Caliche Development

DIAGNOSTIC CARBONATE MORPHOLOGY

STAGE	GRAVELLY SOILS	NONGRAVELLY SOILS
I	Thin, discontinuous pebble coatings	Few filaments or faint coatings
II	Continuous pebble coatings, some interpebble fillings	Few to abundant nodules, flakes, filaments
III	Many interpebble fillings	Many nodules and internodular fillings
IV	Laminar horizon overlying plugged horizon	Laminar horizon overlying plugged horizon

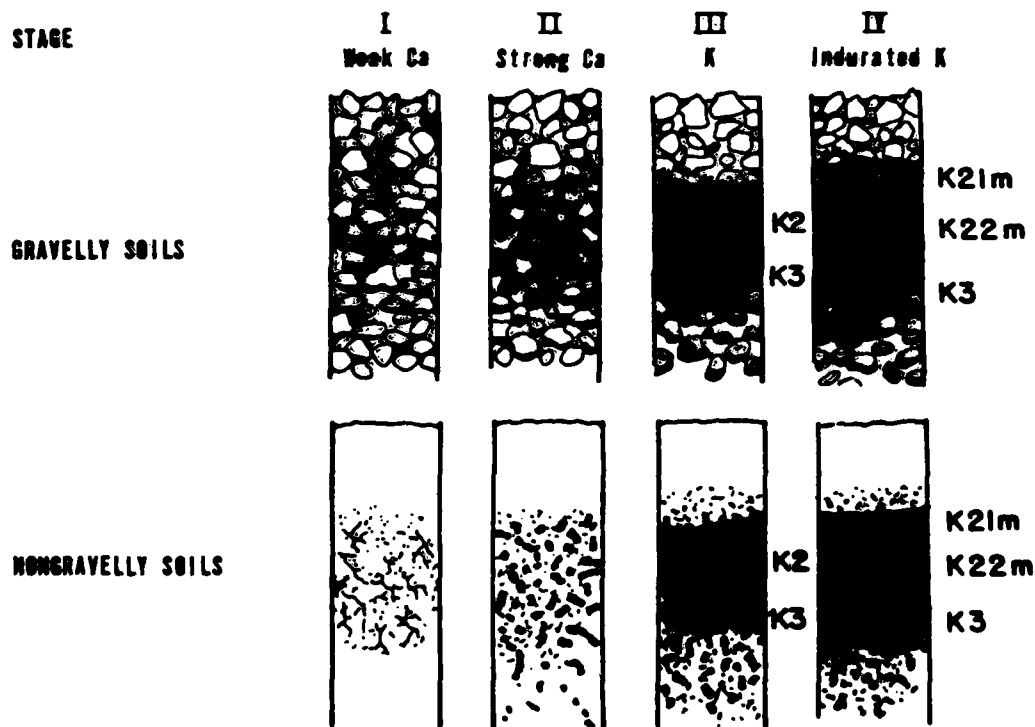

Stages of development of a caliche profile with time. Stage I represents incipient carbonate accumulation, followed by continuous build-up of carbonate until, in Stage IV, the soil is completely plugged.

SUMMARY OF CALICHE DEVELOPMENT

Reference: Gile, L.H., Peterson, F.F., and Grossman, R.B., 1965, The K horizon: A master horizon of carbonate accumulation: Soil Science, v. 89, p. 74-82.

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - DMO


FIGURE
B-1

FUGRO NATIONAL INC.

APPENDIX C

Unified Soil Classification System

Field Identification Procedures (Excluding particle sizes and bearing fractions on estimated weight)				Group Symbols		Typical Names		Information Required for Descriptive Soils		Laboratory Classification Criteria	
Coarse-grained soils More than half of coarse fraction is gravel No. 4 sieve size may be used as	Clean gravel (little or no sand)	Wide range in grain sizes and substantial amounts of all intermediate particle sizes	Predominantly one size or a range of sizes with some intermediate sizes missing	GW	Well graded gravel, gravel-mixture, little or no sand	Give typical name: indicate approximate percentages of sand, gravel, and silt; surface condition, and hardness of the coarse grains; local or geologic name and other pertinent descriptive information; and symbols in parentheses	For undisturbed soils add information on stratification, degree of compaction, cementation, moisture conditions and drainage characteristics	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for GW Atterberg limits below "A" line, or P_f less than 6 Atterberg limits above "A" line, with P_f greater than 7 $C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Determine percentages of gravel and sand from grain size curve Depending on percentages of fines (fraction smaller than No. 200 sieve) (Coarse-grained soils are classified as follows: CM, GC, SM, SC More than 12% Less than 5% 5% to 12%	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Greater than 4 Between 1 and 3 Above "A" line with P_f less than 6 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7
Fine-grained soils More than half of material is finer than No. 200 sieve size	Silt and clay (less than 50% liquid limit)	Dry Strength (crushing character-istics)	Dispersibility (reaction to shaking)	ML	Inorganic silts and very fine sands, rock flour, silty or clayey fine sand with slight plasticity	Give typical name: indicate degree and amount of plasticity, character of plasticity, and maximum size of coarse grains; color in wet condition, odor if any, local or geologic name and other pertinent descriptive information; and symbol in parentheses	For undisturbed soils add information on structure, stratification, degree of consolidation, moisture conditions and drainage characteristics	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Determine percentages of gravel and sand from grain size curve Depending on percentages of fines (fraction smaller than No. 200 sieve) (Coarse-grained soils are classified as follows: CM, GC, SM, SC More than 12% Less than 5% 5% to 12%	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Greater than 4 Between 1 and 3 Above "A" line with P_f less than 6 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7
Highly Organic Soils	Silt and clay (less than 50% liquid limit)	Dry Strength (crushing character-istics)	Dispersibility (reaction to shaking)	MH	Inorganic silts, micaceous or diatomaceous fine sandy or silty soils, elastic silts	Give typical name: indicate degree and amount of plasticity, character of plasticity, and maximum size of coarse grains; color in wet condition, odor if any, local or geologic name and other pertinent descriptive information; and symbol in parentheses	For undisturbed soils add information on structure, stratification, degree of consolidation, moisture conditions and drainage characteristics	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Determine percentages of gravel and sand from grain size curve Depending on percentages of fines (fraction smaller than No. 200 sieve) (Coarse-grained soils are classified as follows: CM, GC, SM, SC More than 12% Less than 5% 5% to 12%	$C_u = \frac{D_{60}}{D_{10}}$ $C_c = \frac{D_{30}}{D_{10} \times D_{60}}$ Not meeting all gradation requirements for SW Atterberg limits below "A" line, or P_f less than 5 Atterberg limits above "A" line, with P_f greater than 7	Greater than 4 Between 1 and 3 Above "A" line with P_f less than 6 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7 Above "A" line with P_f greater than 7

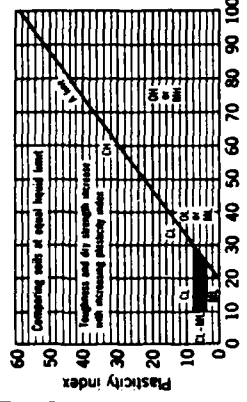

Plasticity chart for laboratory classification of fine grained soils

From Wagner, 1957.

Field Identification Procedures for Fine Grained Soils or Fractions

These procedures are to be performed on the minus No. 40 sieve size particles, approximately 1/4 in. For field classification purposes, screening is not intended, simply remove by hand the coarse particles that interfere with the tests.

Dry Strength (Crushing characteristics):

After removing particles larger than No. 40 sieve size, prepare a pat of moist soil with a volume of about one-half cubic inch. Add enough water if necessary to make the soil soft but not sticky. Place the pat in the open palm of one hand and shake horizontally, striking the pat with the fingers of the other hand. The pat should be broken into a few pieces. The amount of water on the surface of the pat which changes to a lively consistency and becomes glossy. When the sample is squeezed between the fingers, the water and gloss disappear from the surface, the pat stiffens and finally it cracks or crumbles. The rapidity of appearance of water during shaking and of its disappearing during squeezing are the basis for the dry strength test.

Very fine clean sands are the quickest and most distinct reaction whereas a plastic clay has no reaction. Inorganic silts, such as a typical rock silt, show a moderately quick reaction.

Dispersibility (Reaction to shaking):

After removing particles larger than No. 40 sieve size, prepare a pat of moist soil with a volume of about one-half cubic inch. Add enough water if necessary to make the soil soft but not sticky. Place the pat in the open palm of one hand and shake horizontally, striking the pat with the fingers of the other hand. The pat should be broken into a few pieces. The amount of water on the surface of the pat which changes to a lively consistency and becomes glossy. When the sample is squeezed between the fingers, the water and gloss disappear from the surface, the pat stiffens and finally it cracks or crumbles. The rapidity of appearance of water during shaking and of its disappearing during squeezing are the basis for the dry strength test.

Very fine clean sands are the quickest and most distinct reaction whereas a plastic clay has no reaction. Inorganic silts, such as a typical rock silt, show a moderately quick reaction.

Plasticity (Consistency near plastic limit):

After removing particles larger than No. 40 sieve size, a specimen of soil about one-half cubic inch in size, is moulded to the consistency of putty. If too dry, water must be added and if sticky, the specimen should be spread out in a thin layer and allowed to lose some moisture. The specimen is then rolled into a thread about one-eighth inch in diameter. The thread is then folded and re-rolled repeatedly. During this manipulation the moisture content is gradually reduced and the specimen stiffens. Finally loss of plasticity, and crumbles when the plastic limit is reached.

A slight leading action continued until the lump crumbles. The further the thread near the plastic limit and the stiffer the lump when it finally crumbles, the more plastic is the soil. Weakness of the thread at the plastic limit and quick loss of coherence of the lump below the plastic limit indicate either inorganic silts or plasticity of organic silts such as loess-type silts and organic clays which occur below the A-line.

Highly organic clays have a very white and spongy feel at the plastic limit.

UNIFIED SOIL CLASSIFICATION SYSTEM

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - BND

TABLE
C-1

TUBRO NATIONAL, INC.

APPENDIX D

Lake Valley
Study Area Photographs




Older Lacustrine Shoreline Deposit (Aols), distributed within the central valley basin, northern Lake Valley; Class I, coarse aggregate source (Field Station 32)

LAKE VALLEY STUDY AREA PHOTOGRAPH

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - BMO

FIGURE
D-1

FUGRO NATIONAL, INC.

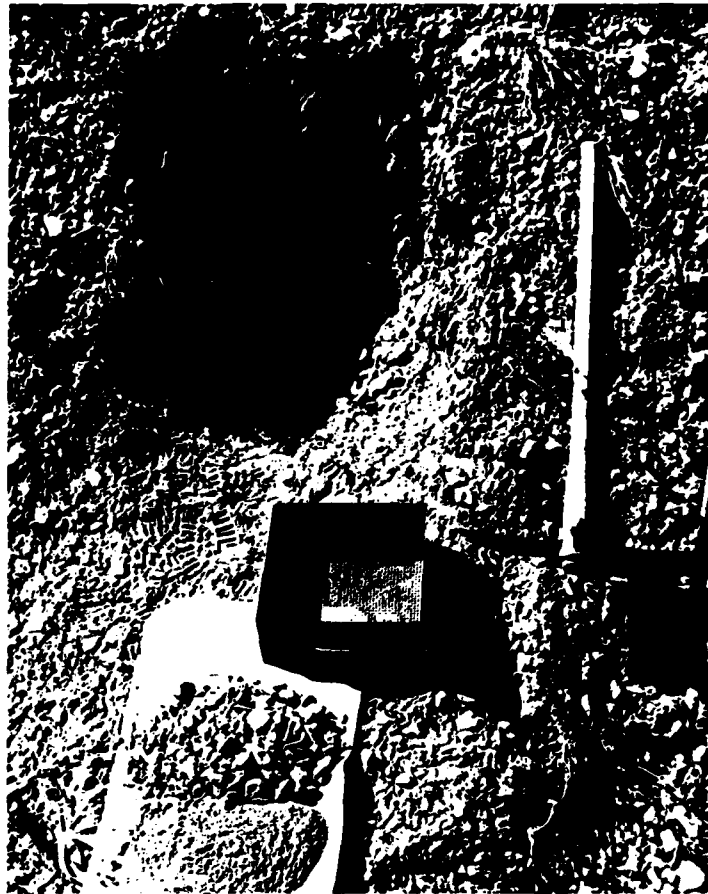

Alluvial Fan Deposit (Aafs) exposed in northeastern Lake Valley;
Class I coarse aggregate source (Station 21)

LAKE VALLEY STUDY AREA PHOTOGRAPH

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - SMO

FIGURE
D-2

FUGRO NATIONAL, INC.



Prospect Mountain Quartzite (Qtz) exposed within the Pioche Hills;
in the southwestern part of the study area; Class I crushed rock
aggregate source (Station 45)

LAKE VALLEY STUDY AREA PHOTOGRAPH

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - BMO

FIGURE
D-3

FUGRO NATIONAL, INC.

27 FEB 81



Laketown Dolomite (Do) exposed in low hills east of the Schell Creek Range in the northwestern part of the study area; Class I crushed rock aggregate source (Station 38).

LAKE VALLEY STUDY AREA PHOTOGRAPH

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - SMO

FIGURE
D-4

FUGRO NATIONAL, INC.

APPENDIX E

Fugro National Geologic Unit Cross Reference

U ARSA POTENTIAL AGGREGATE SOURCE SYMBOLS

FUGRO NATIONAL GENERAL GEOLOGIC UNIT EXPLANATION


	100%
	Shown in regions where rock is exposed, the areally predominant (greater than 70 percent) rock type is indicated. In those areas where two rock types occur the predominant rock type is shown followed by the subordinate rock type (e.g. S_{sp}/I_1). Rock may be subdivided into subtypes (e.g. S_{sp}/I_1).
GR	I INTRUSIVE (UNDIFFERENTIATED) Rocks formed by solidification of a molten or partially molten mass
Vu	I₁ Intrusive Plutonic rocks formed by solidification of molten material beneath the surface (e.g. granite, granodiorite, diorite, gabbro)
Vb	I₂ Extrusive (intermediate and acidic) Volcanic rocks of intermediate and acidic composition formed by solidification of molten material at or near the surface (e.g. rhyolite, latite, dacite, andesite)
Vu	I₃ Extrusive (basic) Volcanic rocks of basic composition generally formed by solidification of molten material at or near the surface (e.g. basalt)
Su	I₄ Extrusive (pyroclastic) Rocks formed by accumulation of volcanic ejecta (e.g. ash fall, welded tuff, agglomerate)
Su, Qtz	S SEDIMENTARY (UNDIFFERENTIATED) Rocks formed by accumulation of clastic solids, organic solids and/or chemically precipitated minerals
Ls, Do, Cau	S₁ Sandstone and/or Siliceous Rocks Composed of sand size particles (e.g. sandstone, orthoquartzite) or of crysalline siliceous solids (e.g. chert)
	S₂ Carbonate Rocks Composed predominantly of calcium carbonate particles or chemical precipitates (e.g. limestone, dolomite, shale)
	S₃ Argillaceous Rocks Composed of clay and silt-size particles (e.g. siltstone, shale, claystone)
	S₄ Evaporite Rocks Precipitated from solution as a result of evaporation (e.g. halite, gypsum, anhydrite, selenite)
Su	S₅ Coarse Clastic Rocks Composed of gravel-sized or larger clasts (e.g. conglomerate, breccia)
Mu	M METAMORPHIC (UNDIFFERENTIATED) Rocks formed through recrystallization in the solid state of preexisting rocks by heat and pressure
Mu	M₁ Coarse grained rocks formed by higher-grade regional metamorphism (either banded or granular) (e.g. gneiss, granulite, amphibolite)
Mu	M₂ Fine grained schistose rocks formed by lower grade regional metamorphism (e.g. schist, slate, phyllite)
Mu	M₃ Metacrystalline rocks formed chiefly by contact metamorphism (e.g. hornfels, marble)
Qtz	M₄ Metapelite rocks formed by metamorphism of highly siliceous rocks
	MAJOR-FILL
Aal	A MAJOR-FILL DEPOSITS Fill-in coarse-grained materials deposited principally by wind, water or gravity
Au, Aal	A₁ Younger Fluvial Deposits Major modern stream channel and flood-plain deposits
Au	A₂ Older Fluvial Deposits Older incised stream channel and flood-plain deposits in elevated terraces bordering major modern drainages
Aol	A₃ Eolian Deposits Wind-blown deposits of sand occurring as either thin sheets (A_{3s}) or dunes (A_{3d})
Aaf	A₄ Playa and Lacustrine Deposits Deposits occurring in modern active playas (A_{4a}) or in either inactive playas or older lake beds and abandoned shorelines associated with extinct lakes (A_{4b})
Au	A₅ Alluvial Fan Deposits Alluvial deposits consisting of debris fan and water-laid alluvium near mountain fronts, grading into predominantly water-laid alluvium deposited in shifting distributary channels near the basin center. Younger (A_{5y}) intermediate (A_{5i}) and older (A_{5o}) alluvial fans are differentiated by surface soil development, terrain conditions and present depositional structural environment
Aaf	A₆/A₇ Mixed non-fan units Most locally extensive unit is listed first
	A₆ (A₇) Pyroclastic unit underlies this group of overlapping deposit units


FUGRO NATIONAL GEOLOGIC UNIT CROSS REFERENCE

MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - DMO

FIGURE
E-1

FUGRO NATIONAL INC.

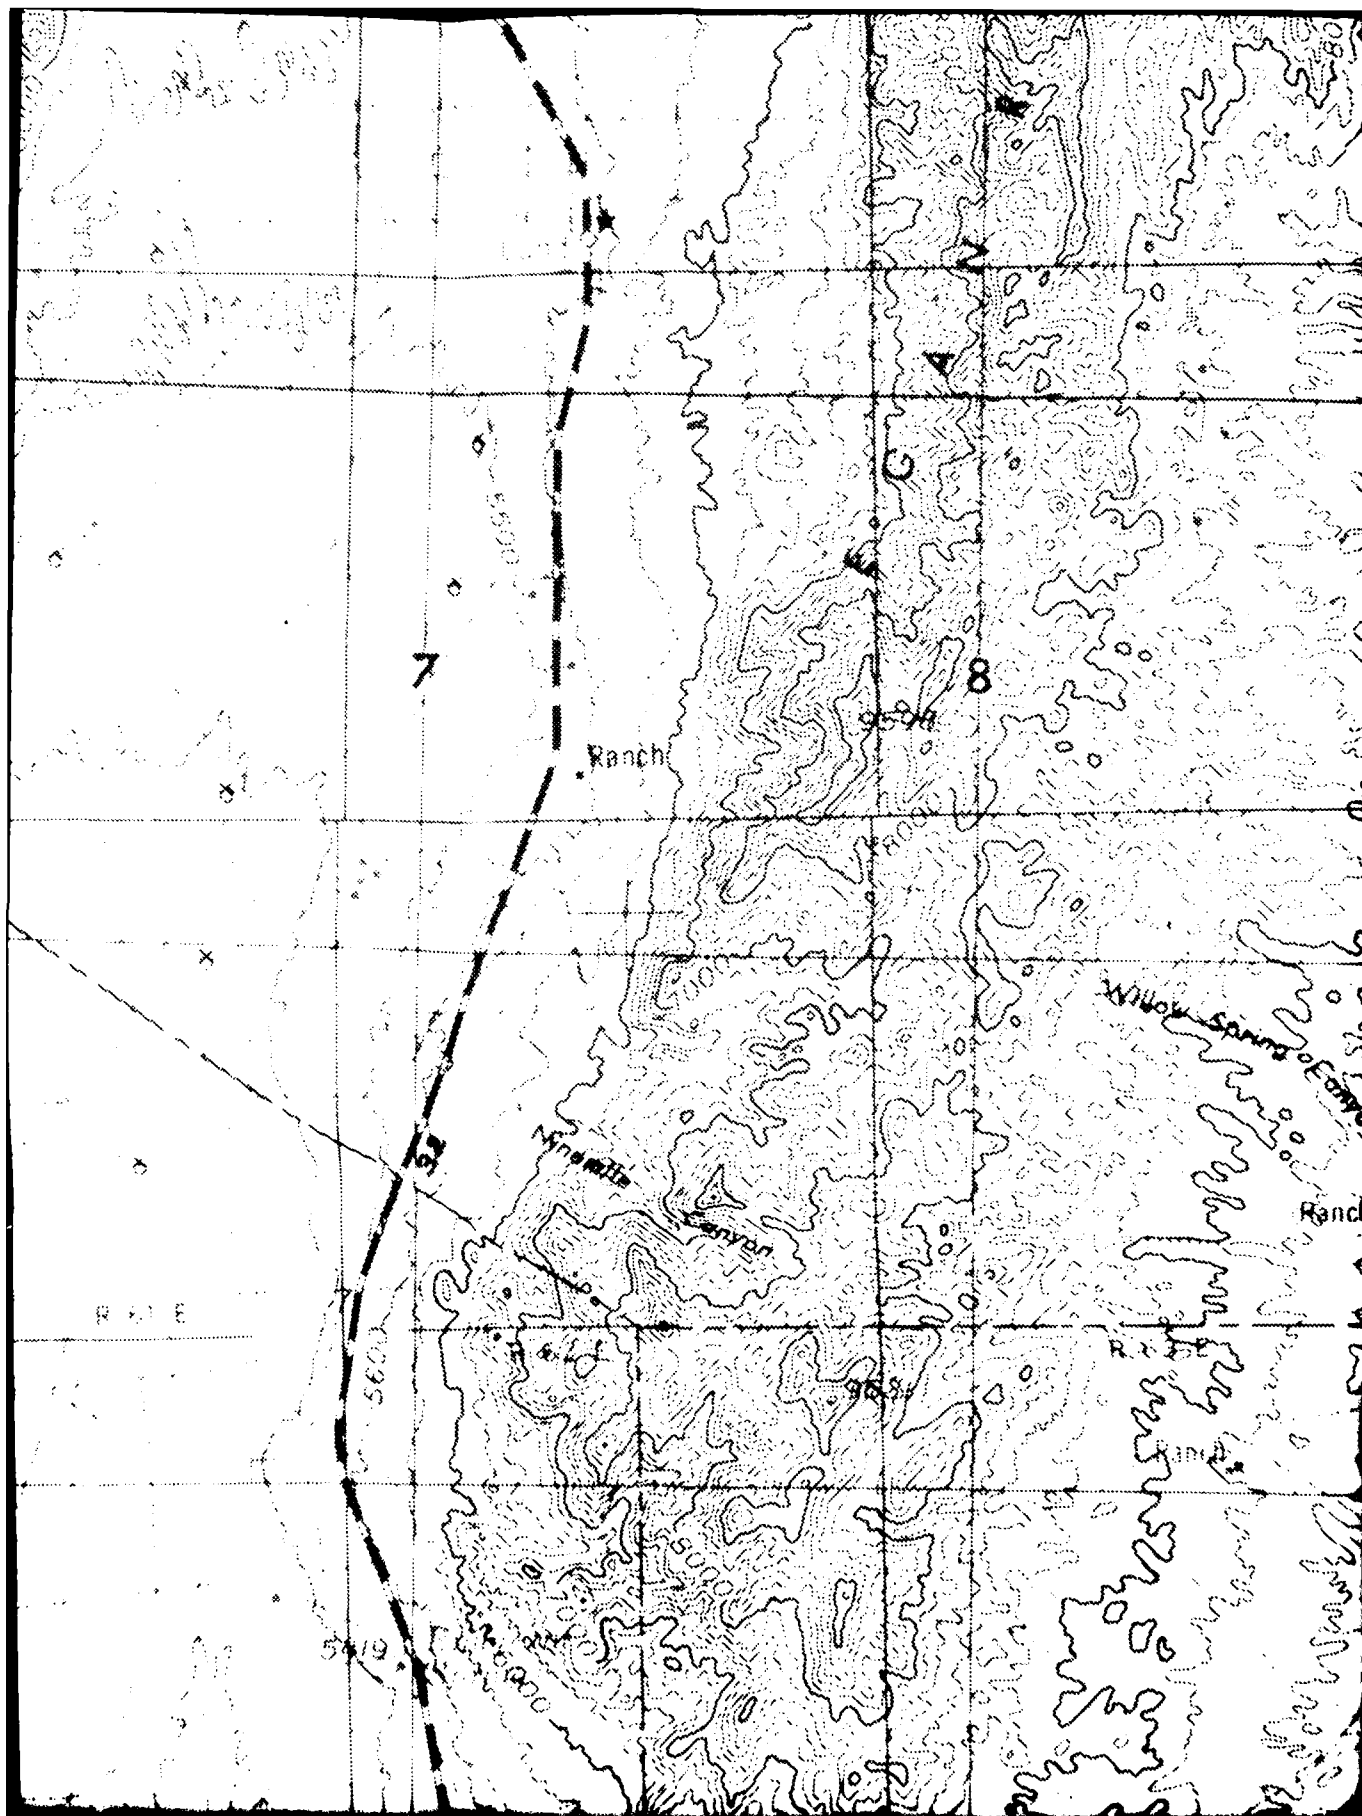

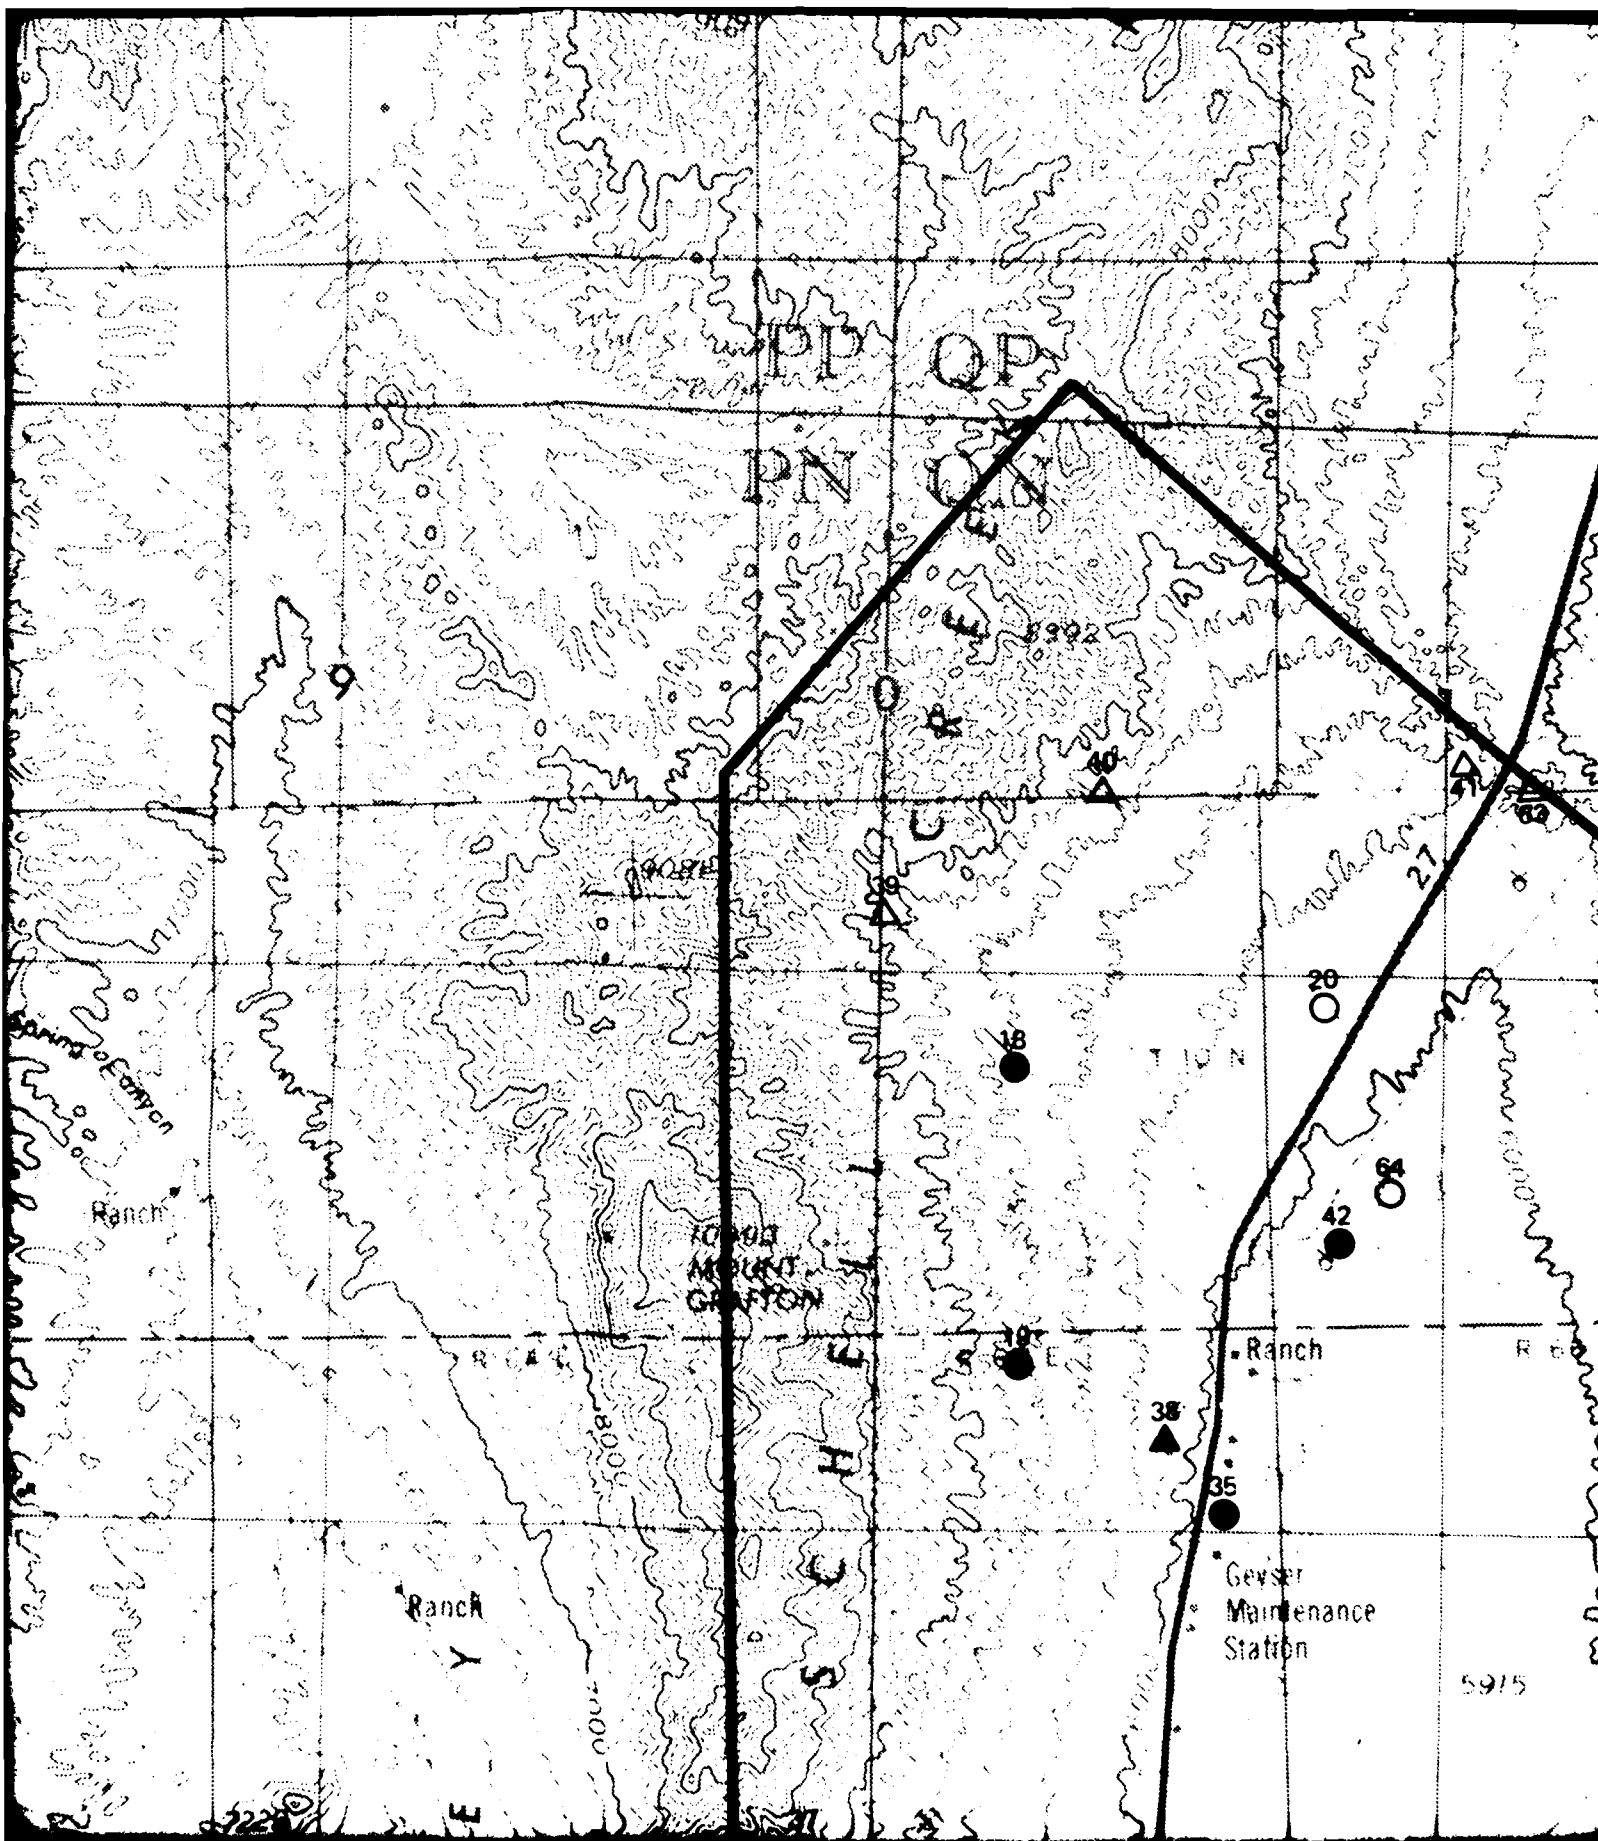


78-A112 705


FUGRO NATIONAL INC LONG BEACH CA
MX SITING INVESTIGATION. GEOTECHNICAL EVALUATION. AGGREGATE RES--ETC(U)
FEB 81 F04704-80-C-0006
UNCLASSIFIED FN-TR-37-F NL


2-2


1-1

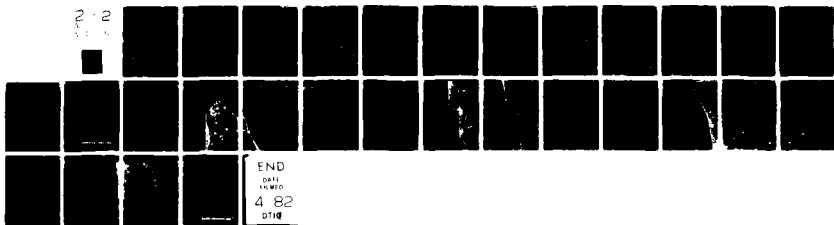


END
DATE
FILMED
4 82
DTIC

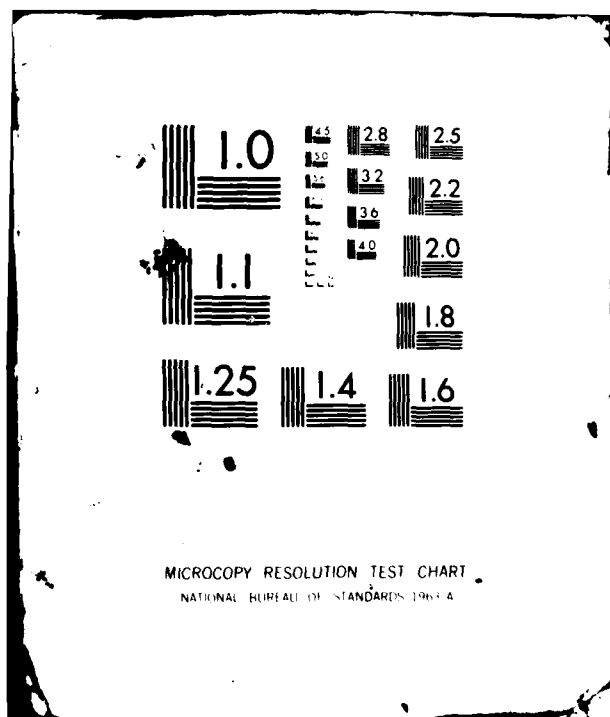


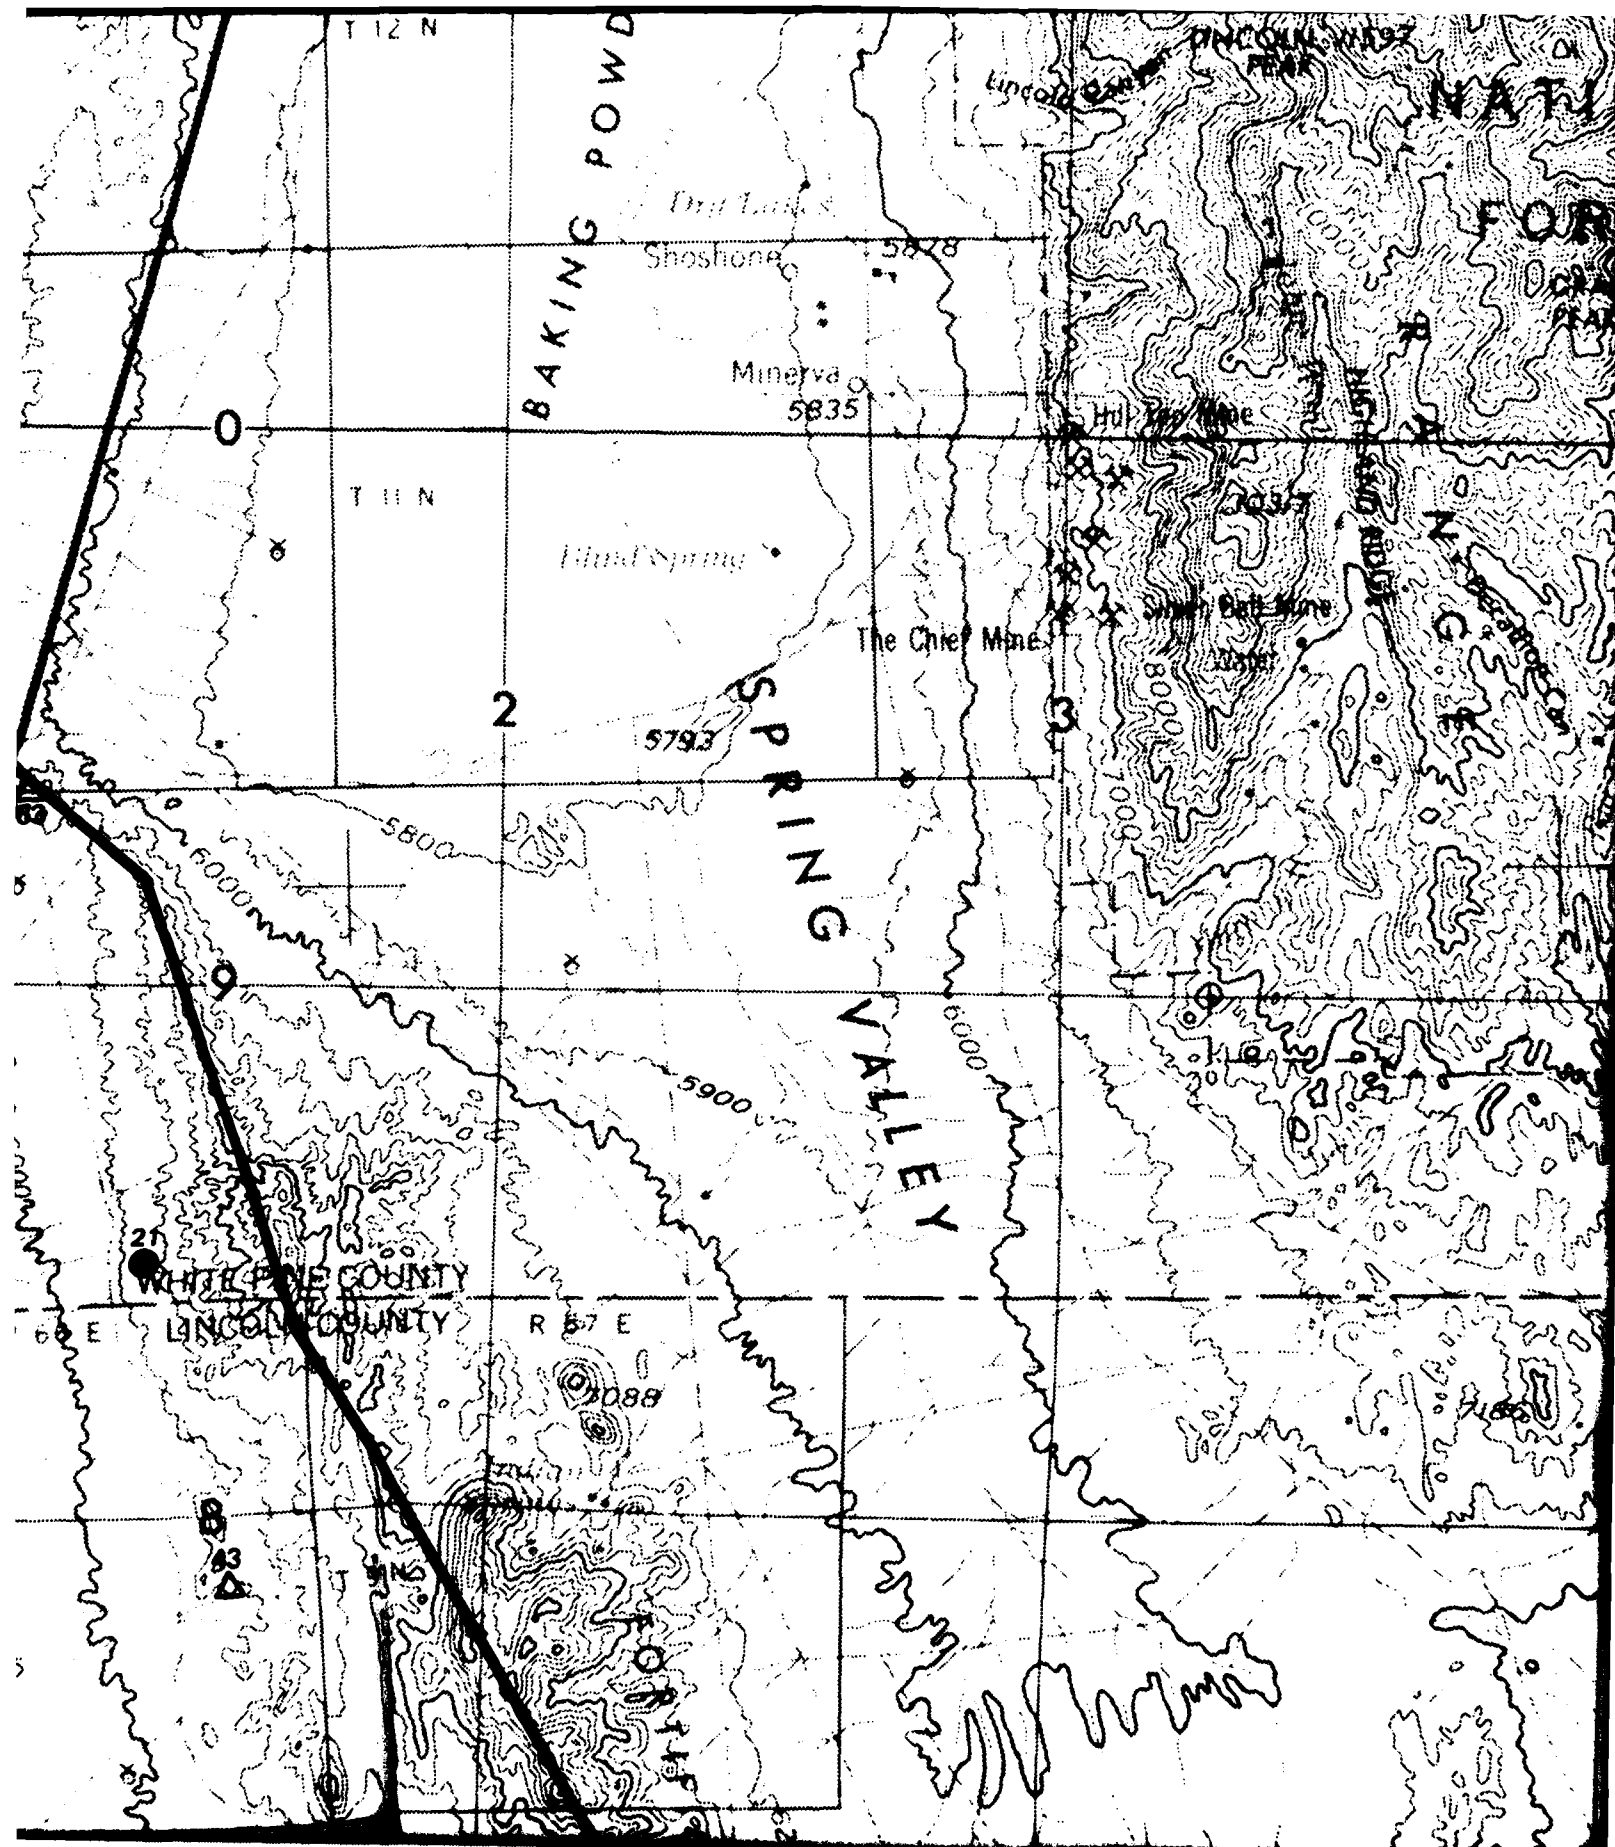


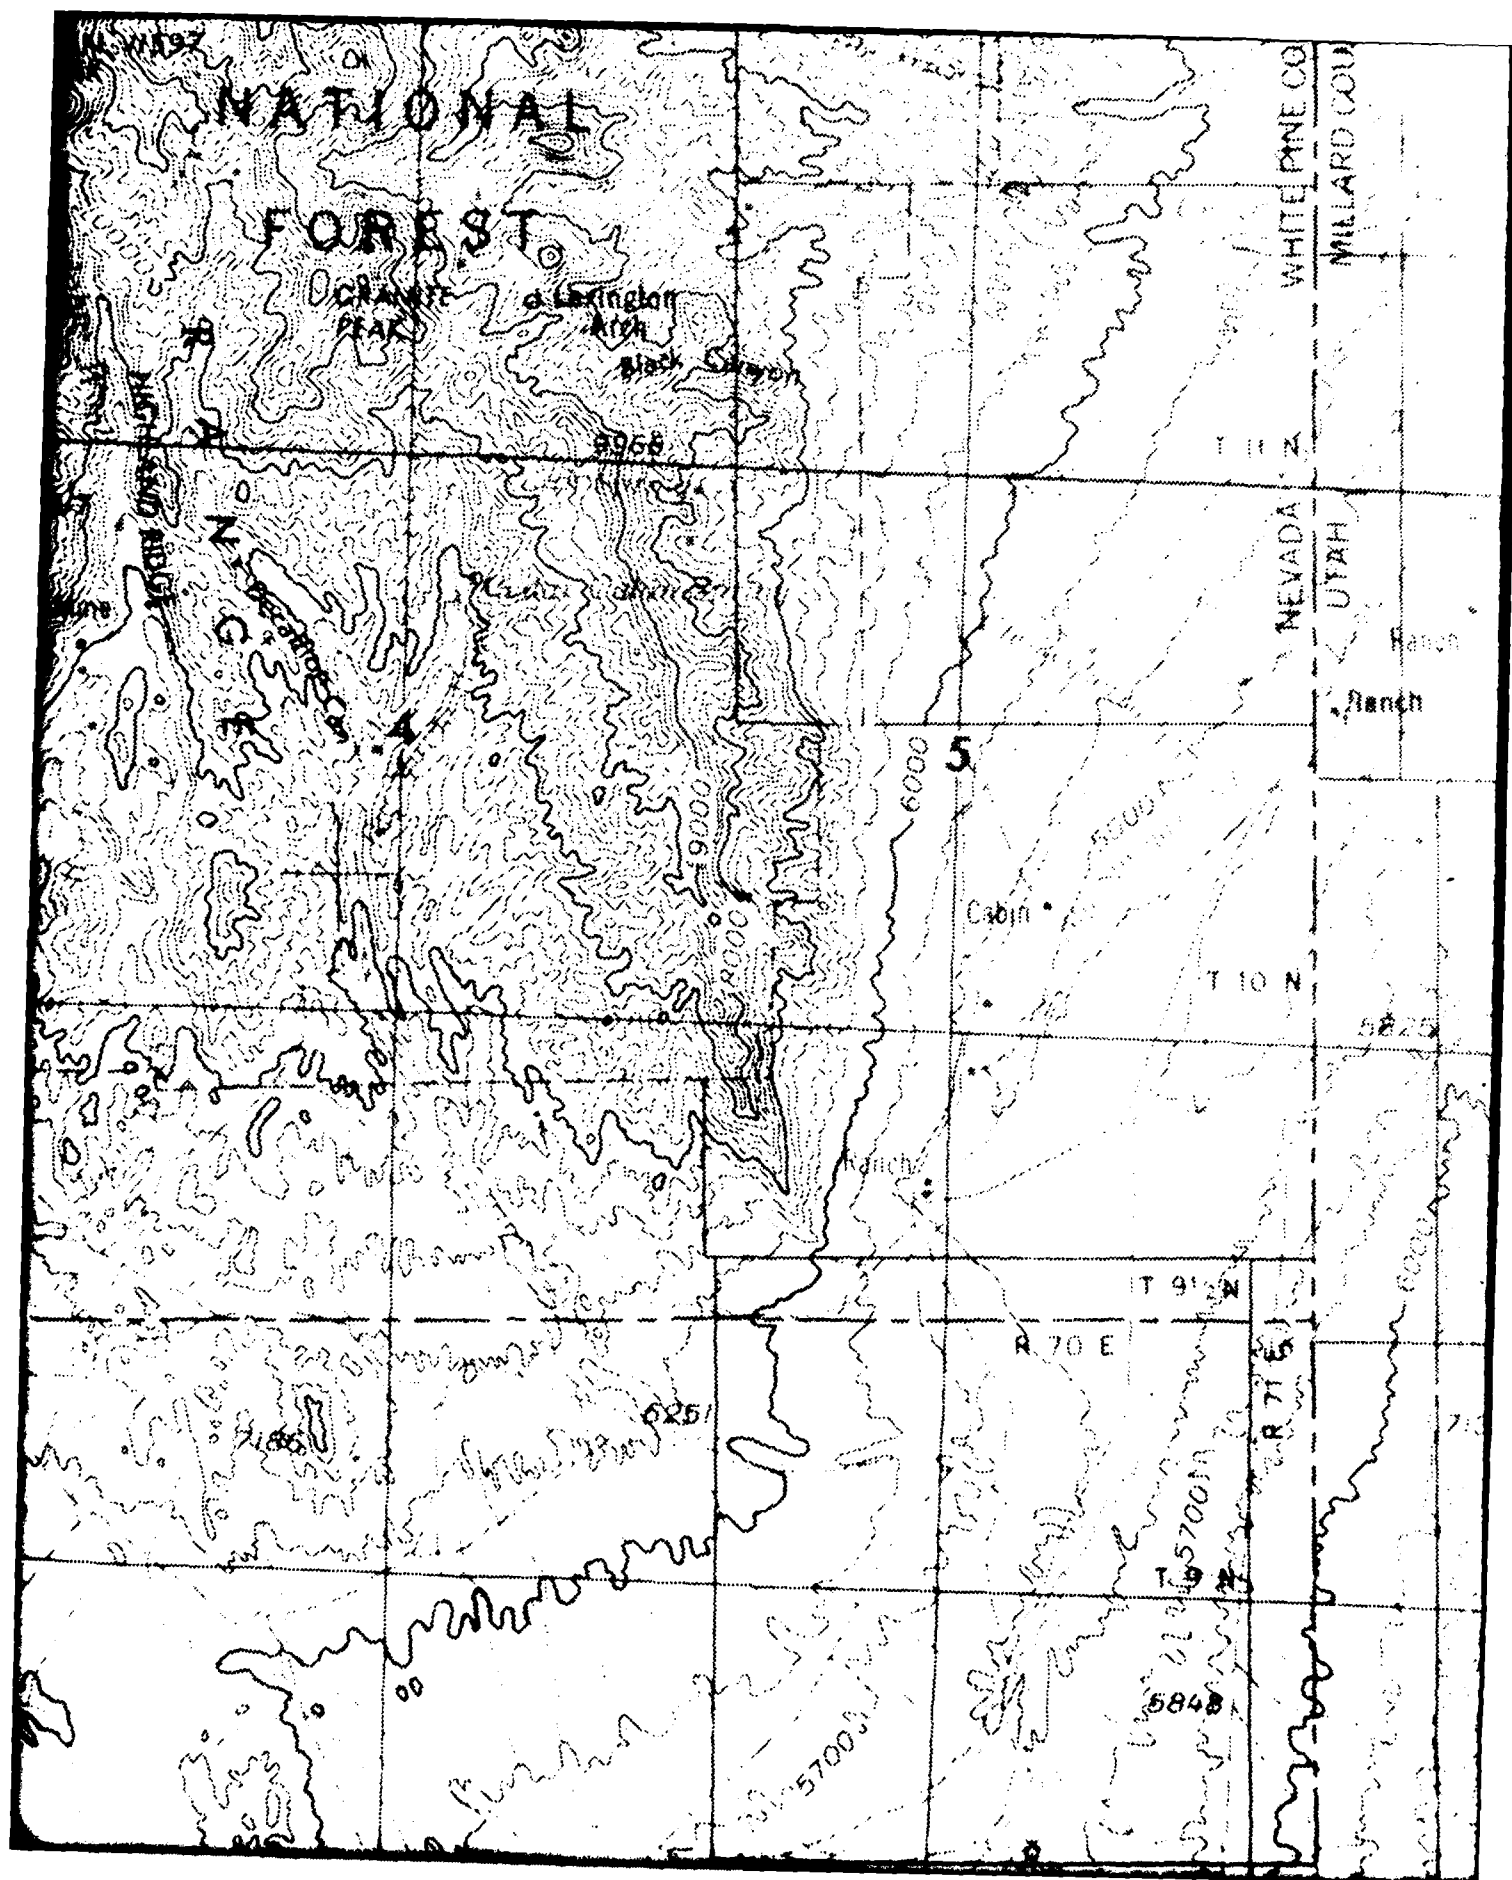


5

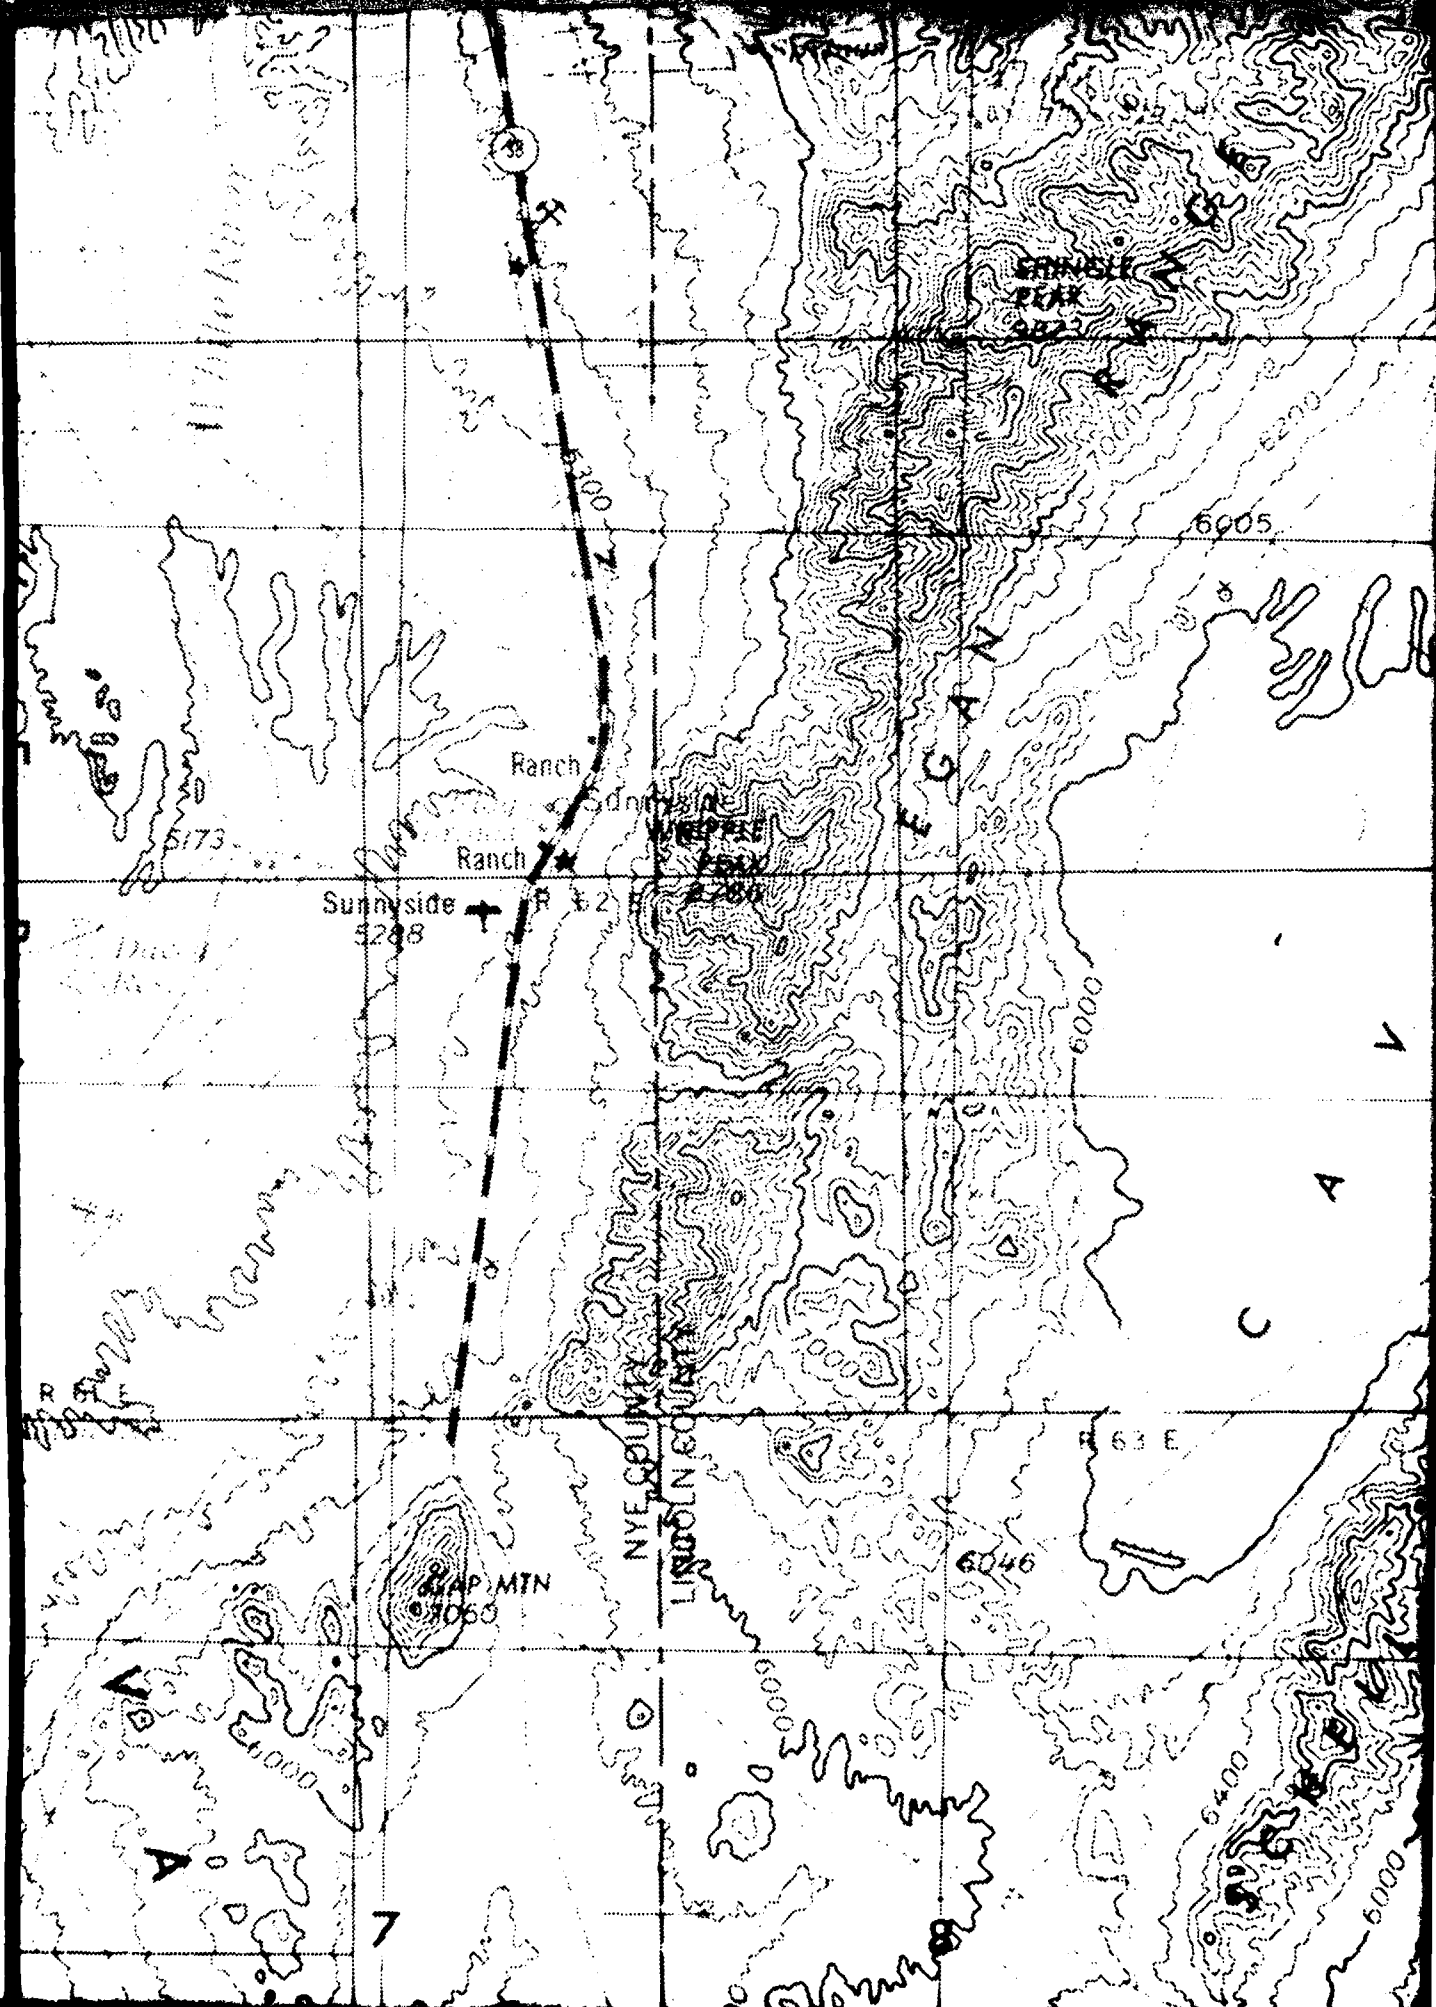


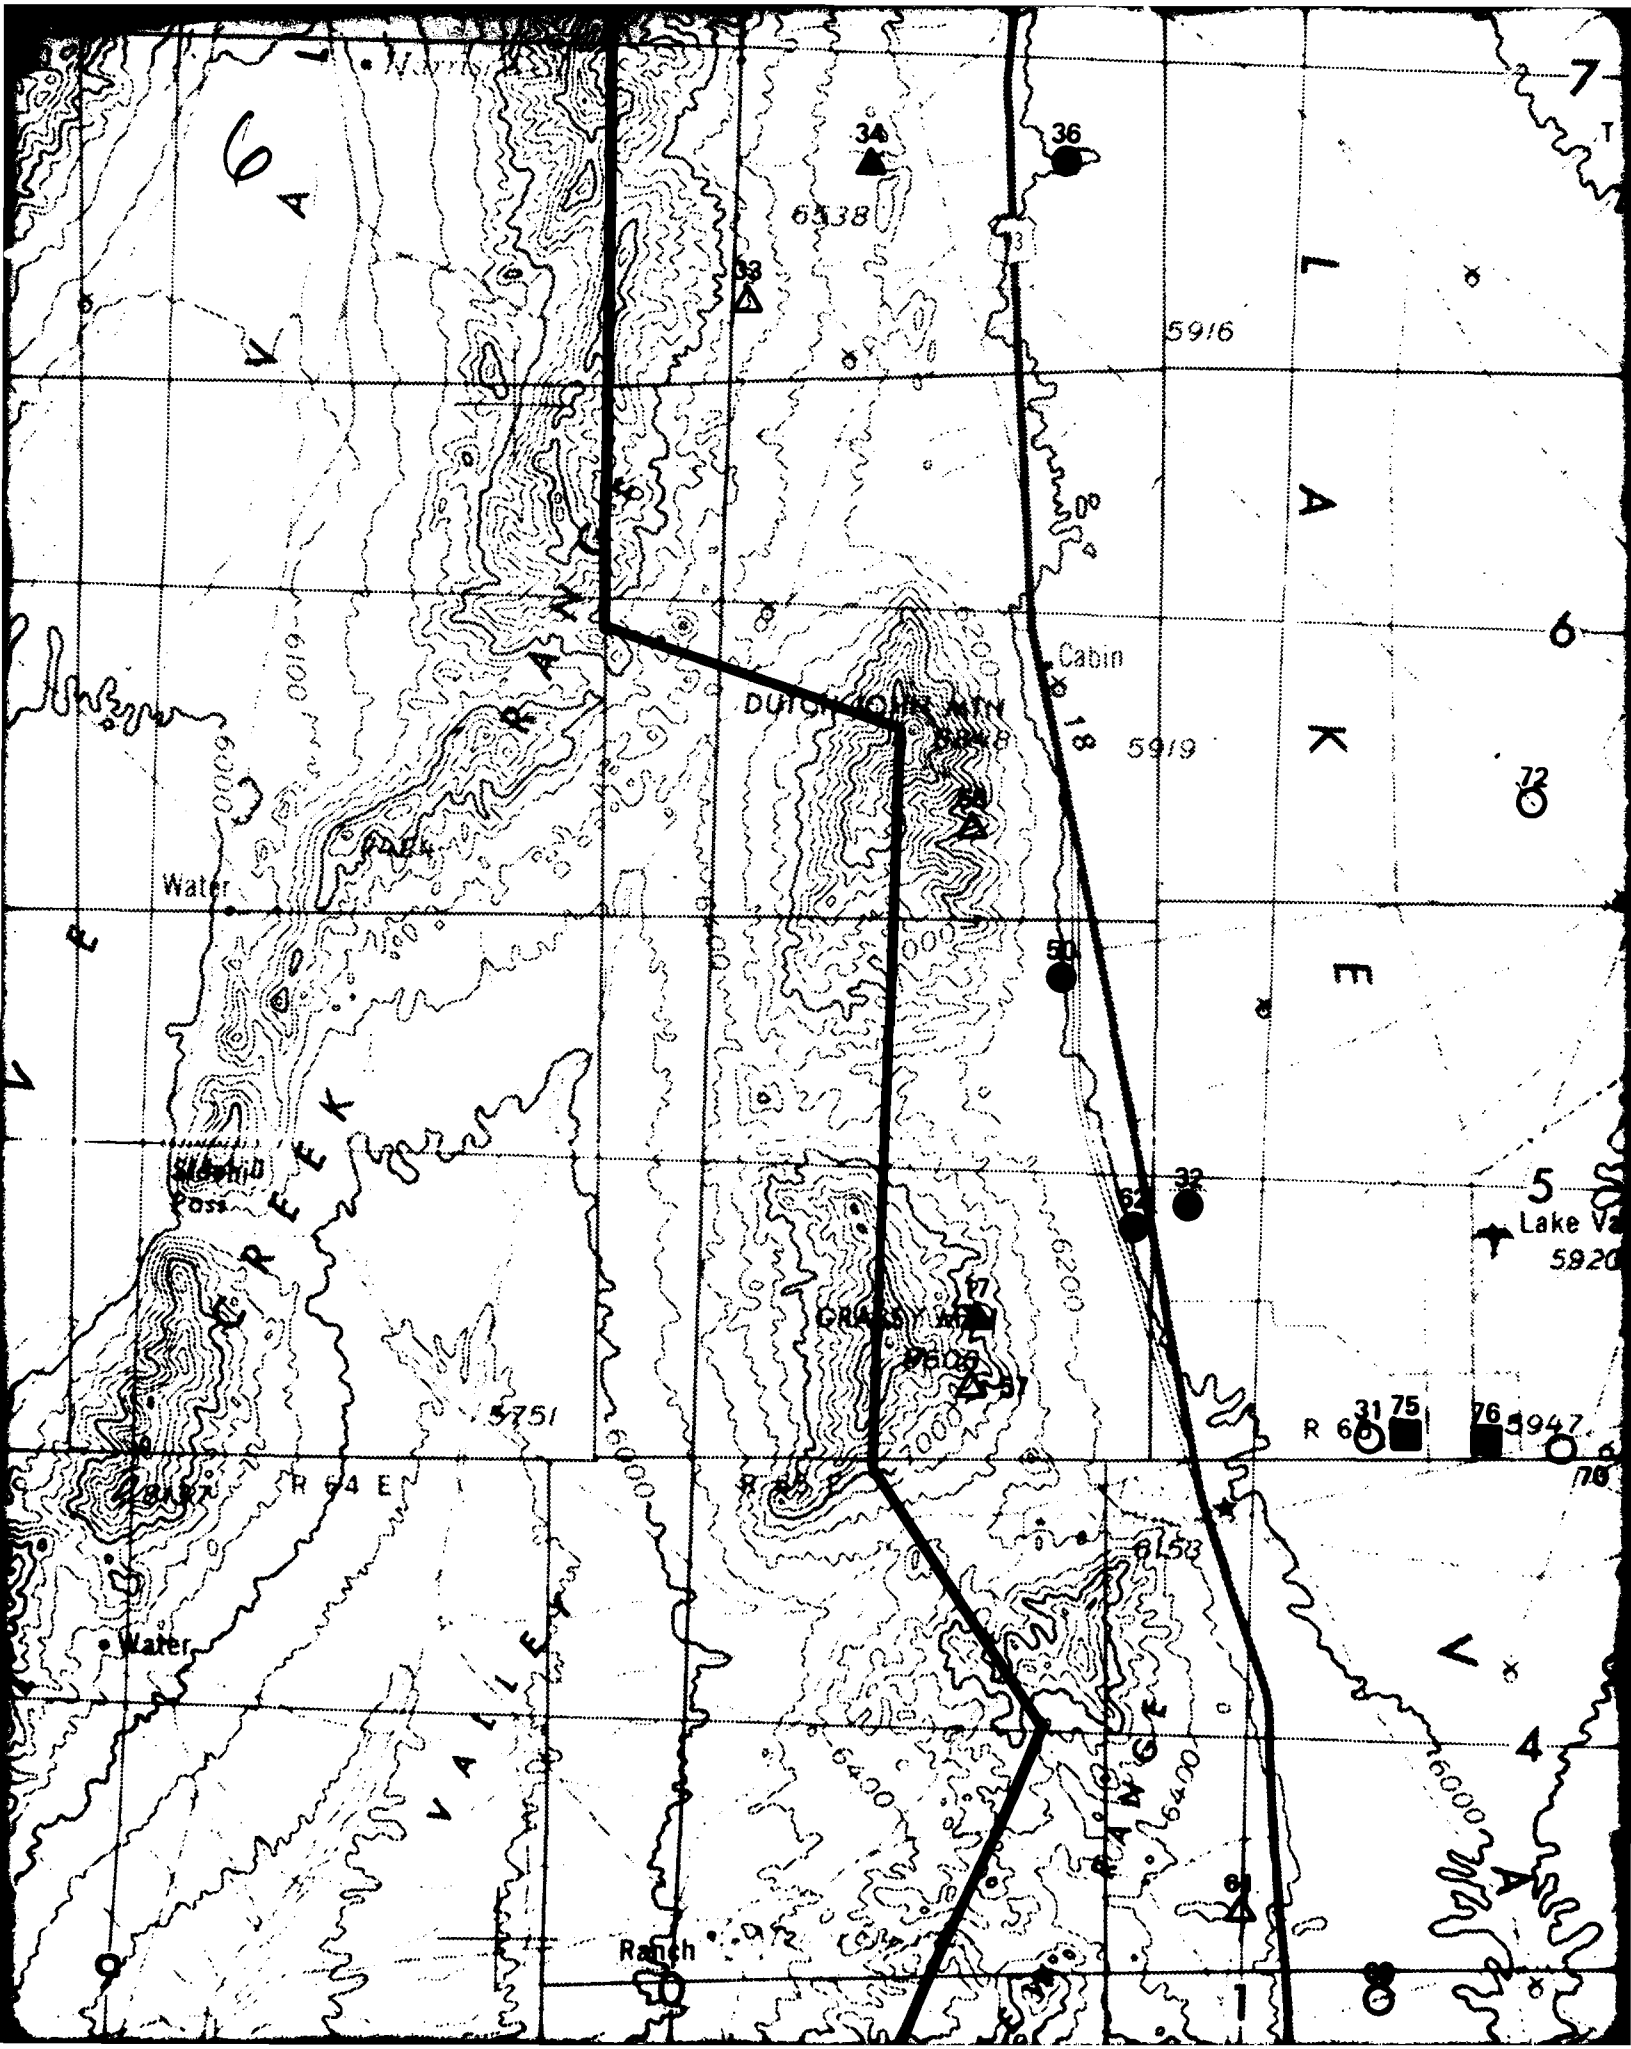

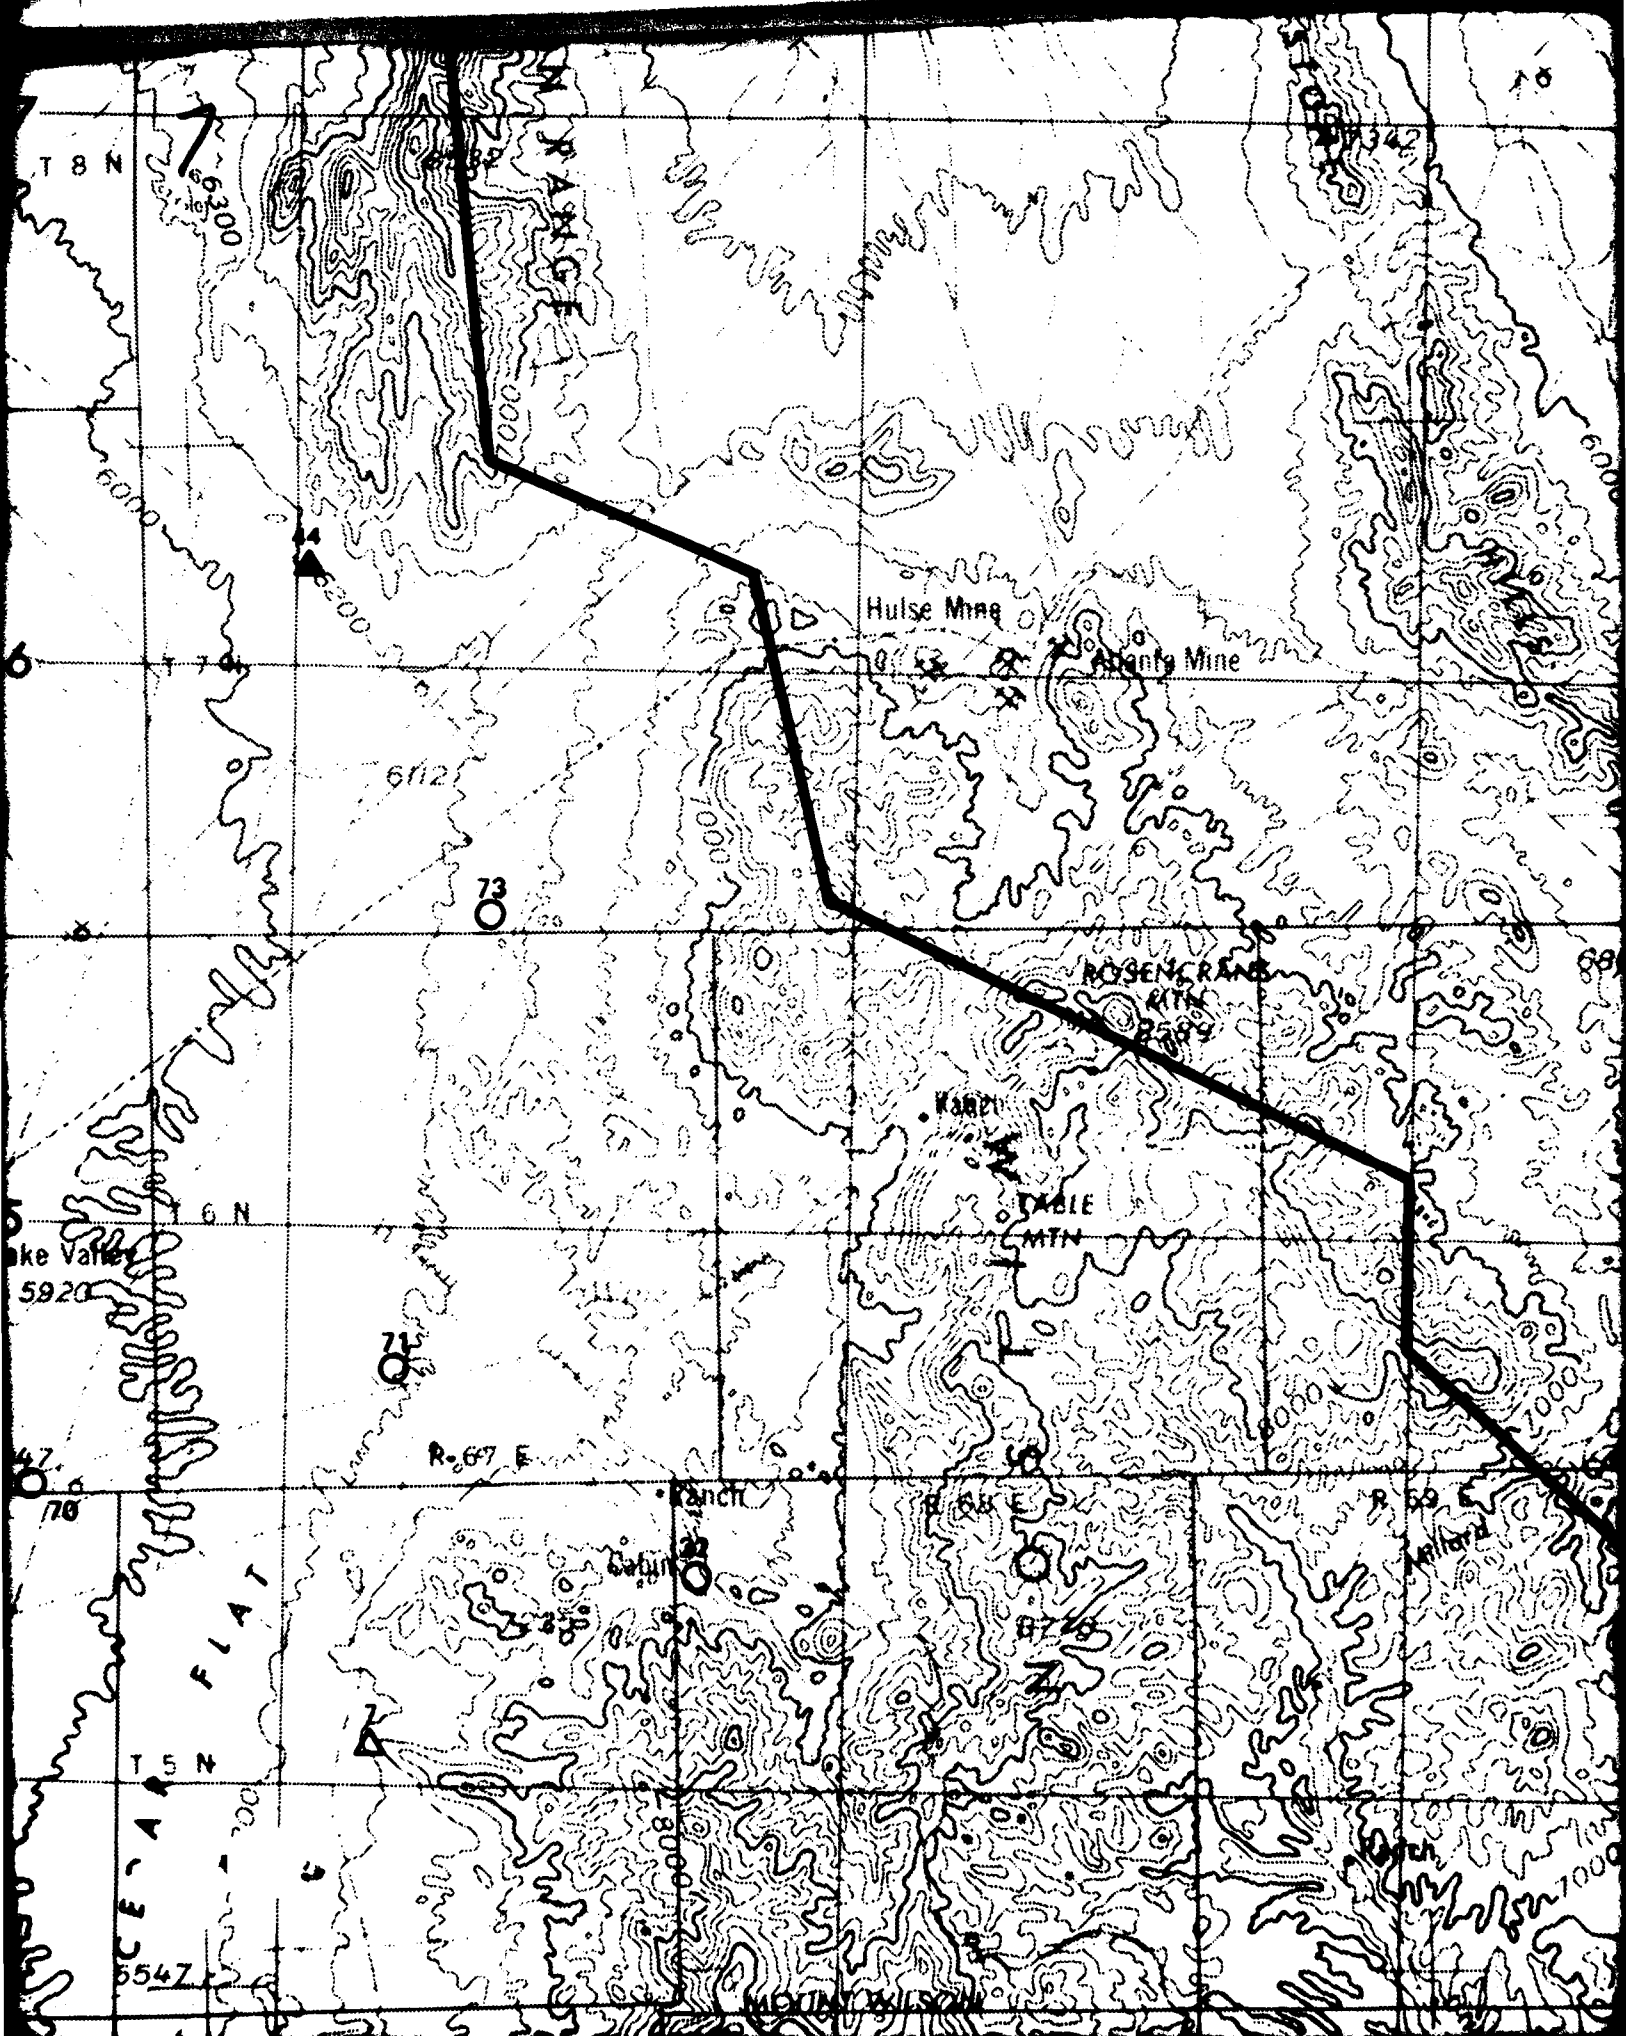

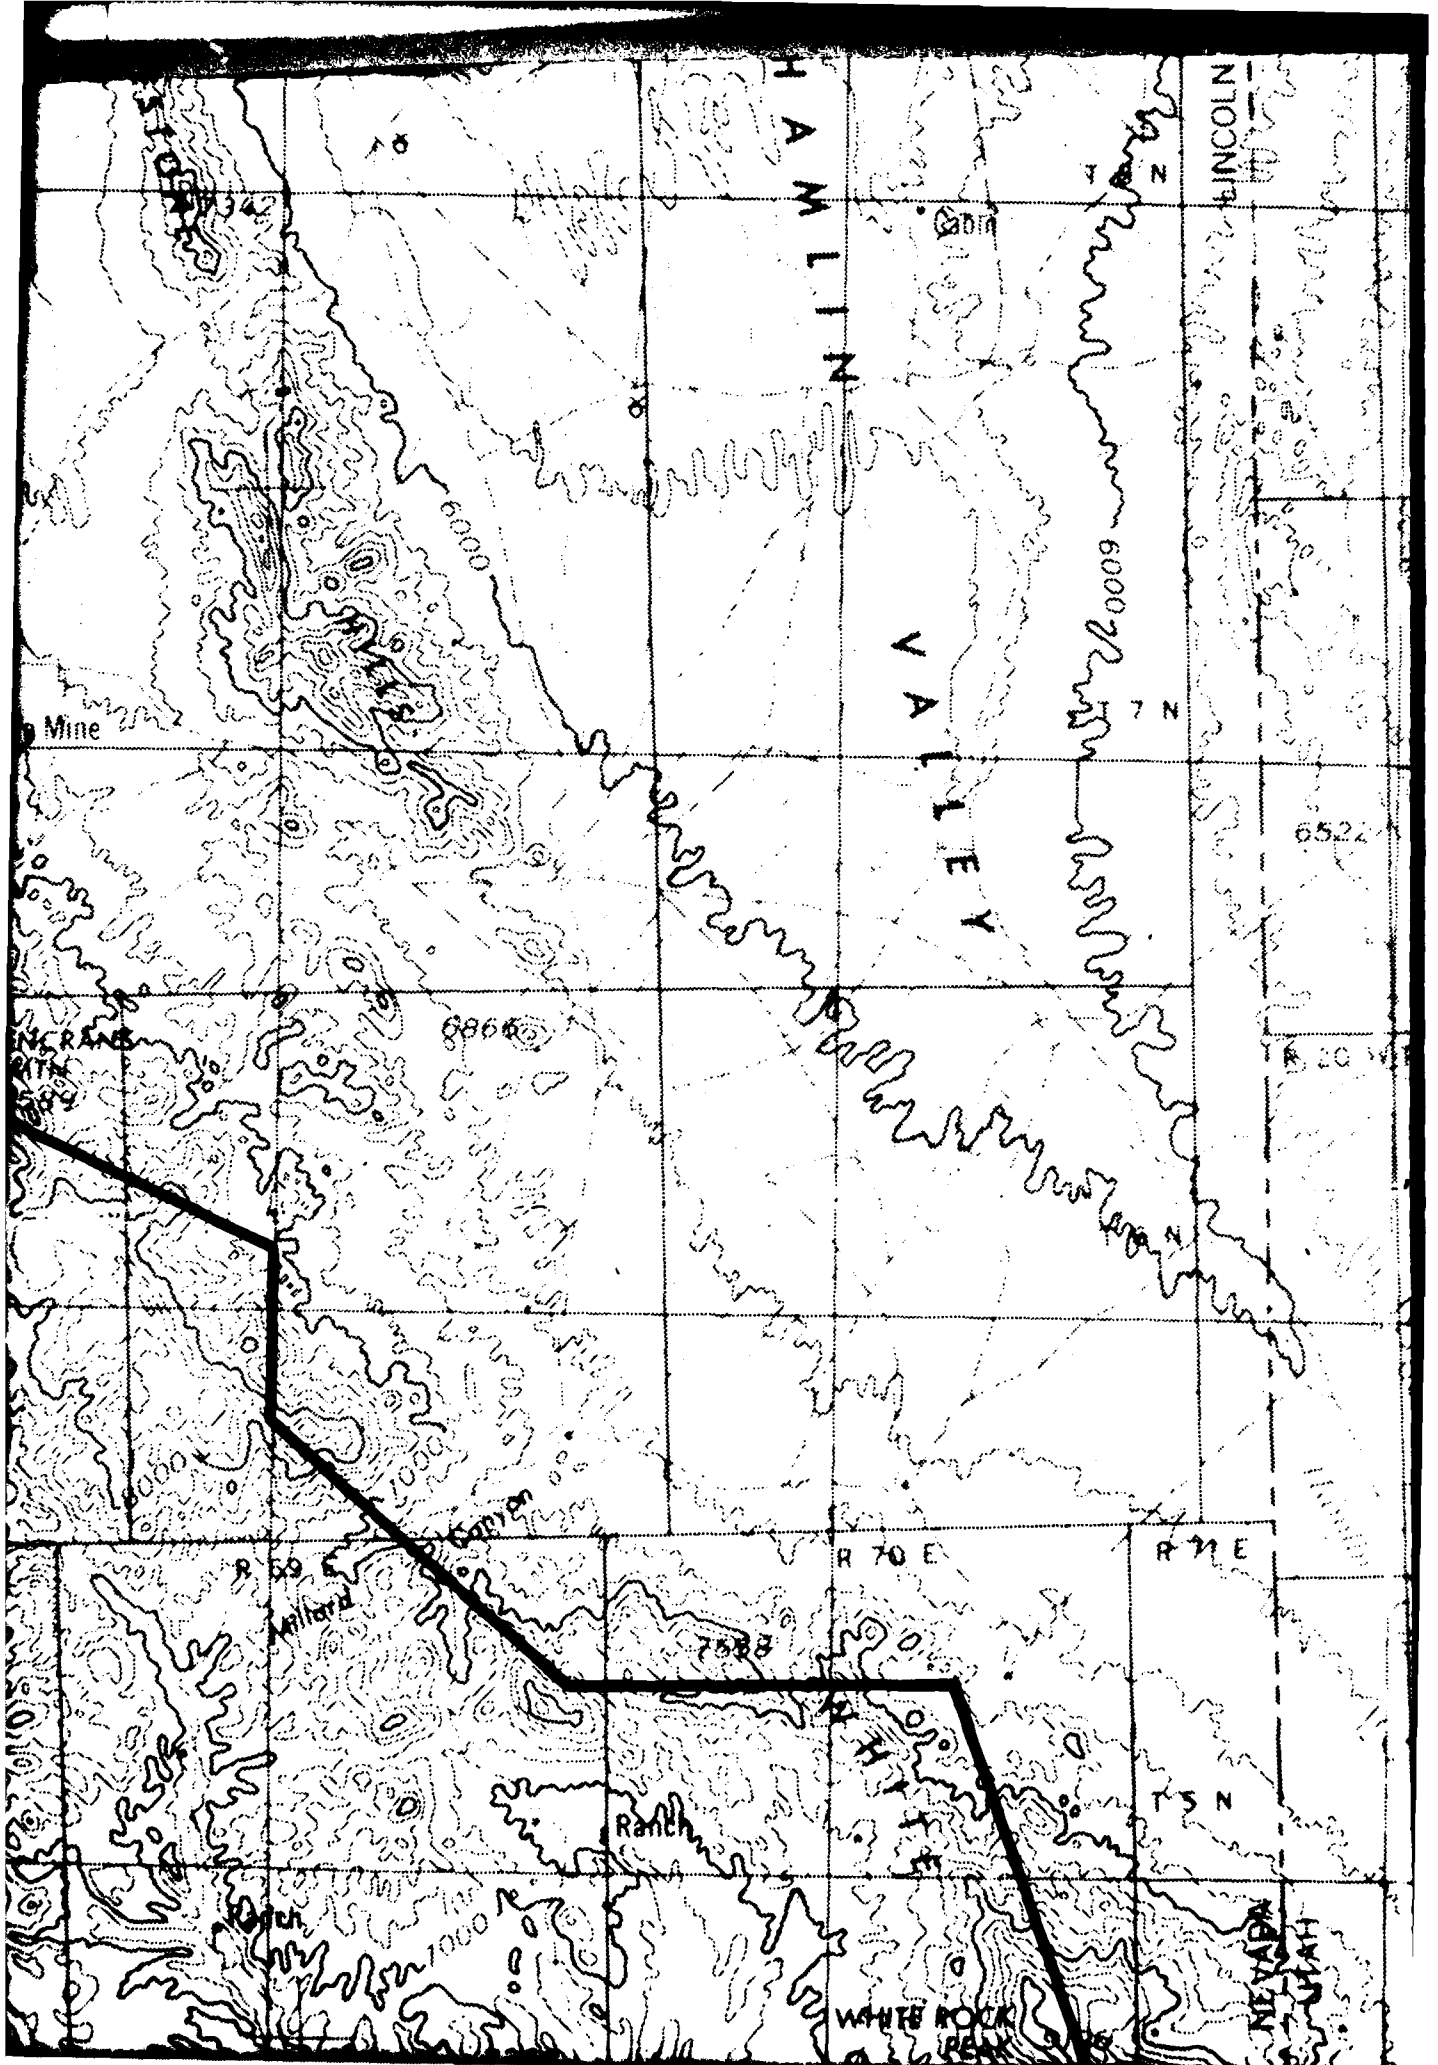

9

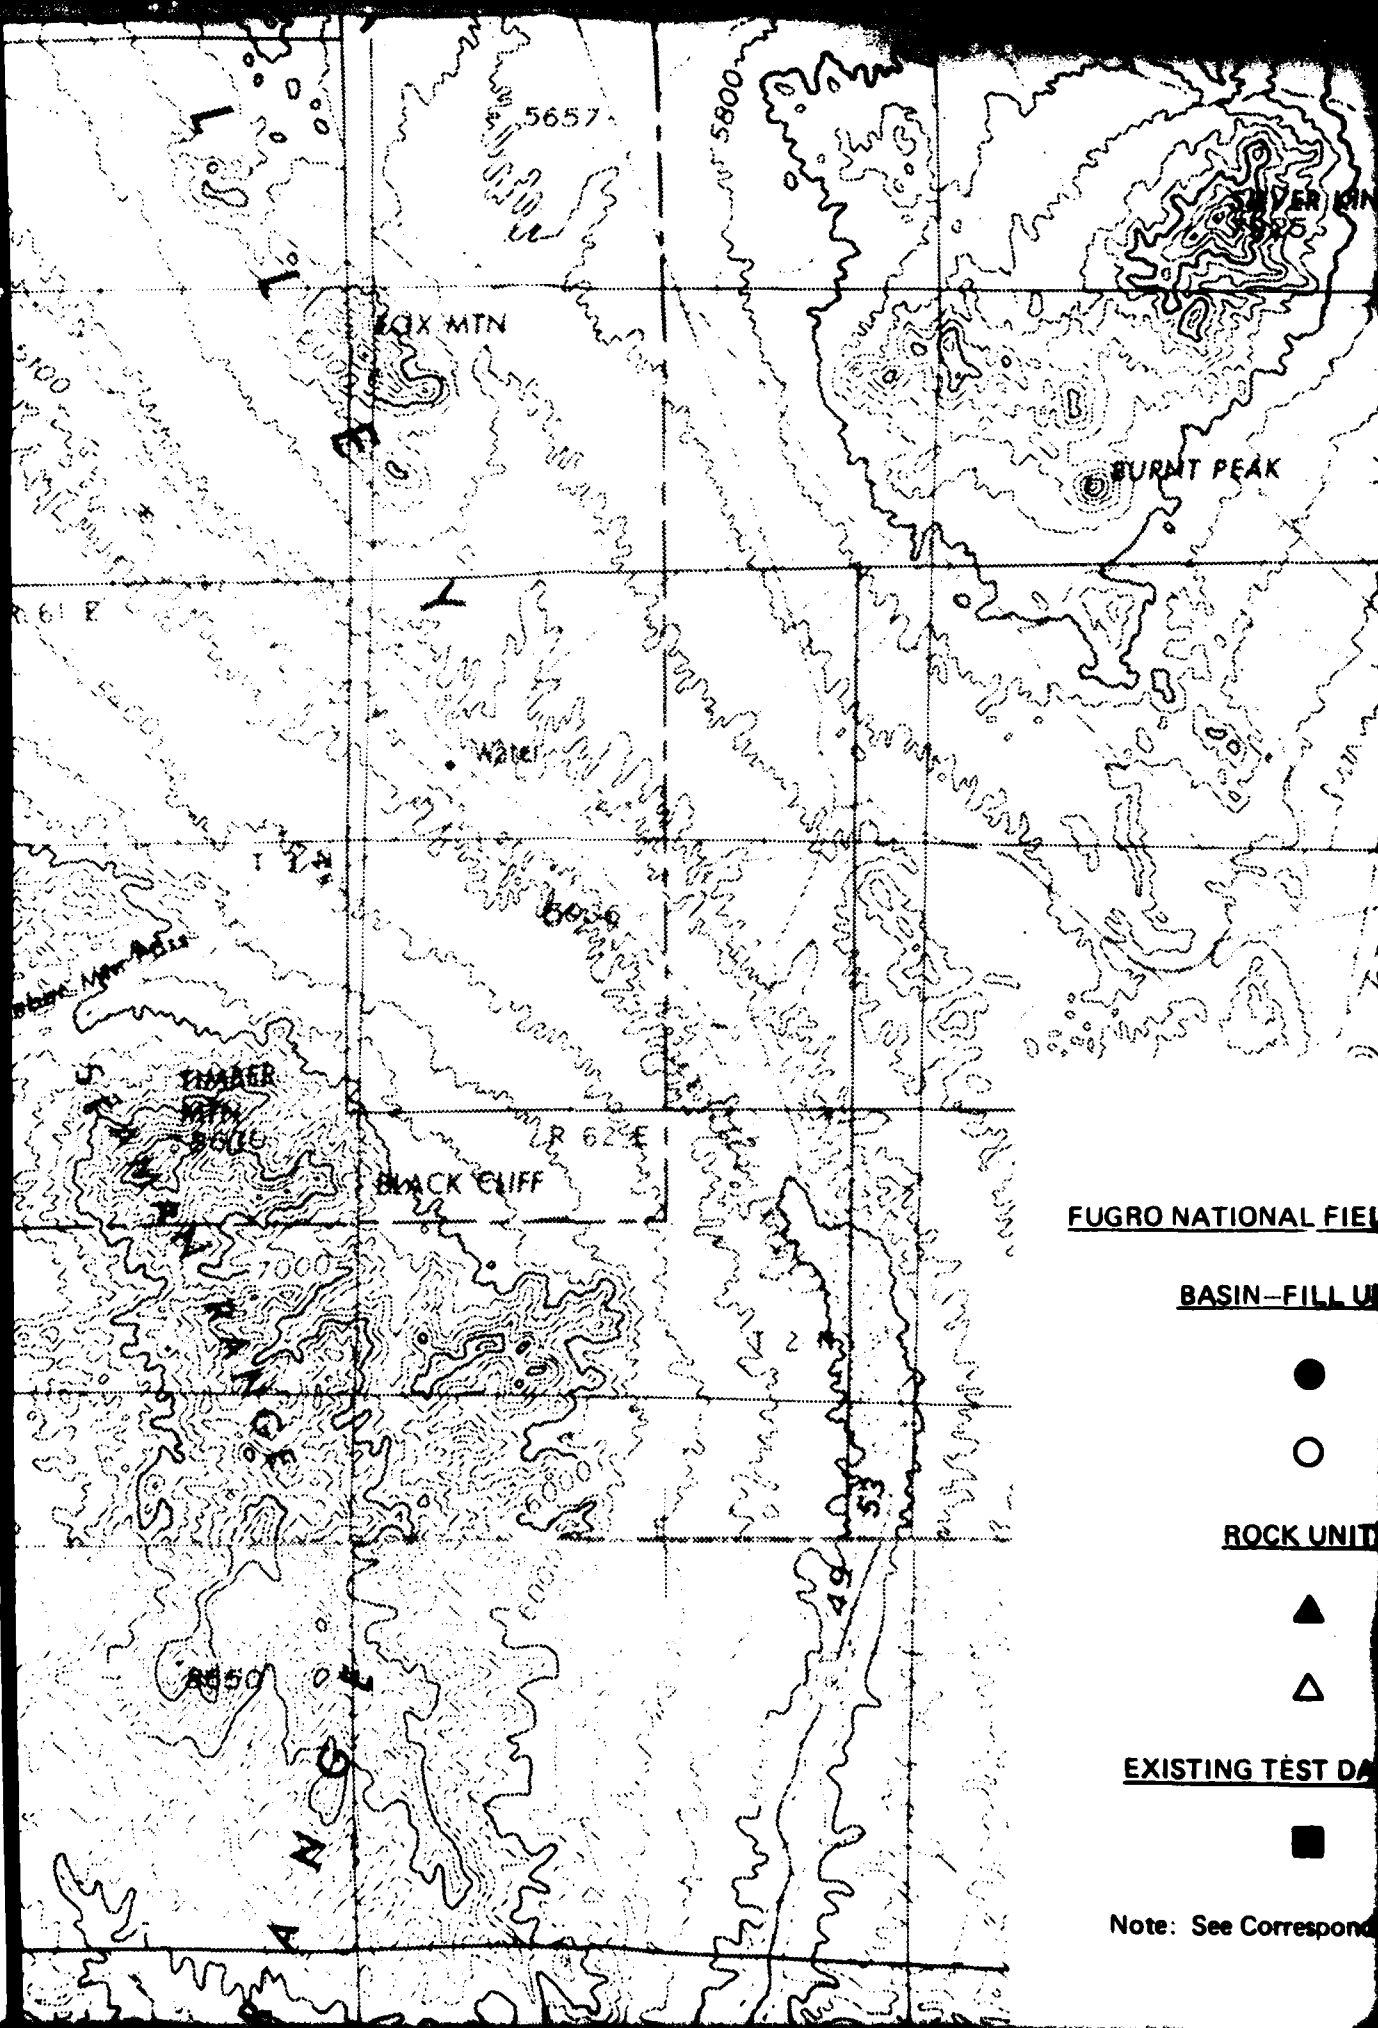

FUGRO NATIONAL FIELD

BASIN-FILL U




ROCK UNIT



EXISTING TEST DA



Note: See Correspond

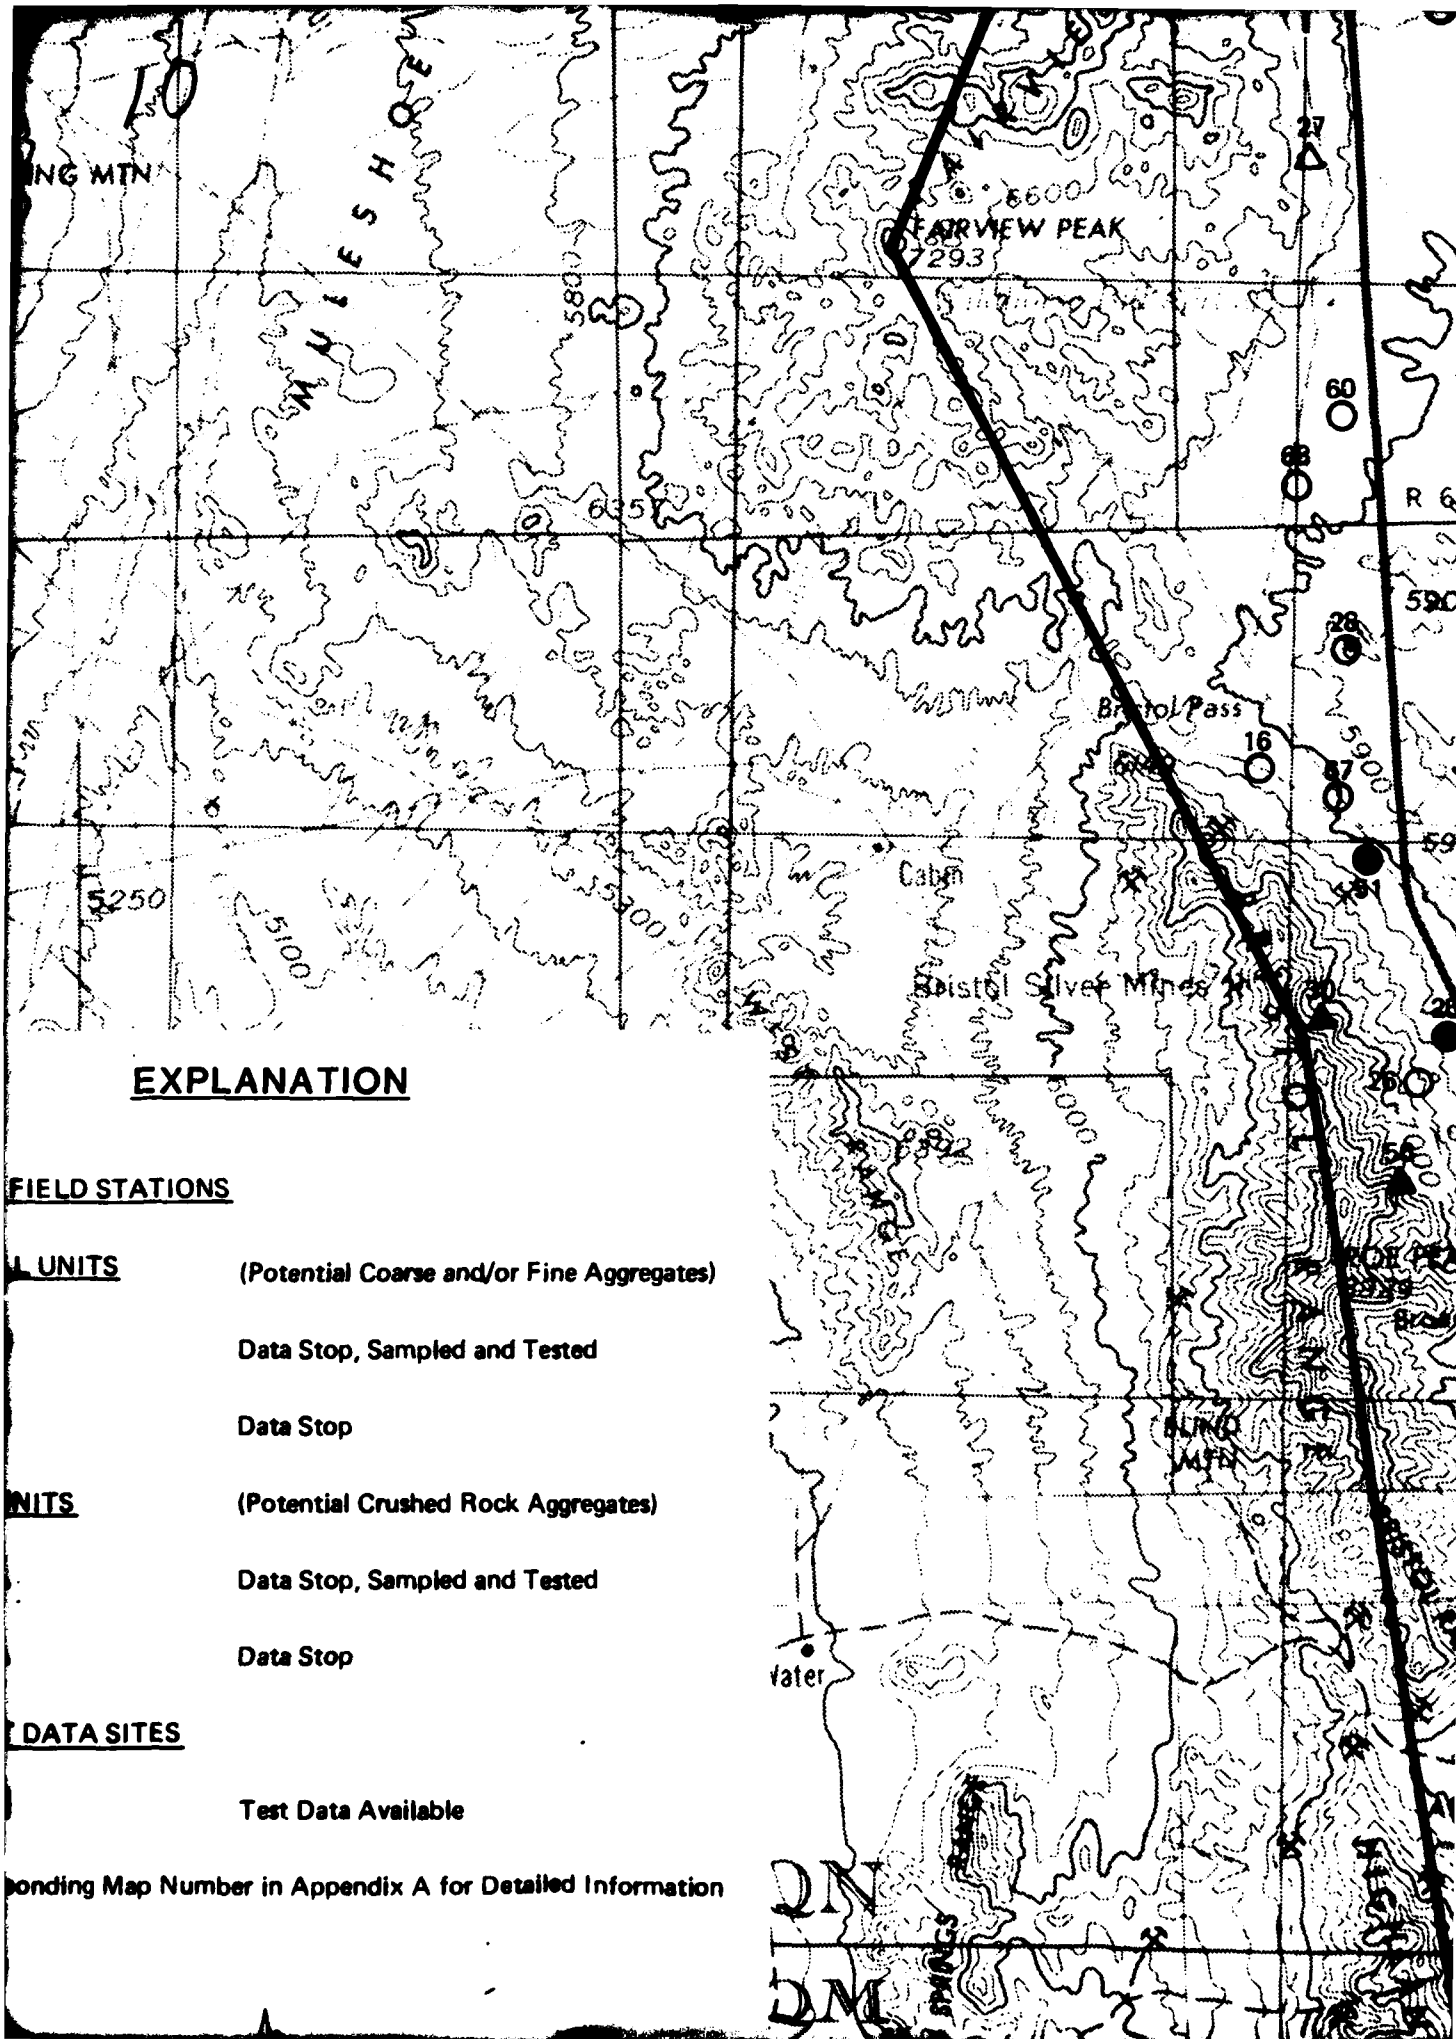

EXPLANATION

FIELD STATIONS

L UNITS

(Potential Coarse and/or Fine Aggregates)

Data Stop, Sampled and Tested

Data Stop

UNITS

(Potential Crushed Rock Aggregates)


Data Stop, Sampled and Tested

Data Stop

DATA SITES

Test Data Available

Consulting Map Number in Appendix A for Detailed Information

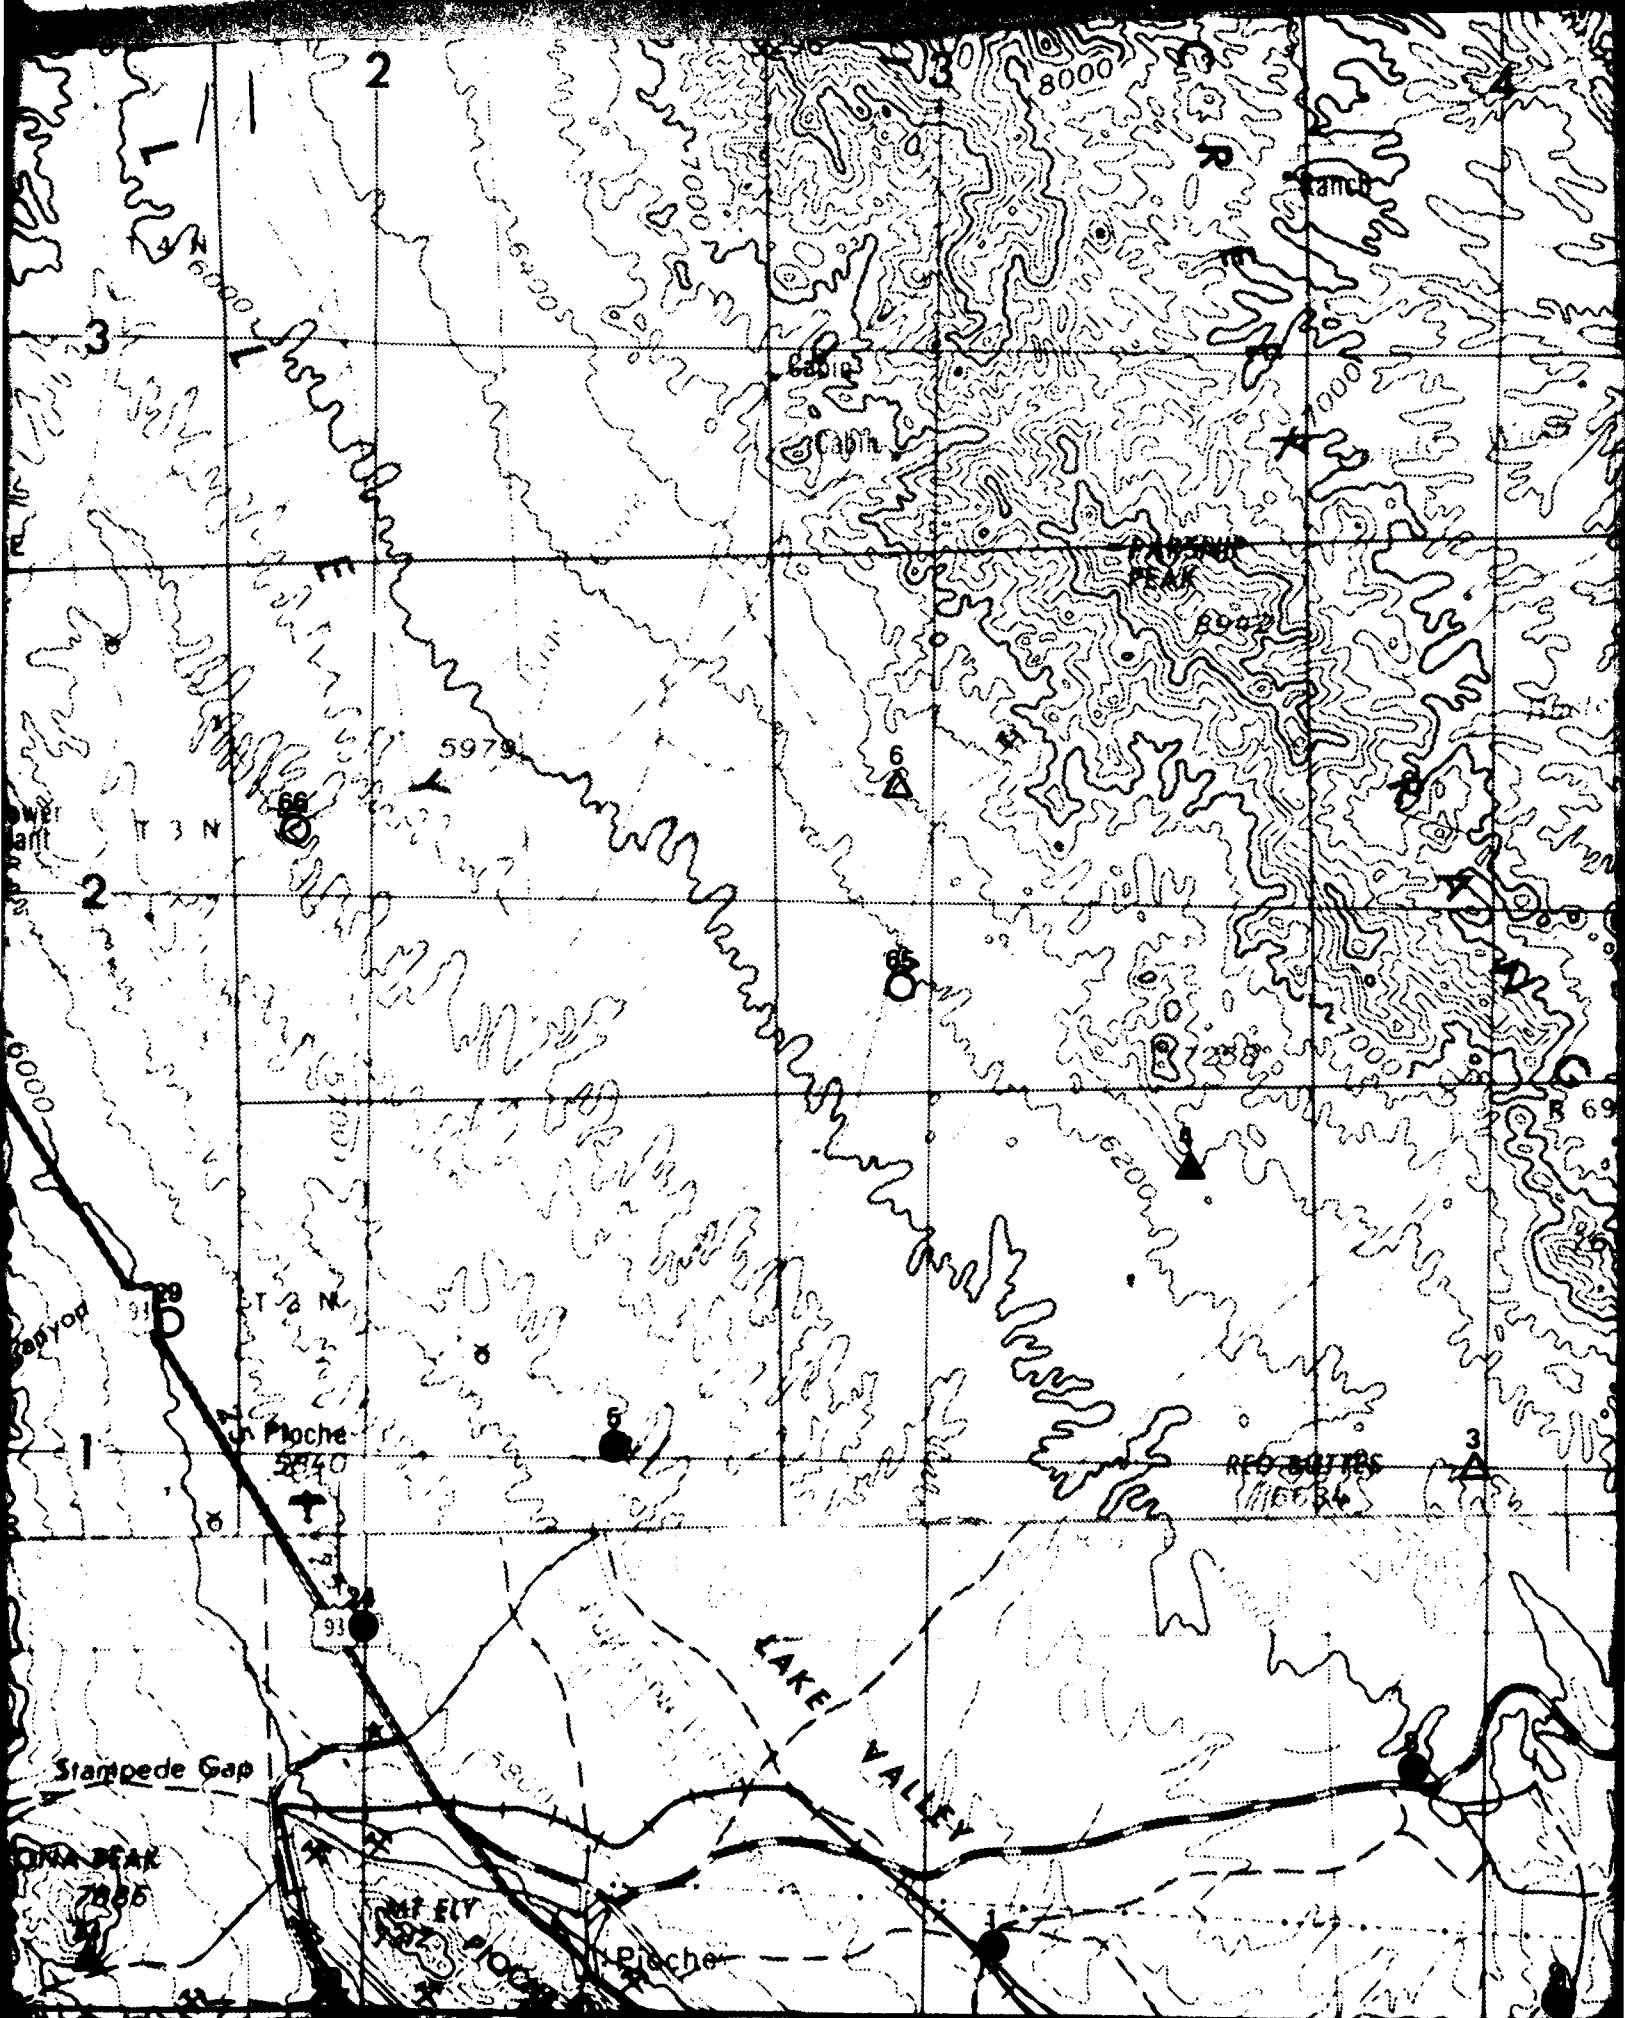


A detailed topographic map of a mountainous region in Arizona. The map features a grid system with latitude and longitude markings. Key geographical features include Marogay Mountain, Serviceberry Canyon, and Deer Lodge Canyon. Elevation contours are shown at various intervals, with labels such as 6086, 6088, 6090, 6092, 6094, 6096, 6098, 6100, 6102, 6104, 6106, 6108, 6110, 6112, 6114, 6116, 6118, 6120, 6122, 6124, 6126, 6128, 6130, 6132, 6134, 6136, 6138, 6140, 6142, 6144, 6146, 6148, 6150, 6152, 6154, 6156, 6158, 6160, 6162, 6164, 6166, 6168, 6170, 6172, 6174, 6176, 6178, 6180, 6182, 6184, 6186, 6188, 6190, 6192, 6194, 6196, 6198, 6200, 6202, 6204, 6206, 6208, 6210, 6212, 6214, 6216, 6218, 6220, 6222, 6224, 6226, 6228, 6230, 6232, 6234, 6236, 6238, 6240, 6242, 6244, 6246, 6248, 6250, 6252, 6254, 6256, 6258, 6260, 6262, 6264, 6266, 6268, 6270, 6272, 6274, 6276, 6278, 6280, 6282, 6284, 6286, 6288, 6290, 6292, 6294, 6296, 6298, 6300, 6302, 6304, 6306, 6308, 6310, 6312, 6314, 6316, 6318, 6320, 6322, 6324, 6326, 6328, 6330, 6332, 6334, 6336, 6338, 6340, 6342, 6344, 6346, 6348, 6350, 6352, 6354, 6356, 6358, 6360, 6362, 6364, 6366, 6368, 6370, 6372, 6374, 6376, 6378, 6380, 6382, 6384, 6386, 6388, 6390, 6392, 6394, 6396, 6398, 6400, 6402, 6404, 6406, 6408, 6410, 6412, 6414, 6416, 6418, 6420, 6422, 6424, 6426, 6428, 6430, 6432, 6434, 6436, 6438, 6440, 6442, 6444, 6446, 6448, 6450, 6452, 6454, 6456, 6458, 6460, 6462, 6464, 6466, 6468, 6470, 6472, 6474, 6476, 6478, 6480, 6482, 6484, 6486, 6488, 6490, 6492, 6494, 6496, 6498, 6500, 6502, 6504, 6506, 6508, 6510, 6512, 6514, 6516, 6518, 6520, 6522, 6524, 6526, 6528, 6530, 6532, 6534, 6536, 6538, 6540, 6542, 6544, 6546, 6548, 6550, 6552, 6554, 6556, 6558, 6560, 6562, 6564, 6566, 6568, 6570, 6572, 6574, 6576, 6578, 6580, 6582, 6584, 6586, 6588, 6590, 6592, 6594, 6596, 6598, 6600, 6602, 6604, 6606, 6608, 6610, 6612, 6614, 6616, 6618, 6620, 6622, 6624, 6626, 6628, 6630, 6632, 6634, 6636, 6638, 6640, 6642, 6644, 6646, 6648, 6650, 6652, 6654, 6656, 6658, 6660, 6662, 6664, 6666, 6668, 6670, 6672, 6674, 6676, 6678, 6680, 6682, 6684, 6686, 6688, 6690, 6692, 6694, 6696, 6698, 6700, 6702, 6704, 6706, 6708, 6710, 6712, 6714, 6716, 6718, 6720, 6722, 6724, 6726, 6728, 6730, 6732, 6734, 6736, 6738, 6740, 6742, 6744, 6746, 6748, 6750, 6752, 6754, 6756, 6758, 6760, 6762, 6764, 6766, 6768, 6770, 6772, 6774, 6776, 6778, 6780, 6782, 6784, 6786, 6788, 6790, 6792, 6794, 6796, 6798, 6800, 6802, 6804, 6806, 6808, 6810, 6812, 6814, 6816, 6818, 6820, 6822, 6824, 6826, 6828, 6830, 6832, 6834, 6836, 6838, 6840, 6842, 6844, 6846, 6848, 6850, 6852, 6854, 6856, 6858, 6860, 6862, 6864, 6866, 6868, 6870, 6872, 6874, 6876, 6878, 6880, 6882, 6884, 6886, 6888, 6890, 6892, 6894, 6896, 6898, 6900, 6902, 6904, 6906, 6908, 6910, 6912, 6914, 6916, 6918, 6920, 6922, 6924, 6926, 6928, 6930, 6932, 6934, 6936, 6938, 6940, 6942, 6944, 6946, 6948, 6950, 6952, 6954, 6956, 6958, 6960, 6962, 6964, 6966, 6968, 6970, 6972, 6974, 6976, 6978, 6980, 6982, 6984, 6986, 6988, 6990, 6992, 6994, 6996, 6998, 7000, 7002, 7004, 7006, 7008, 7010, 7012, 7014, 7016, 7018, 7020, 7022, 7024, 7026, 7028, 7030, 7032, 7034, 7036, 7038, 7040, 7042, 7044, 7046, 7048, 7050, 7052, 7054, 7056, 7058, 7060, 7062, 7064, 7066, 7068, 7070, 7072, 7074, 7076, 7078, 7080, 7082, 7084, 7086, 7088, 7090, 7092, 7094, 7096, 7098, 7100, 7102, 7104, 7106, 7108, 7110, 7112, 7114, 7116, 7118, 7120, 7122, 7124, 7126, 7128, 7130, 7132, 7134, 7136, 7138, 7140, 7142, 7144, 7146, 7148, 7150, 7152, 7154, 7156, 7158, 7160, 7162, 7164, 7166, 7168, 7170, 7172, 7174, 7176, 7178, 7180, 7182, 7184, 7186, 7188, 7190, 7192, 7194, 7196, 7198, 7200, 7202, 7204, 7206, 7208, 7210, 7212, 7214, 7216, 7218, 7220, 7222, 7224, 7226, 7228, 7230, 7232, 7234, 7236, 7238, 7240, 7242, 7244, 7246, 7248, 7250, 7252, 7254, 7256, 7258, 7260, 7262, 7264, 7266, 7268, 7270, 7272, 7274, 7276, 7278, 7280, 7282, 7284, 7286, 7288, 7290, 7292, 7294, 7296, 7298, 7300, 7302, 7304, 7306, 7308, 7310, 7312, 7314, 7316, 7318, 7320, 7322, 7324, 7326, 7328, 7330, 7332, 7334, 7336, 7338, 7340, 7342, 7344, 7346, 7348, 7350, 7352, 7354, 7356, 7358, 7360, 7362, 7364, 7366, 7368, 7370, 7372, 7374, 7376, 7378, 7380, 7382, 7384, 7386, 7388, 7390, 7392, 7394, 7396, 7398, 7400, 7402, 7404, 7406, 7408, 7410, 7412, 7414, 7416, 7418, 7420,

MANOGANT
MOUNTAINS

DEER LODGE CANYON

Note: See Corresp

13

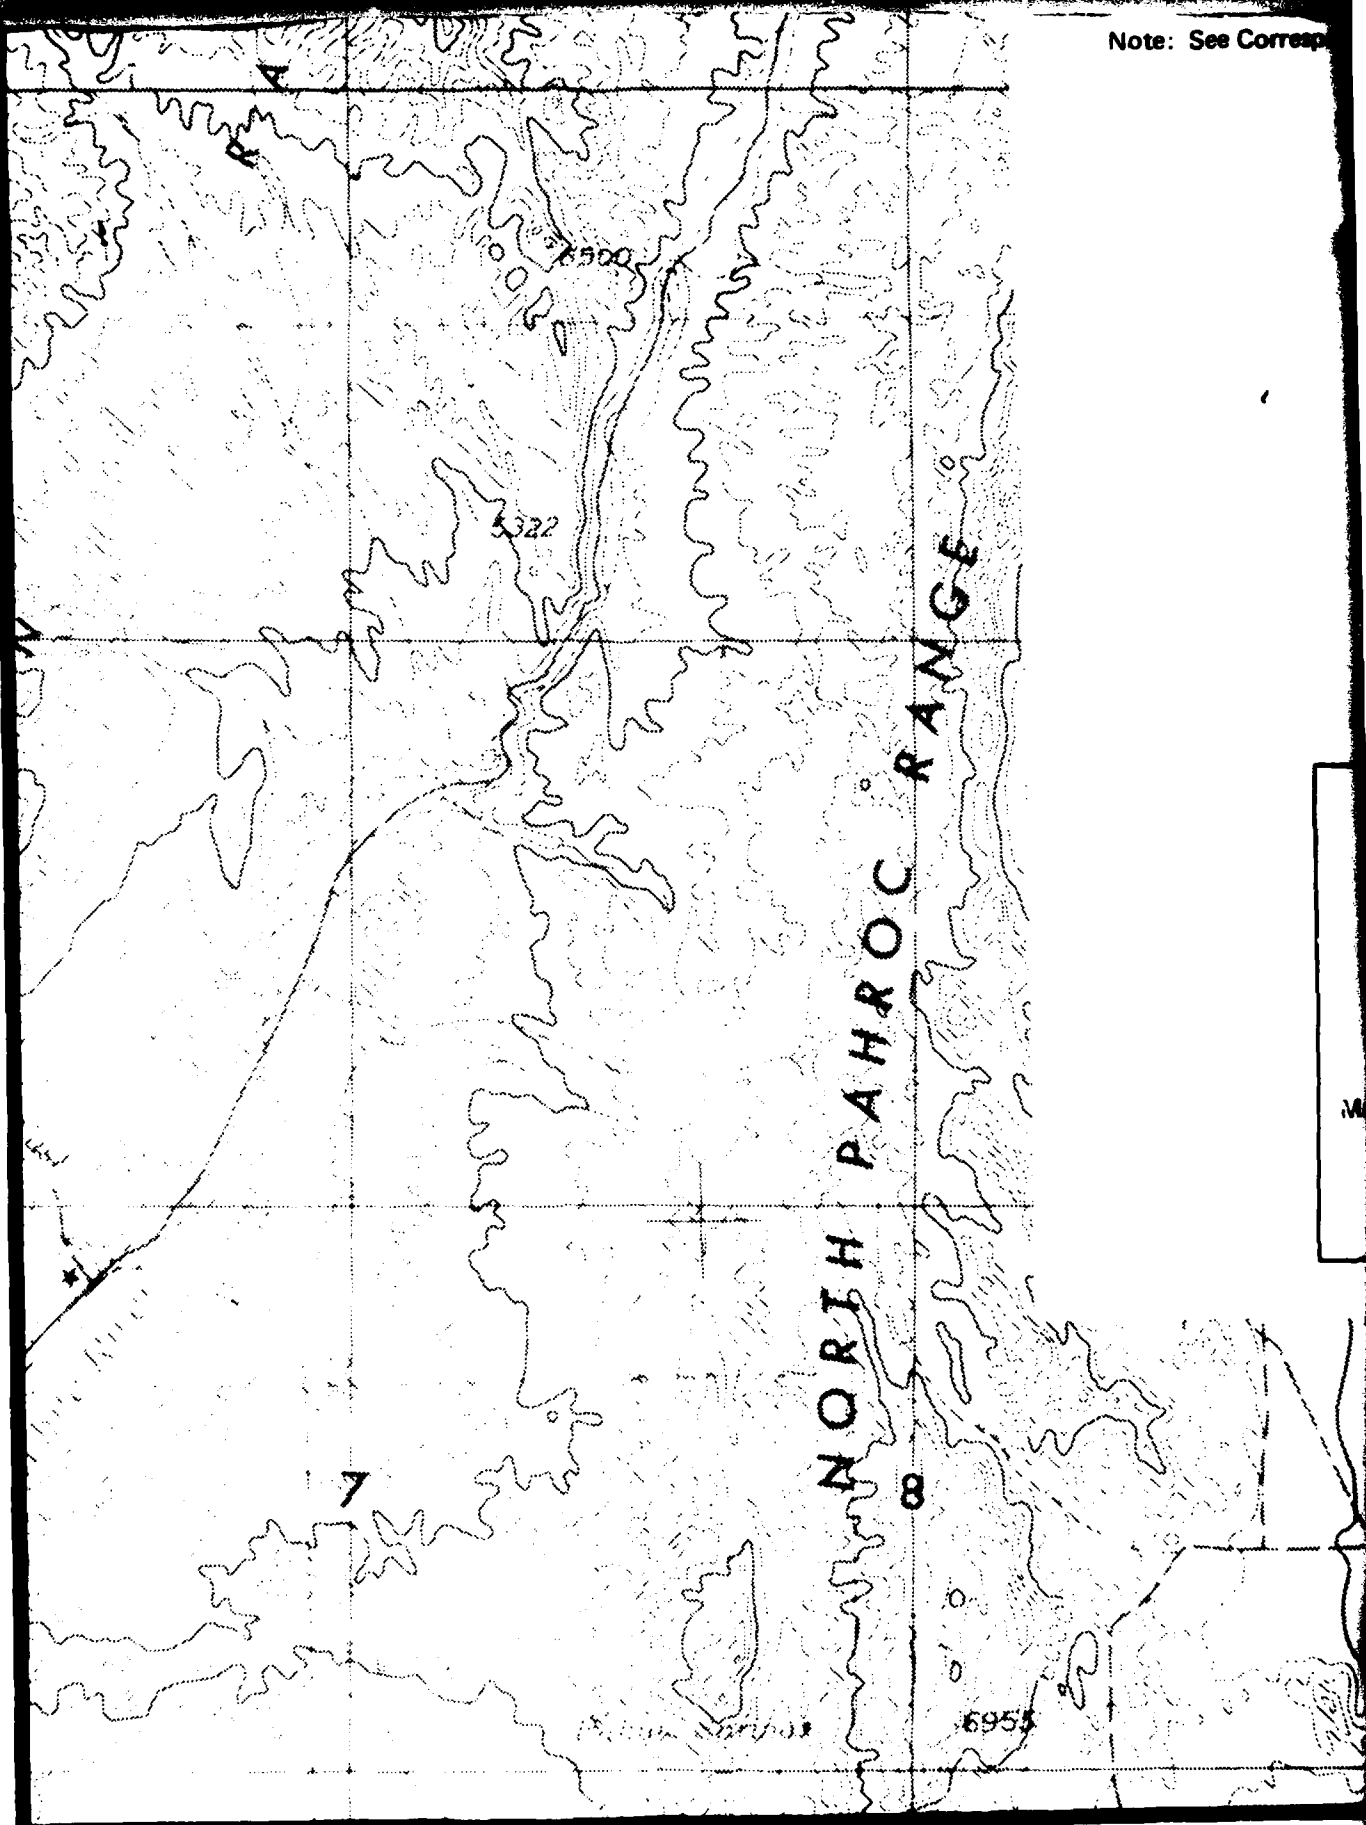


27 FEB 81

Corresponding Map Number in Appendix A for Detailed Information


14



SCALE 1:125,000






STATUTE MILES




KILOMETERS

LOCATION MAP

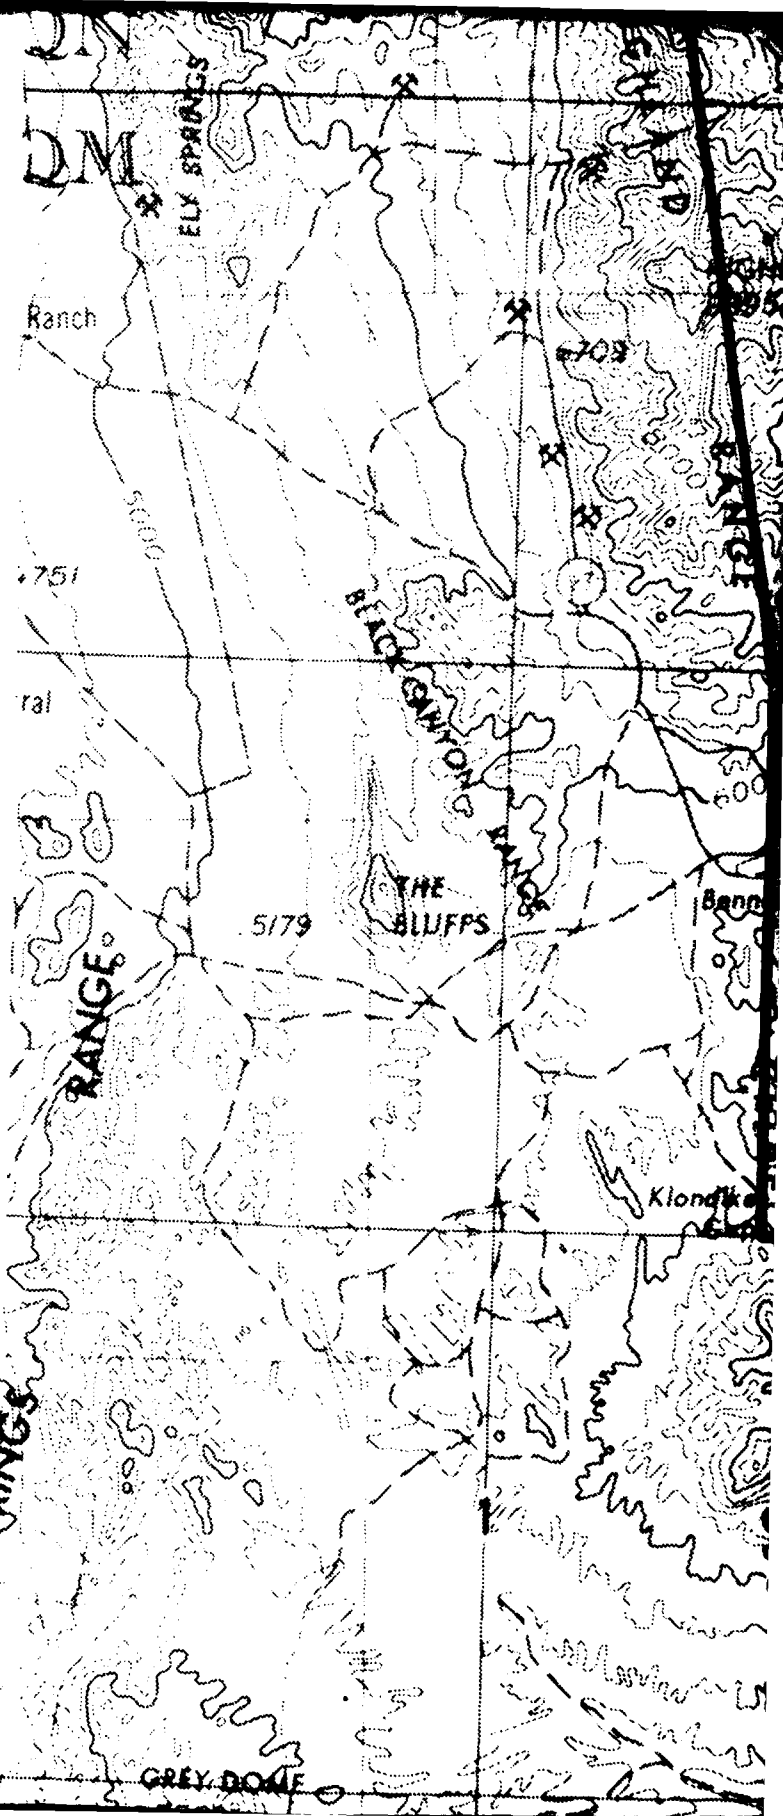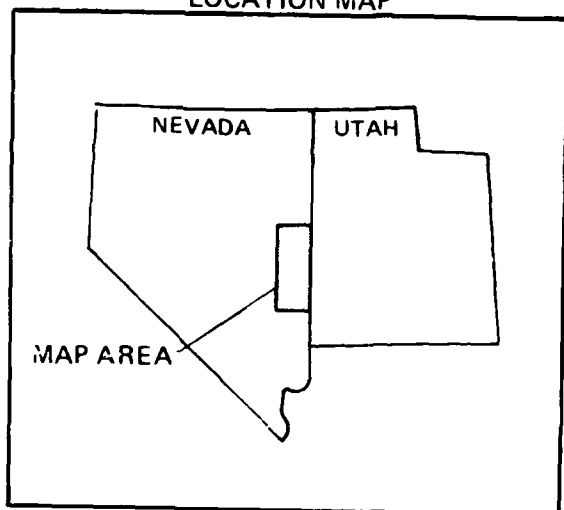

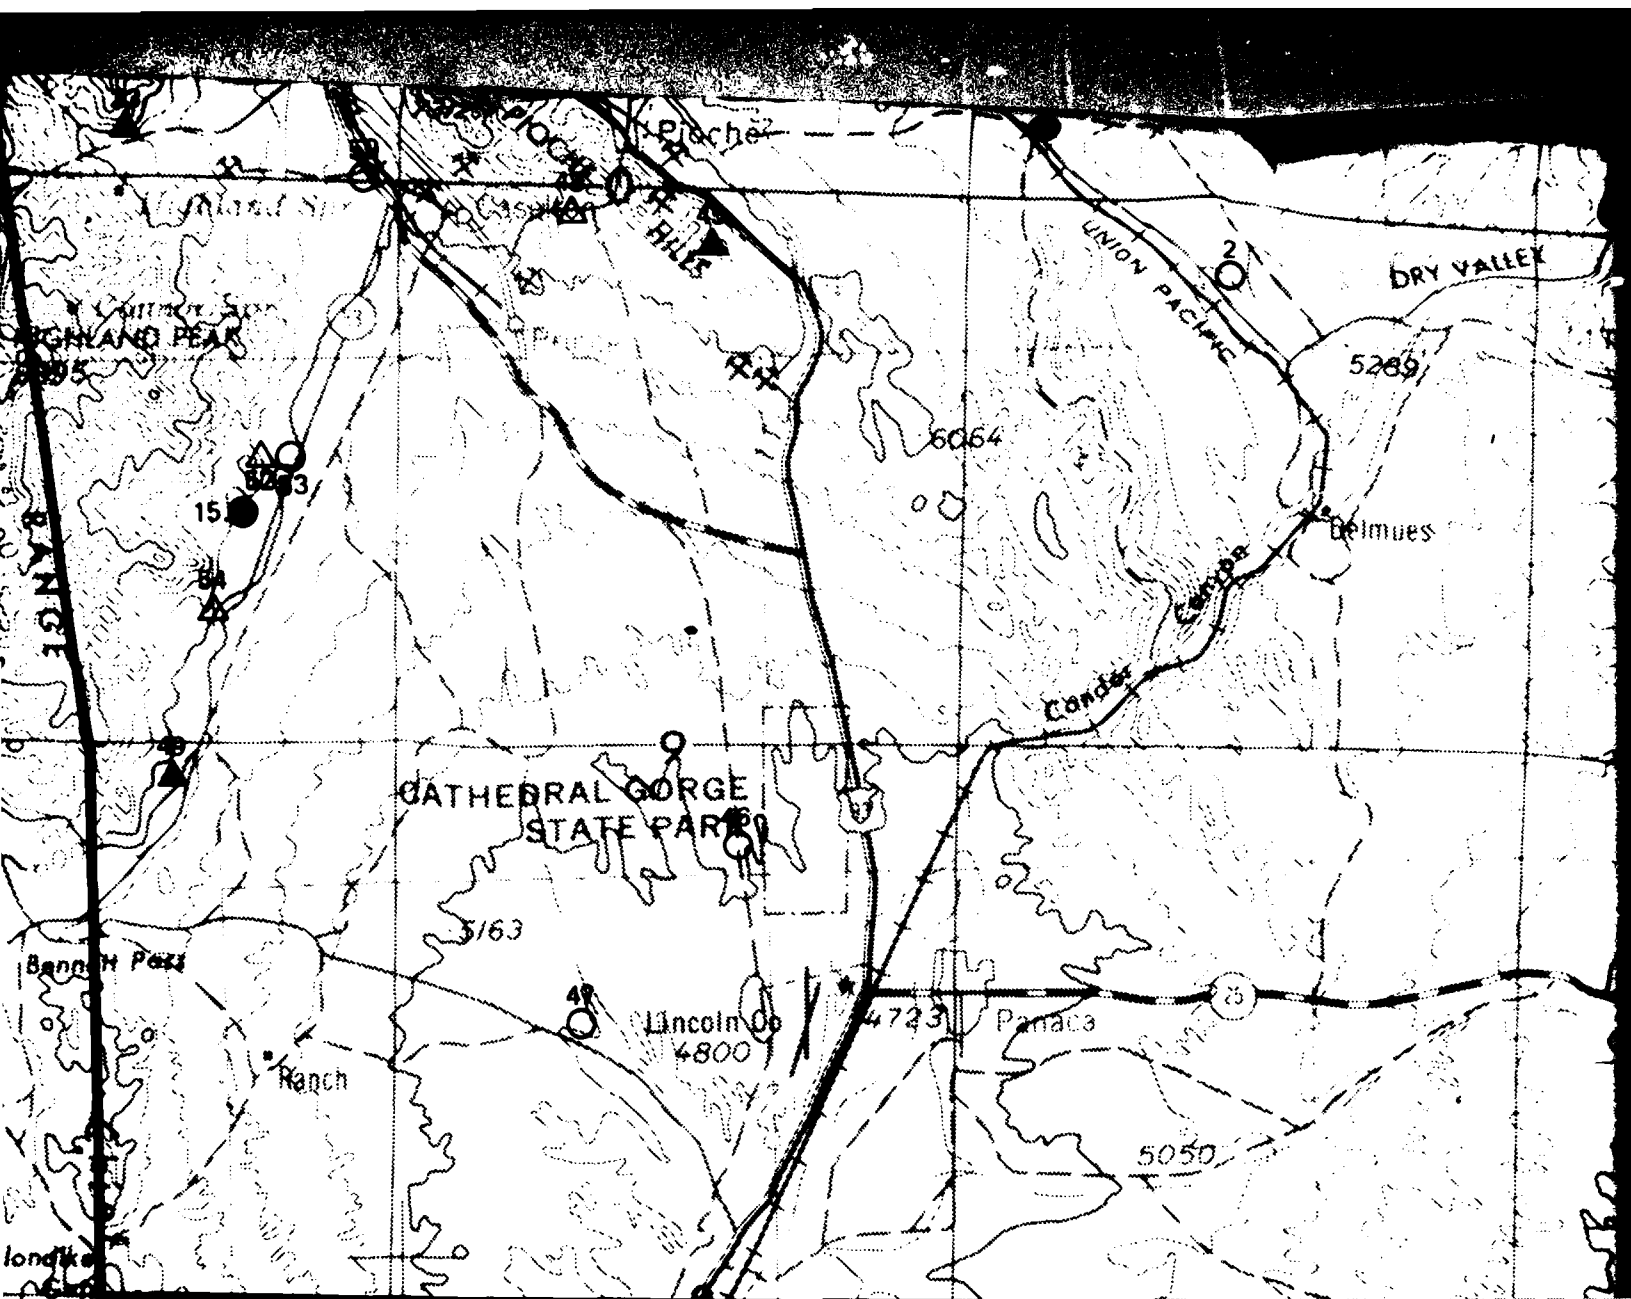

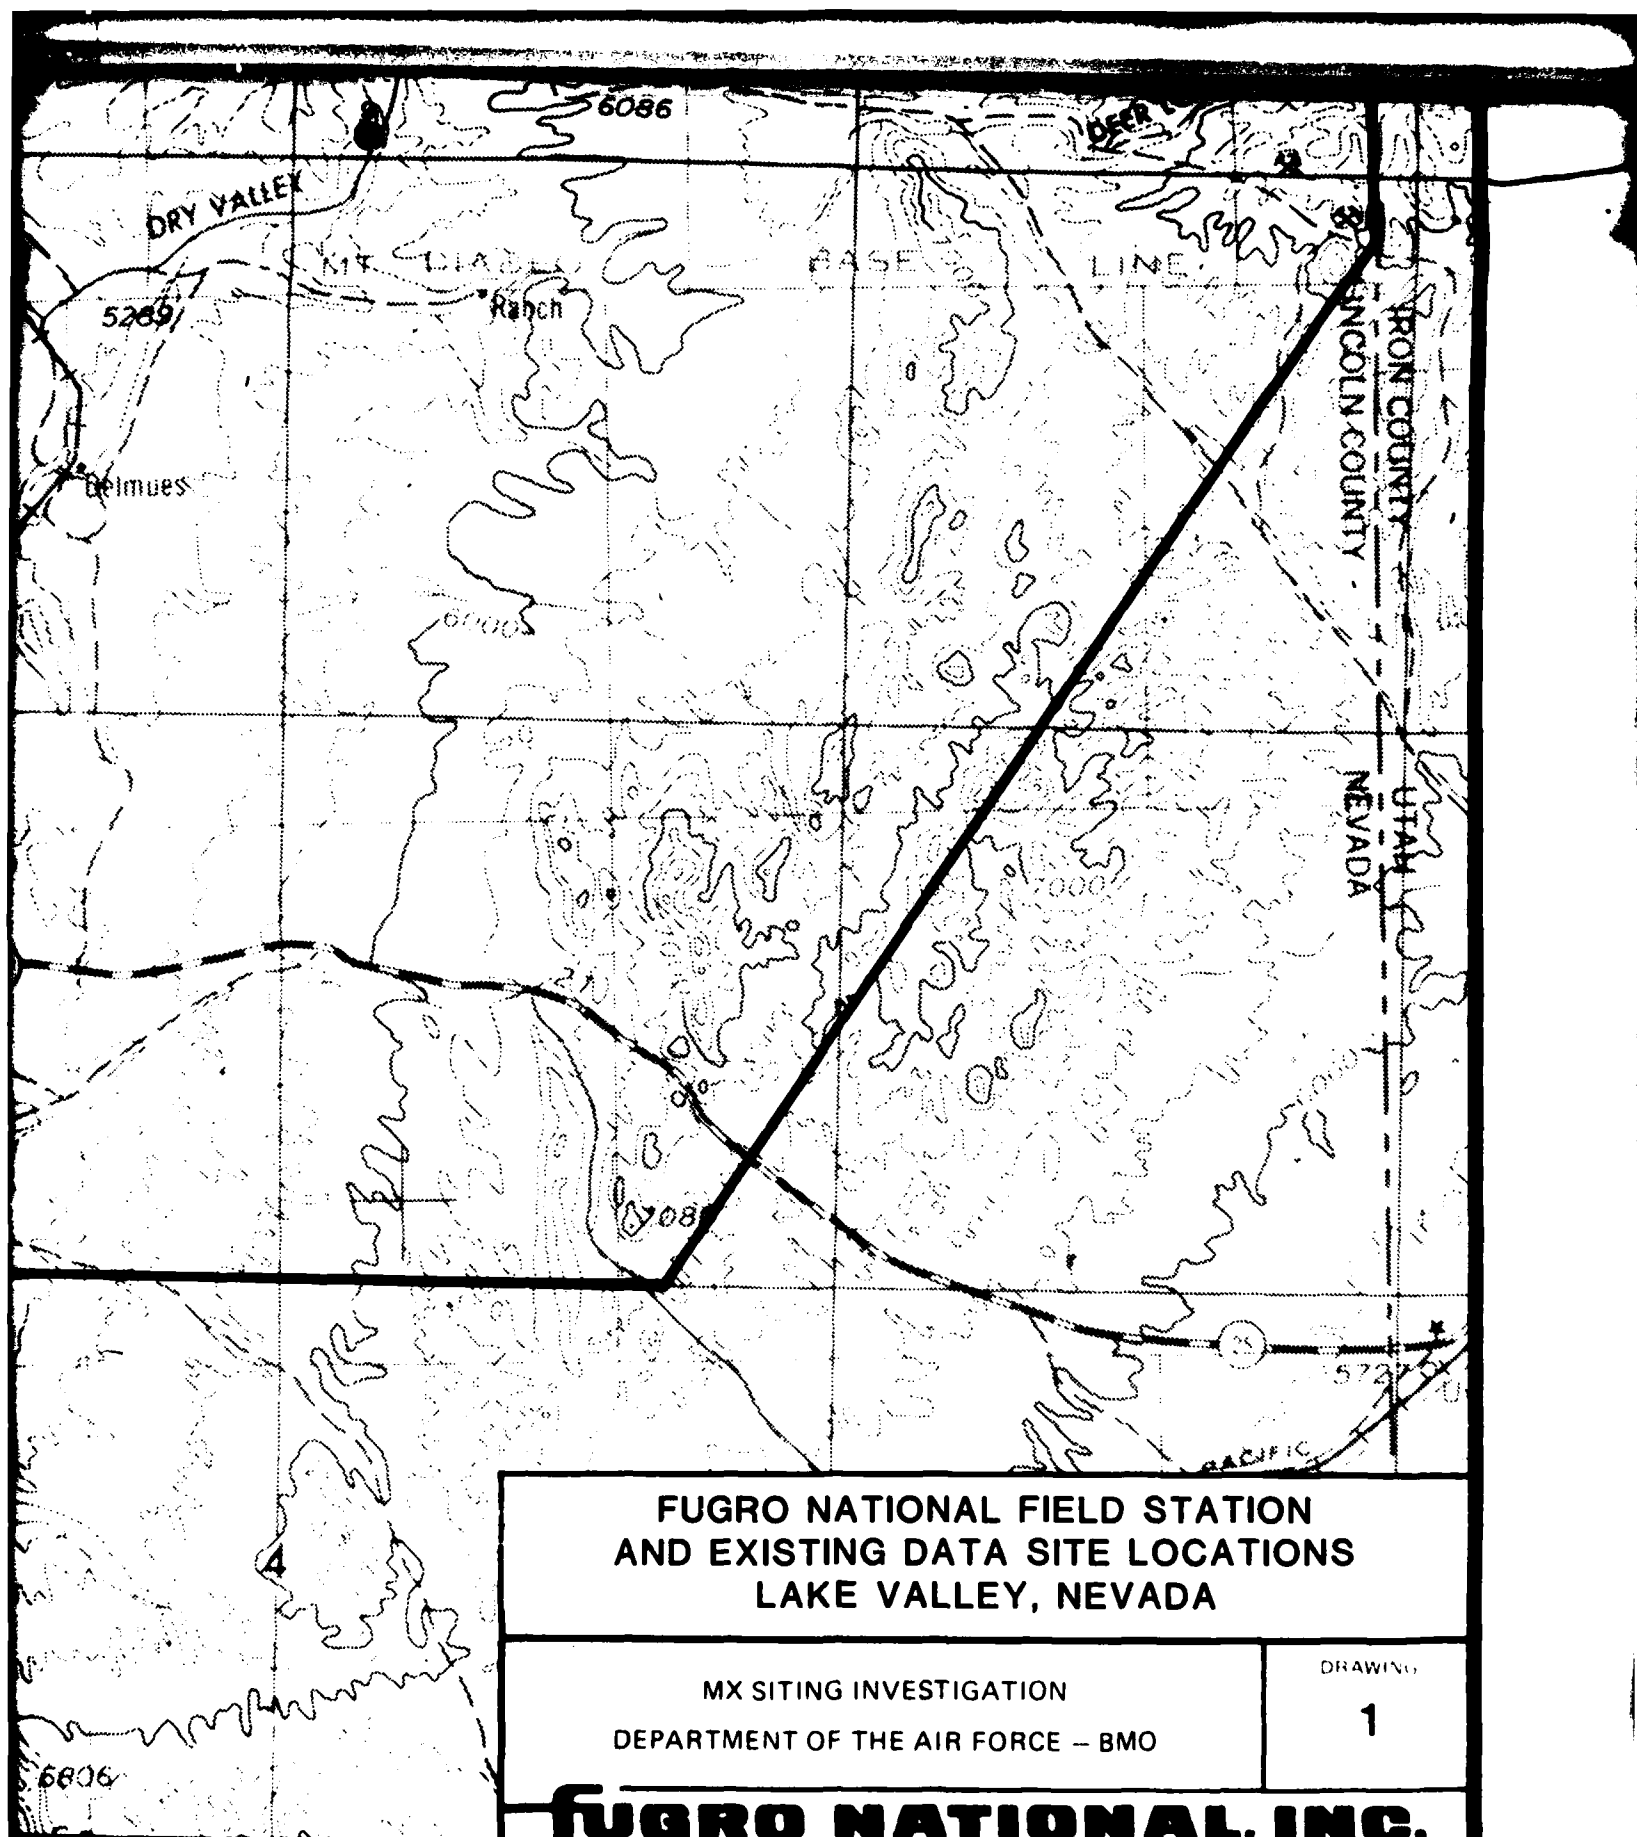


**FUGRO NATIONAL FIELD STATION
AND EXISTING DATA SITE LOCATIONS
LAKE VALLEY, NEVADA**


MX SITING INVESTIGATION
DEPARTMENT OF THE AIR FORCE - BMO


DRAWING


1

FUGRO NATIONAL, INC.

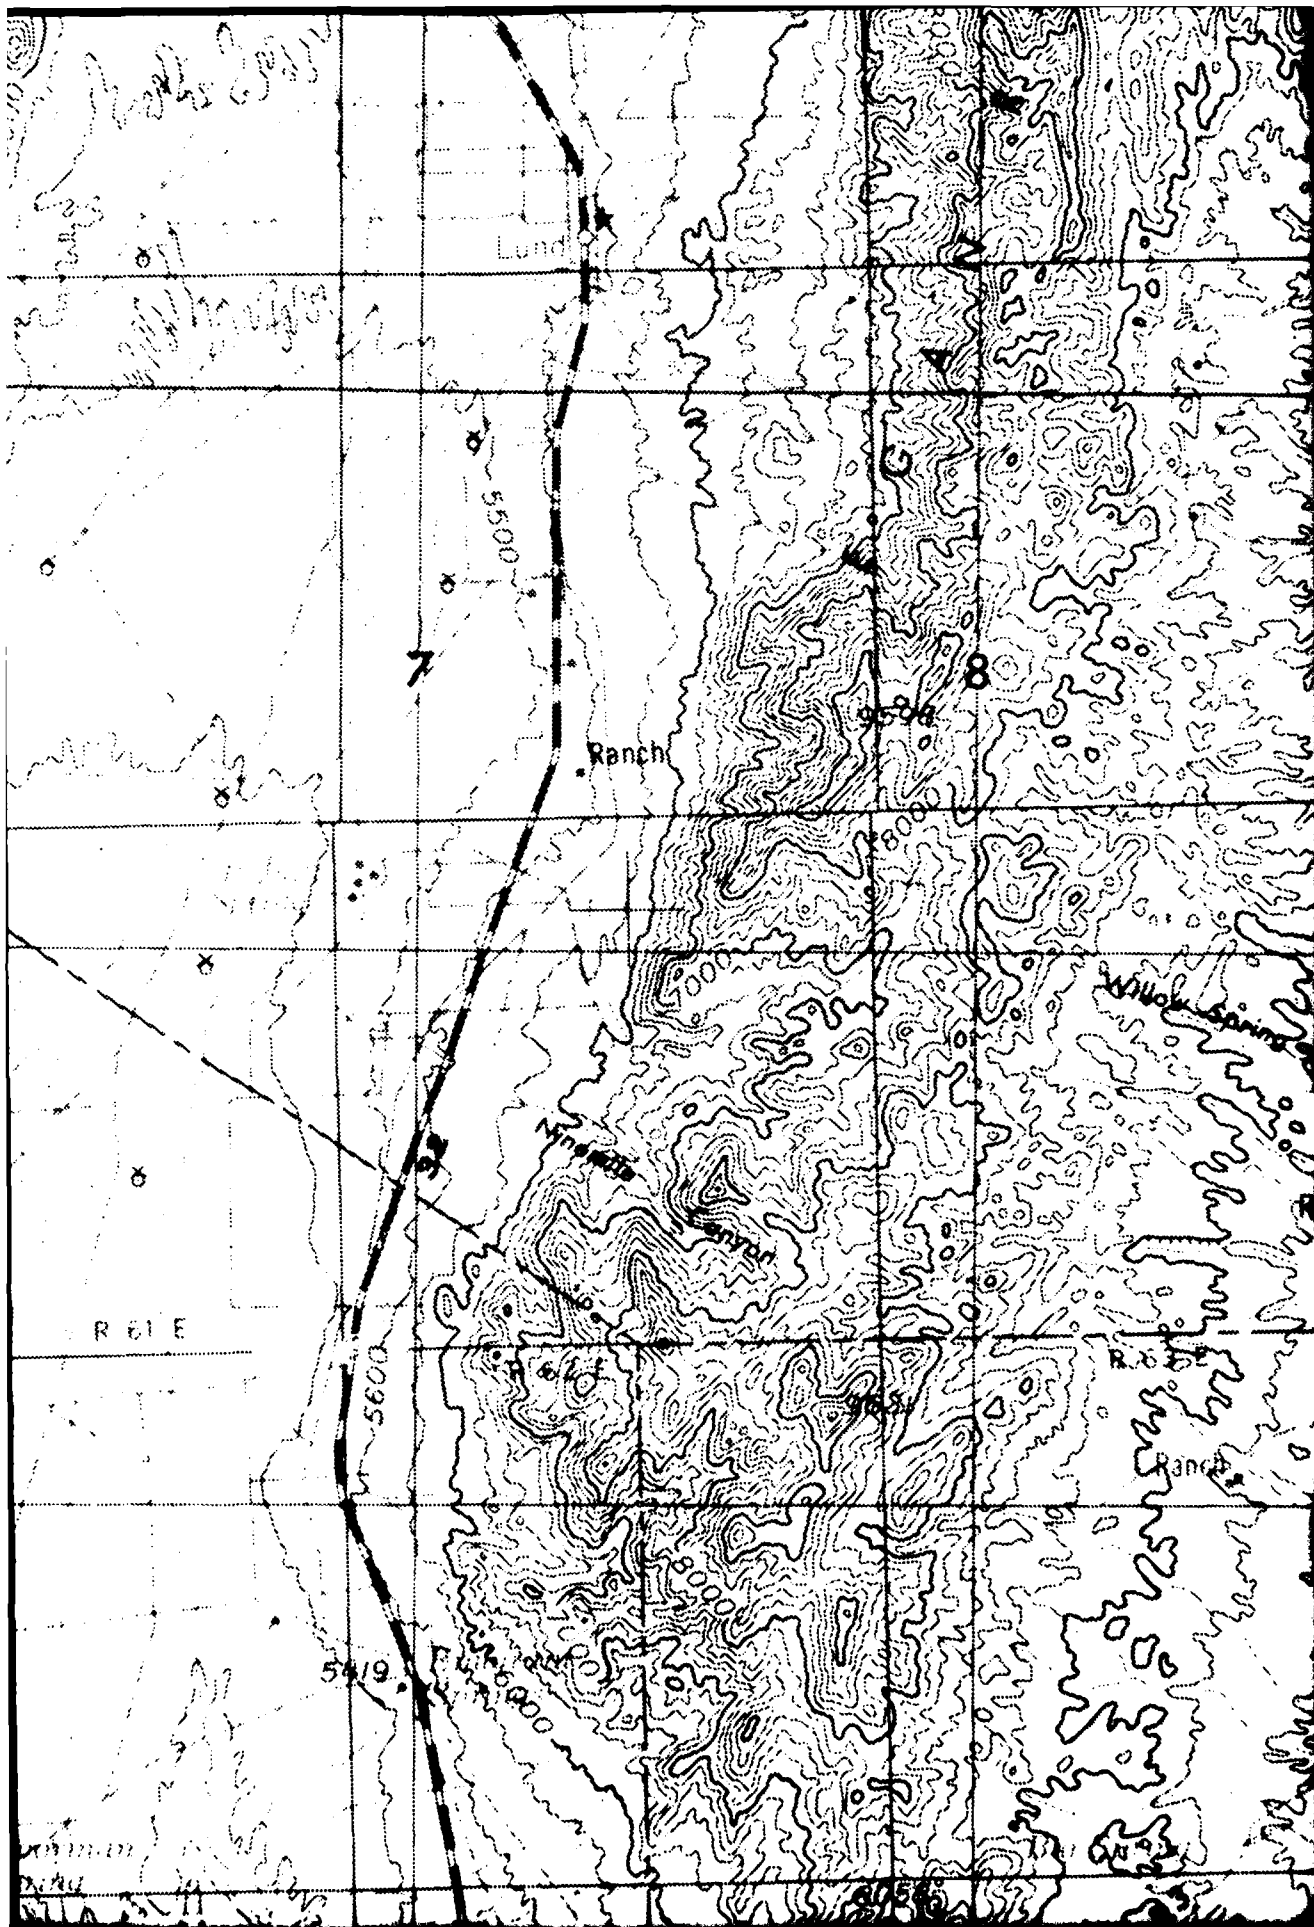


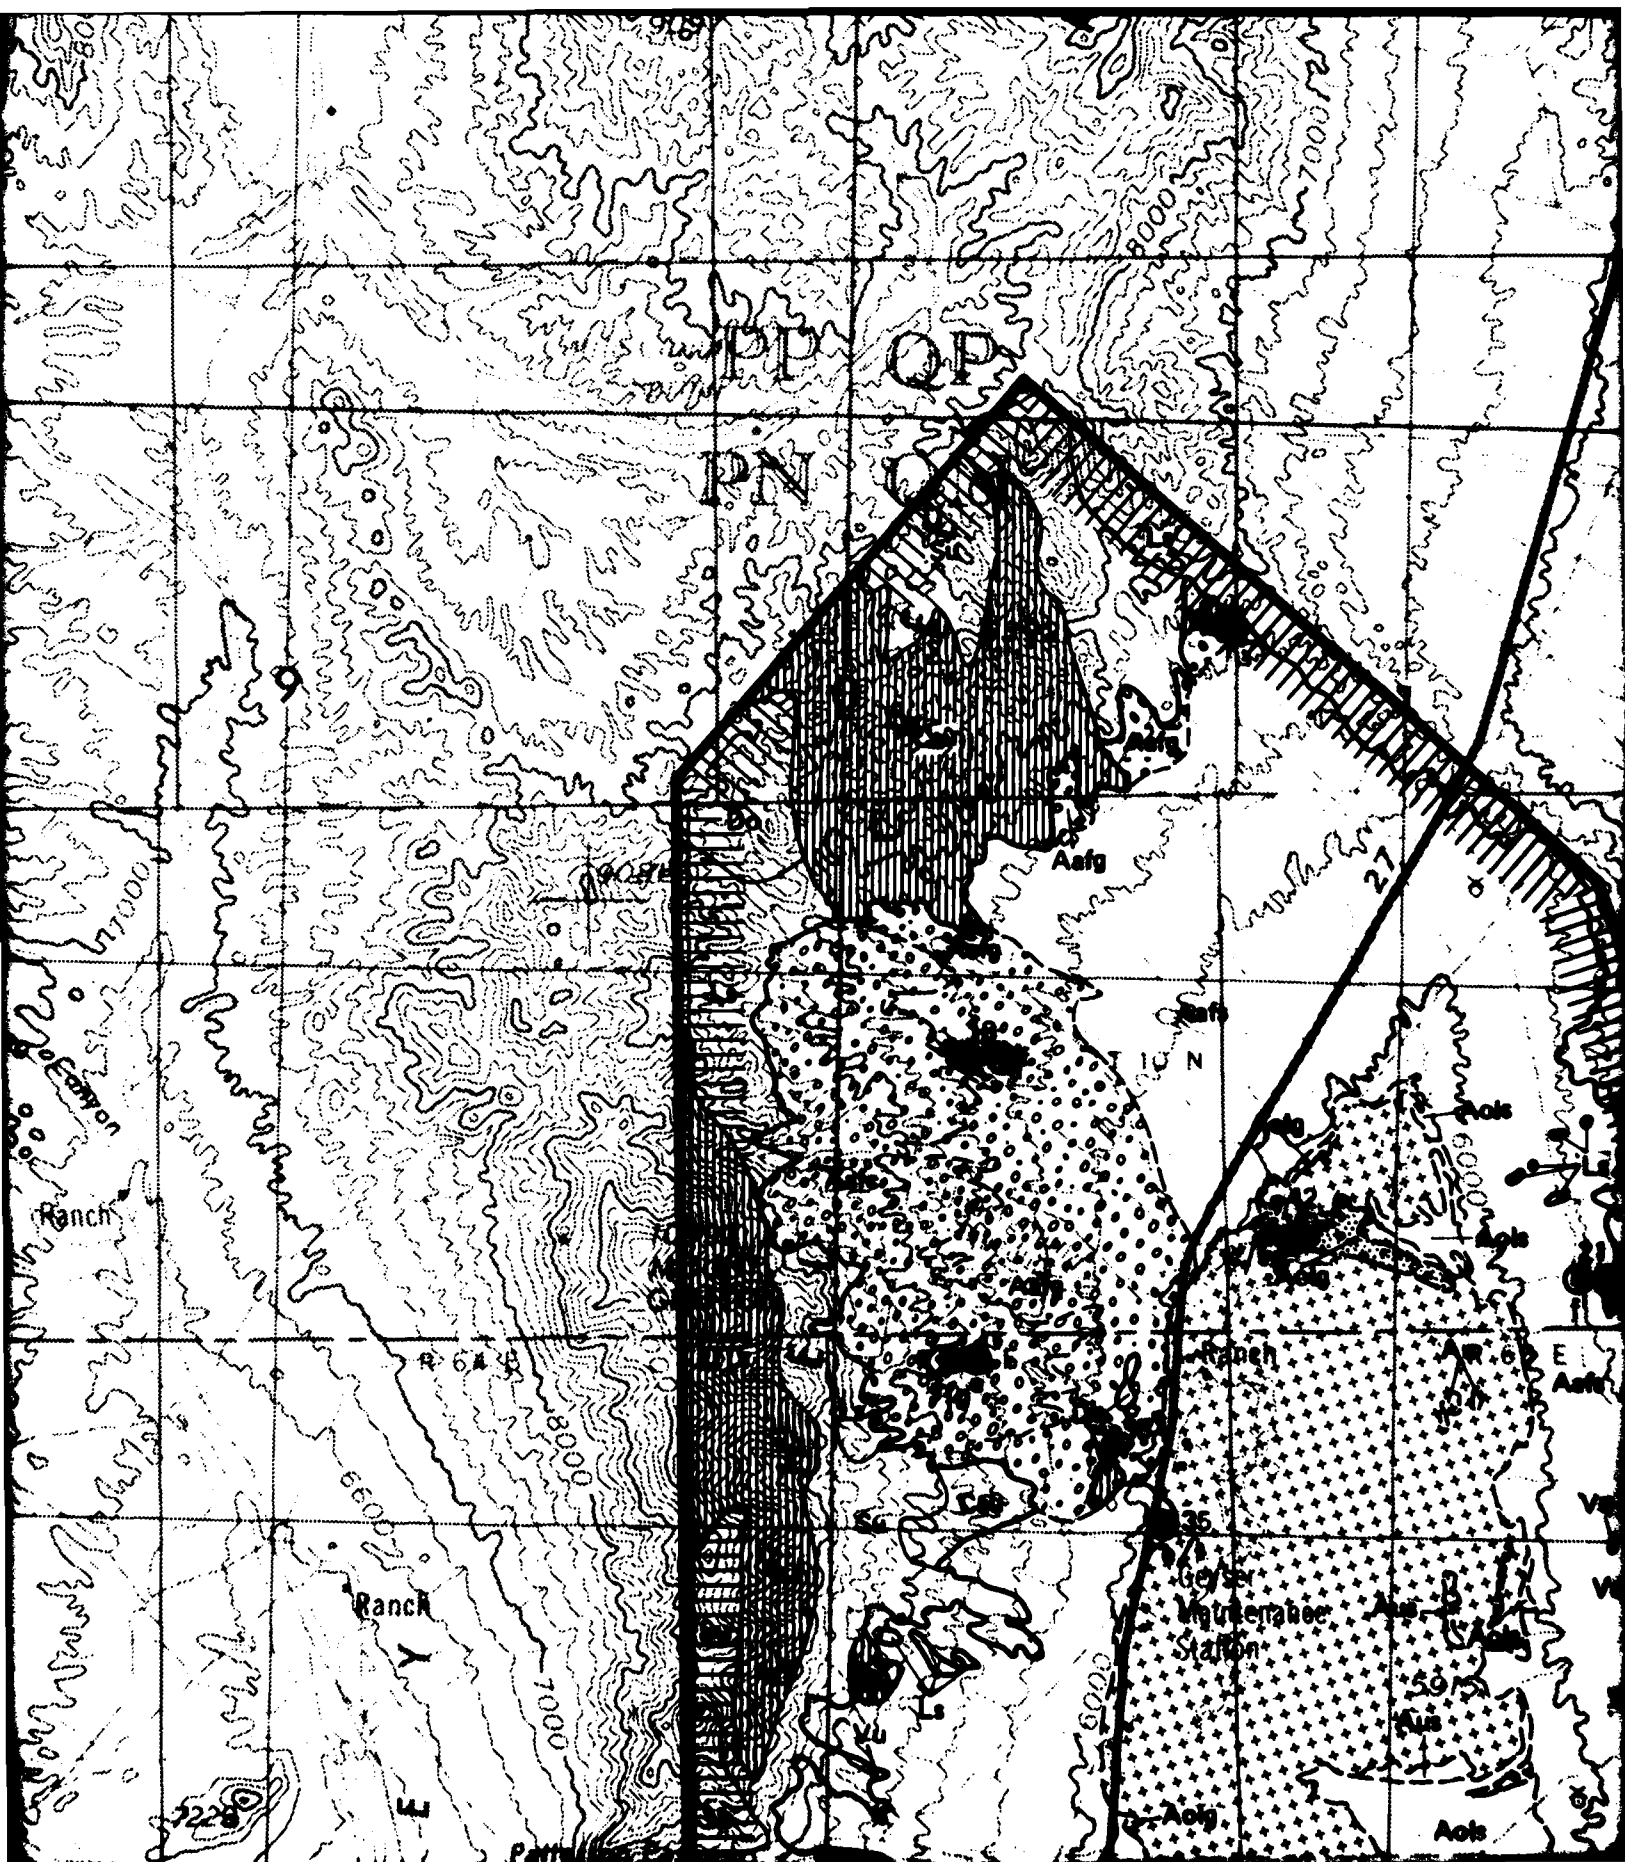


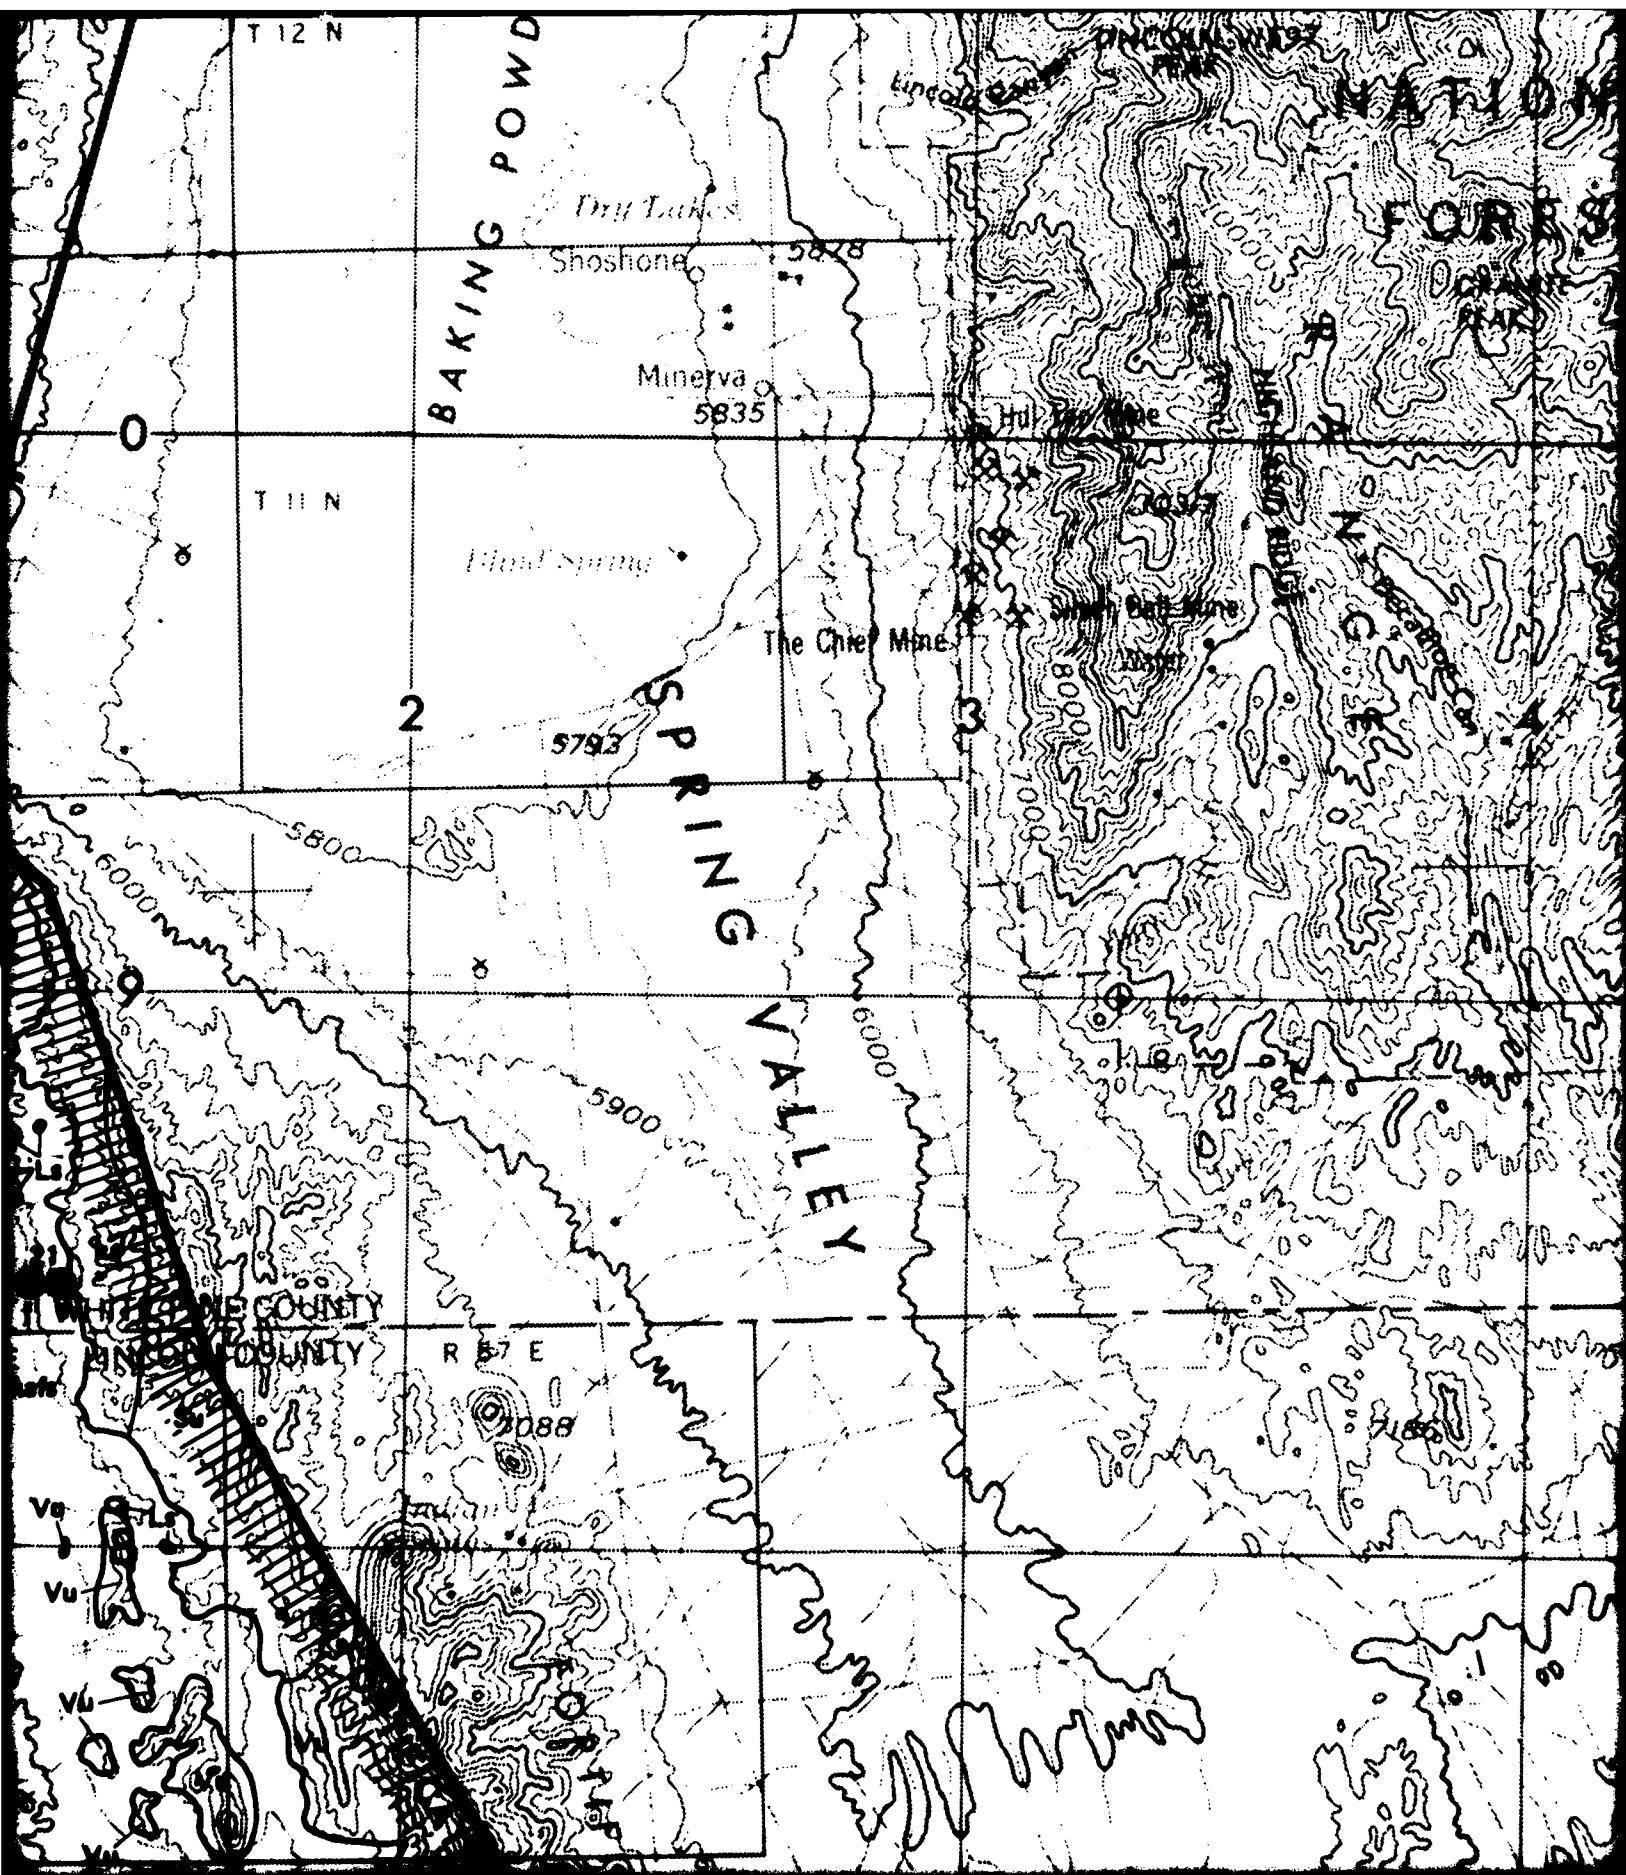


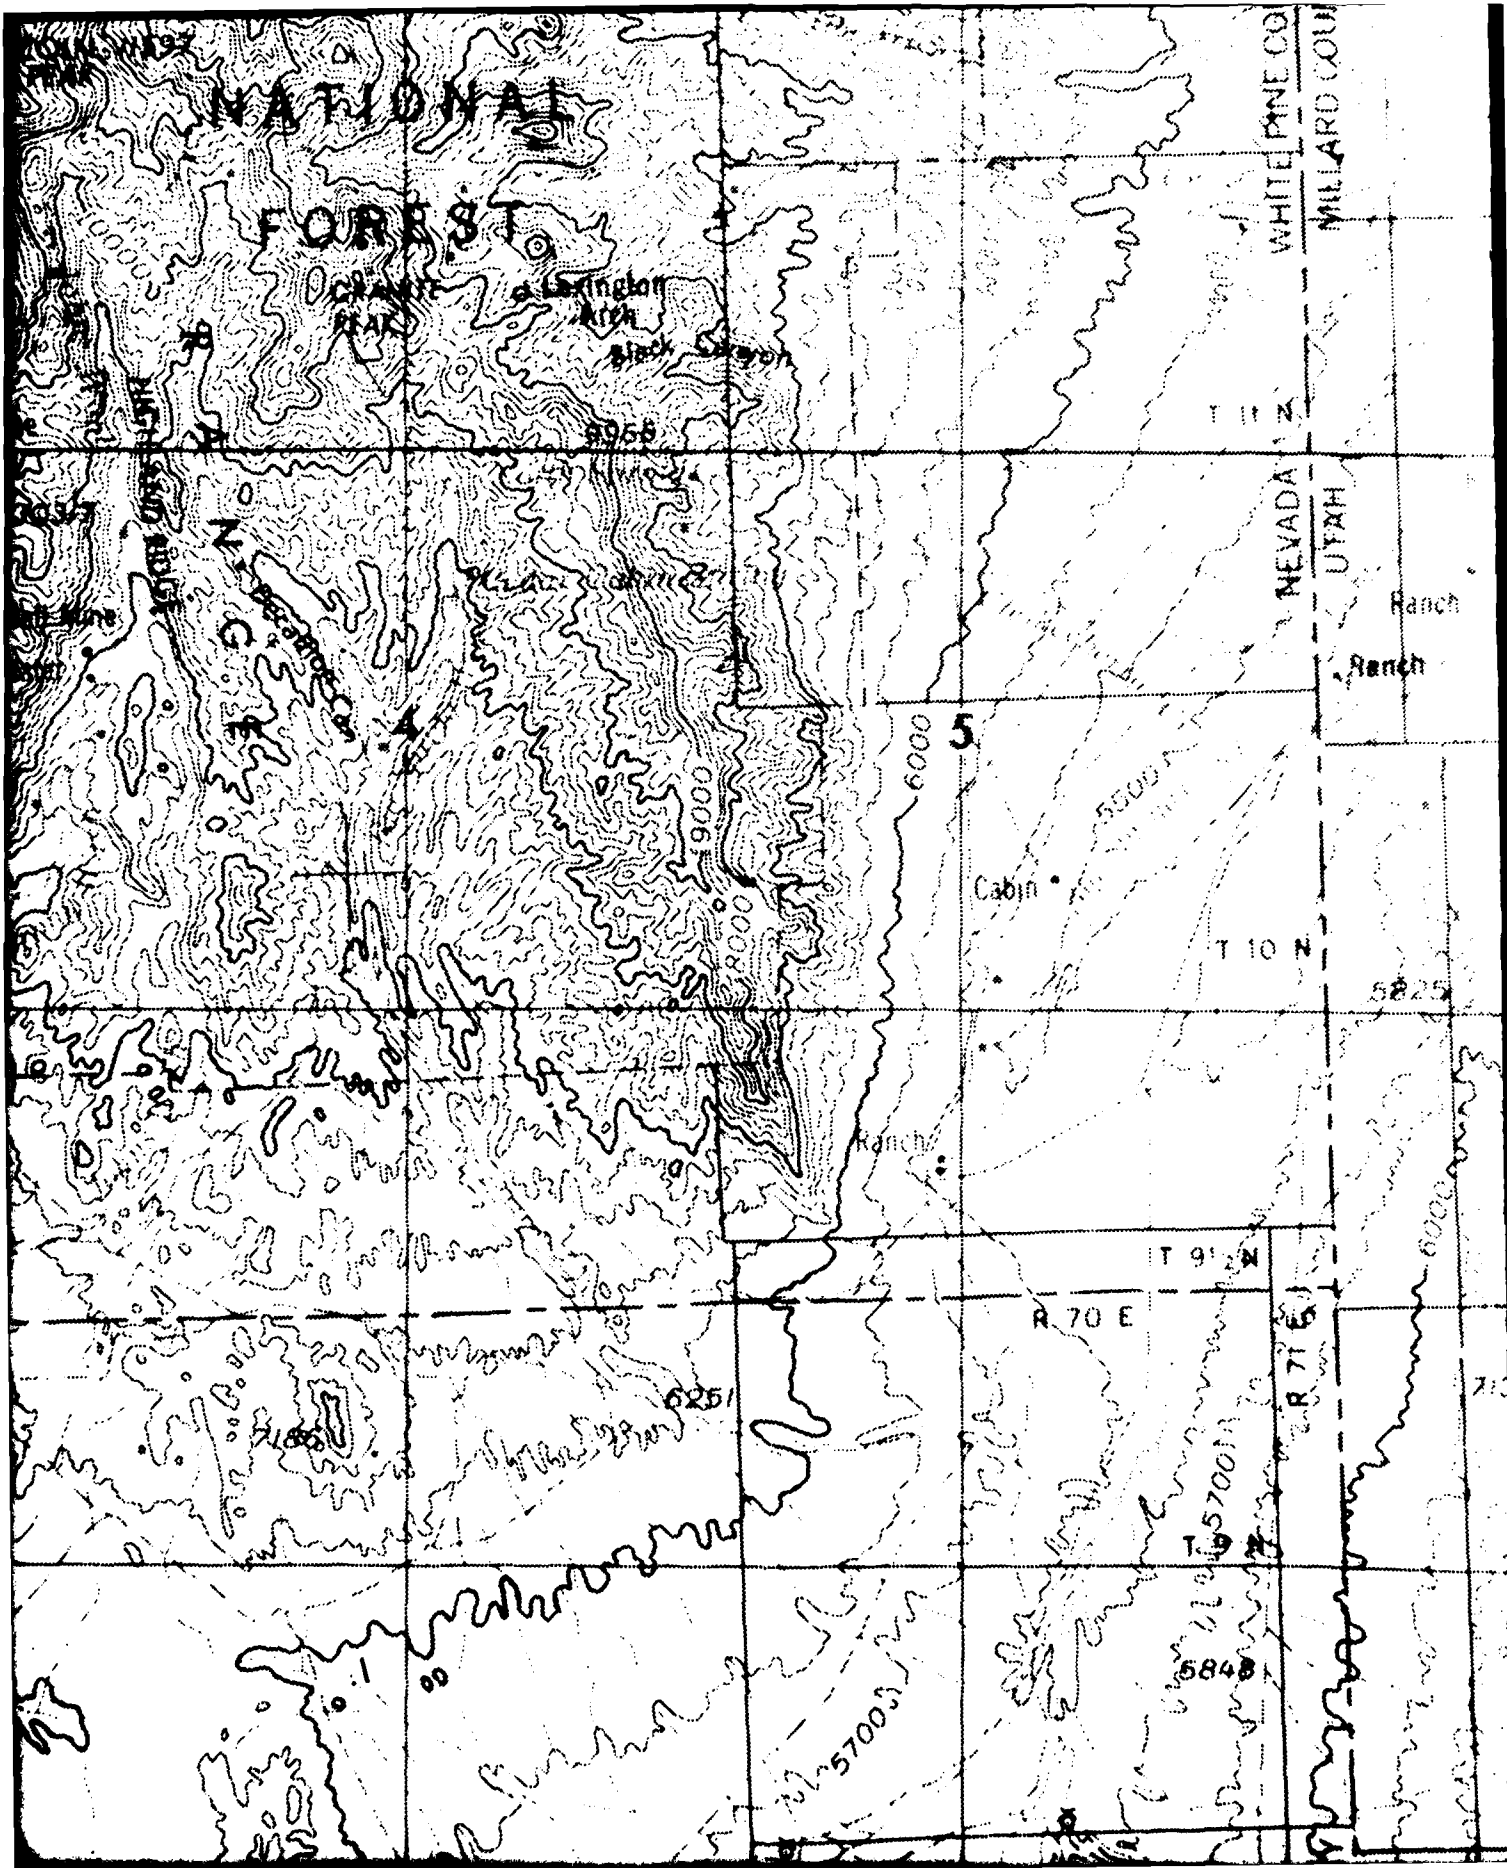


5

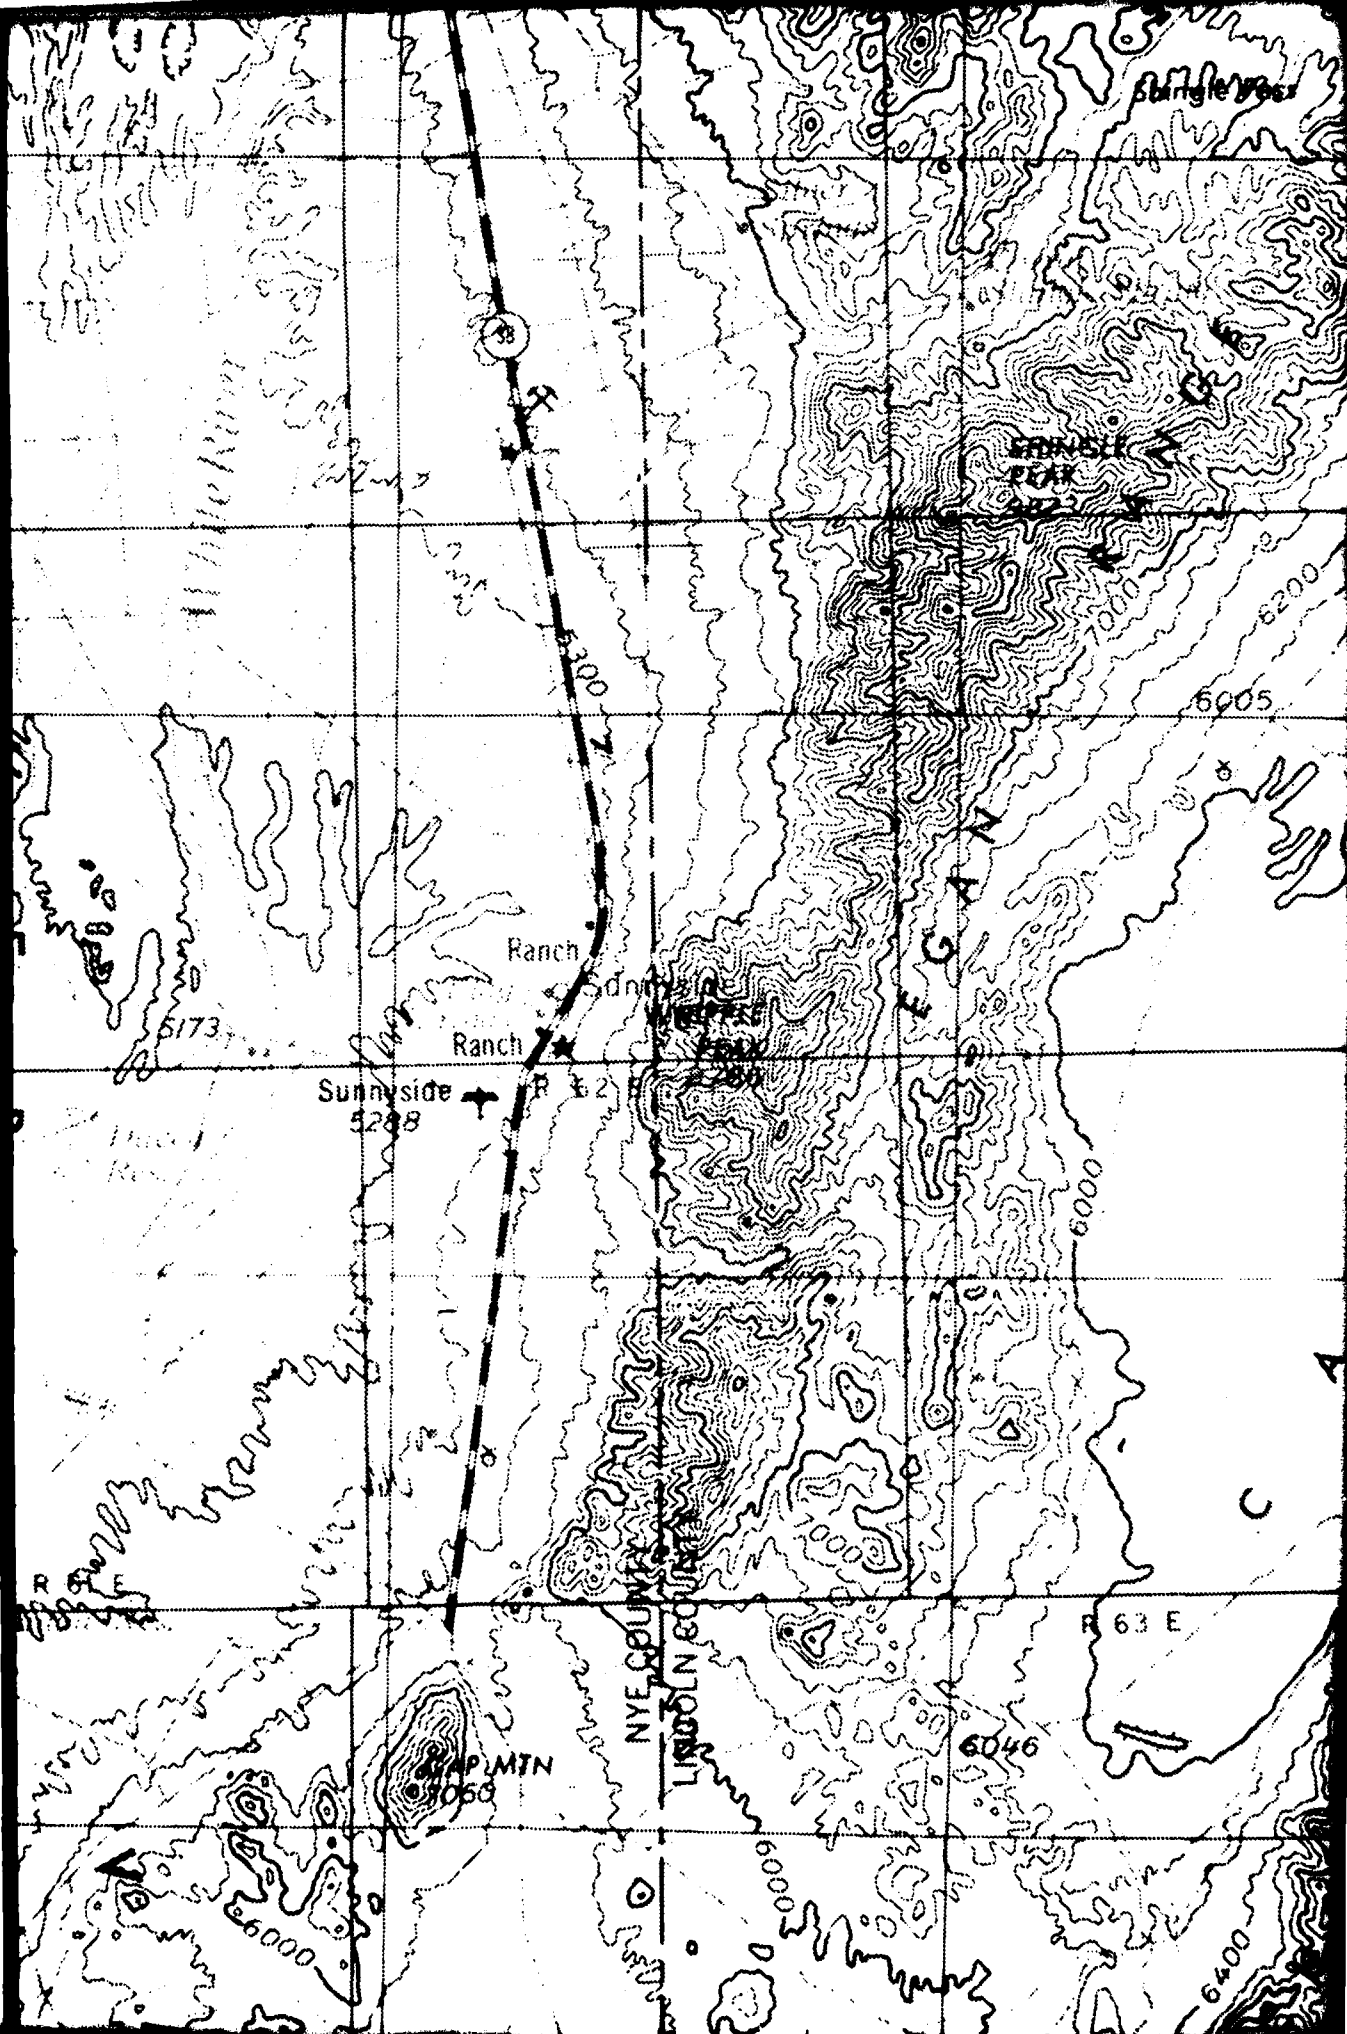


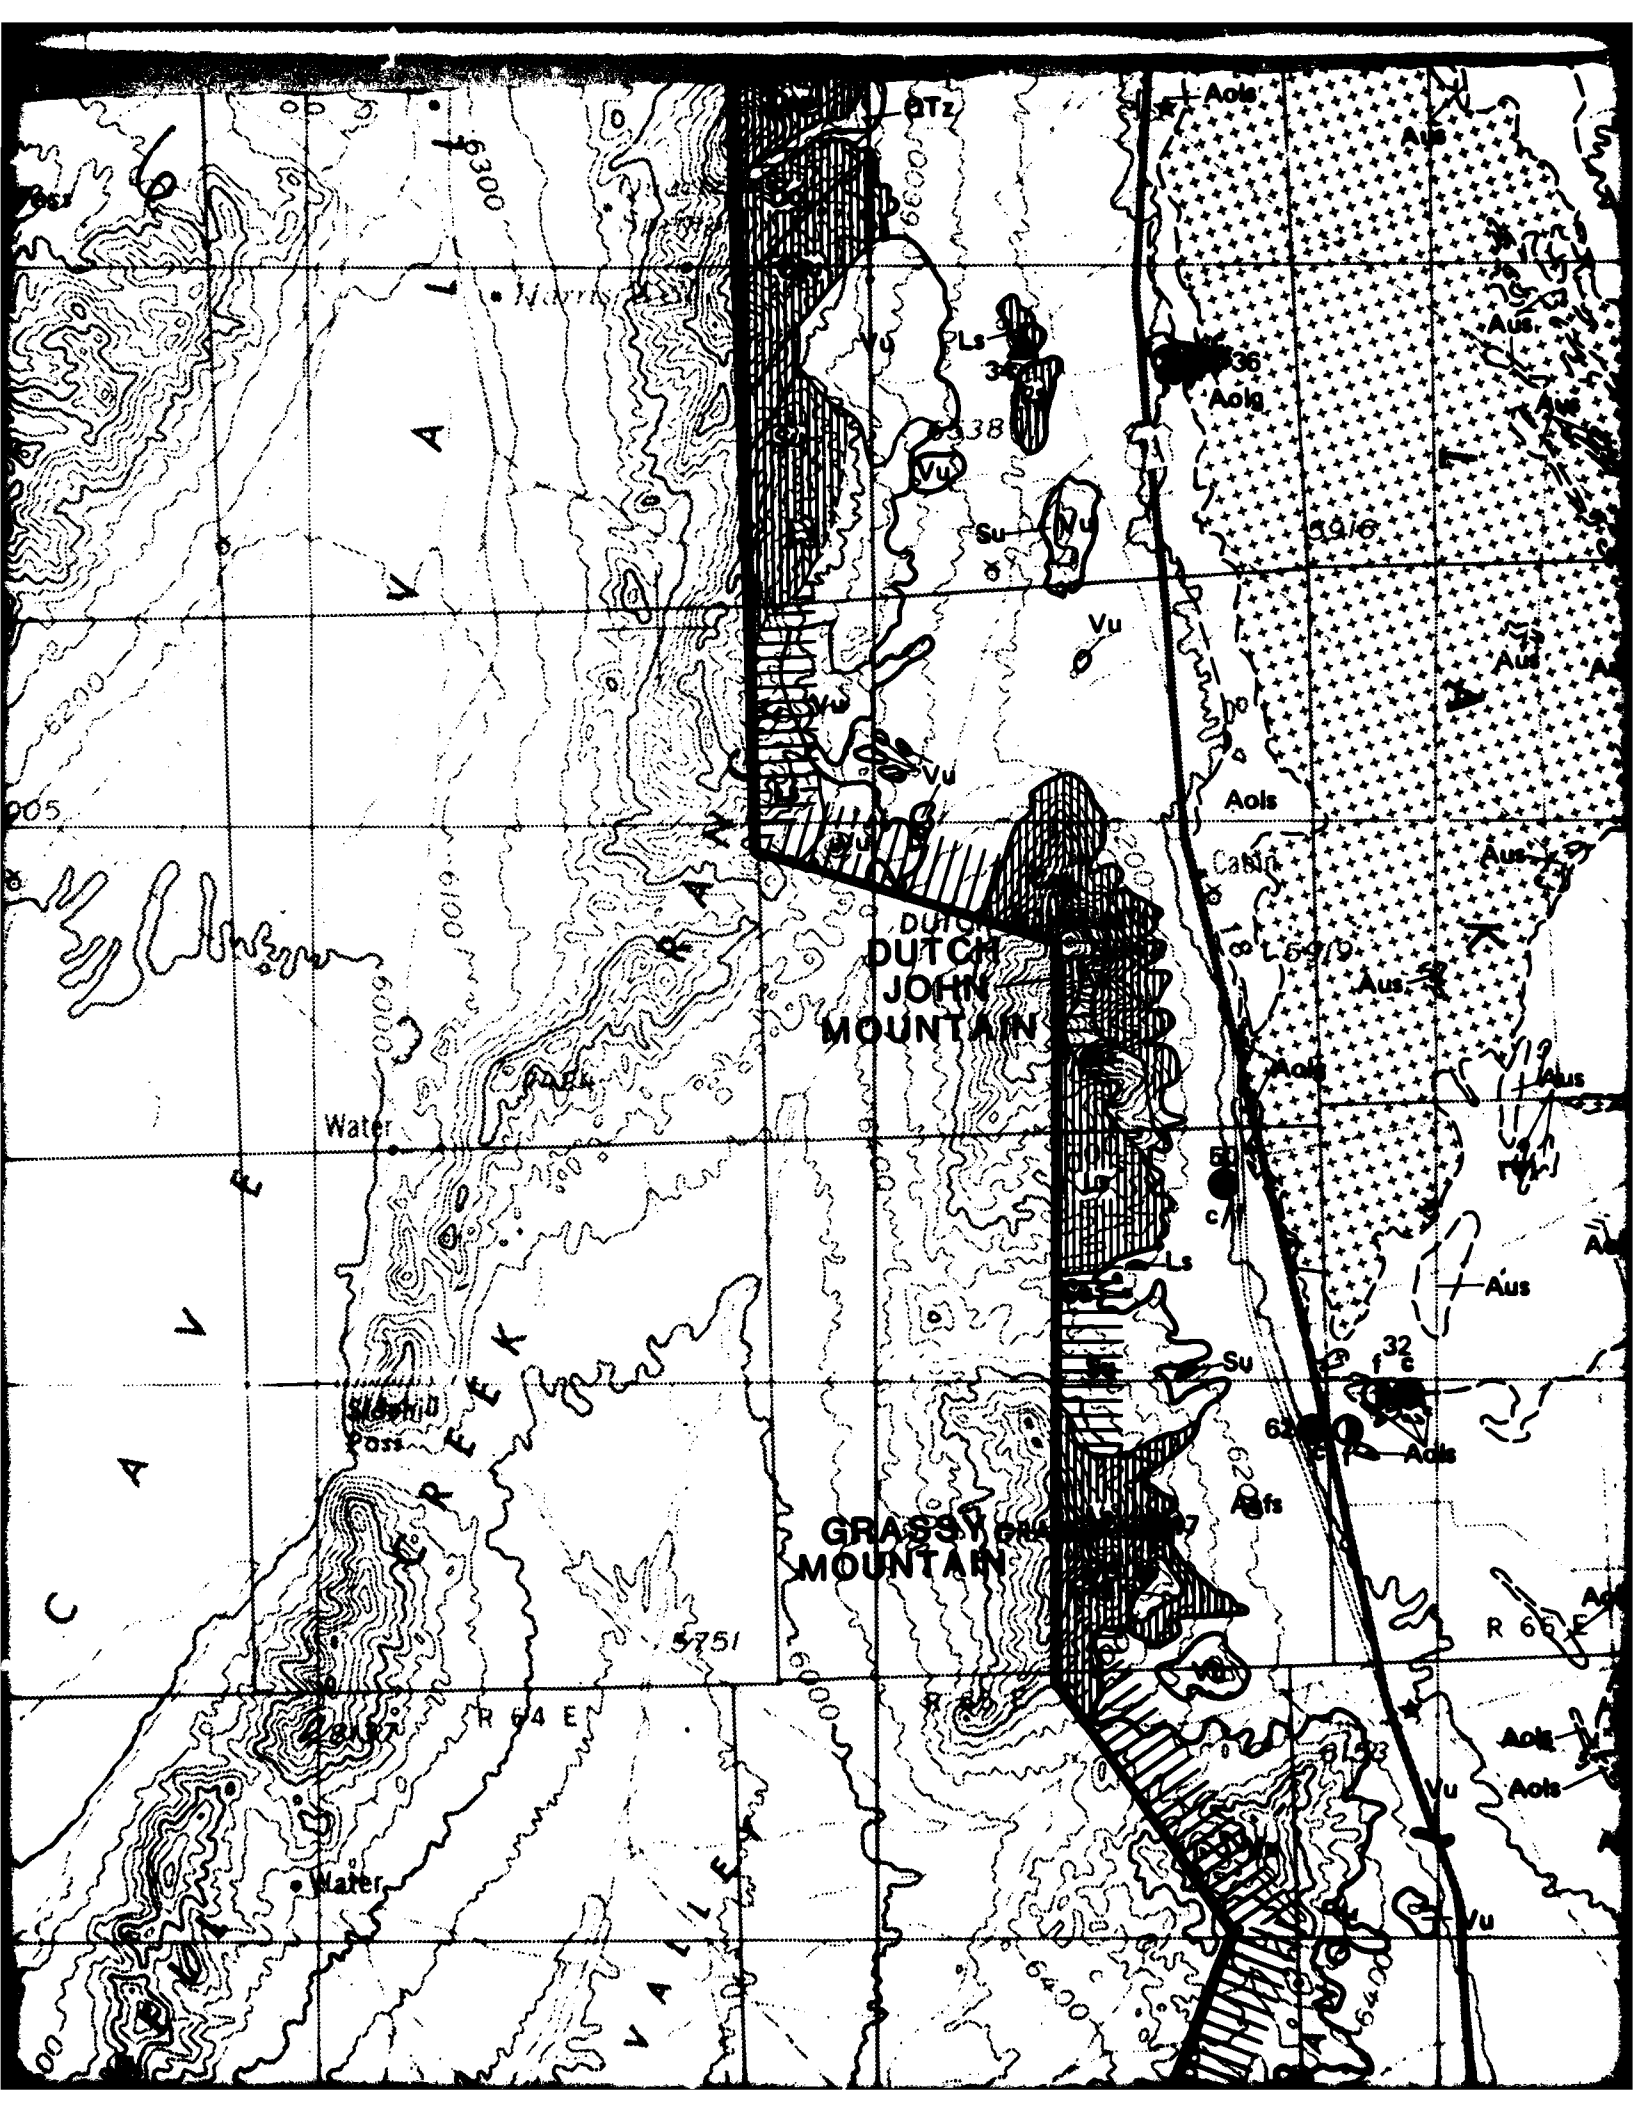

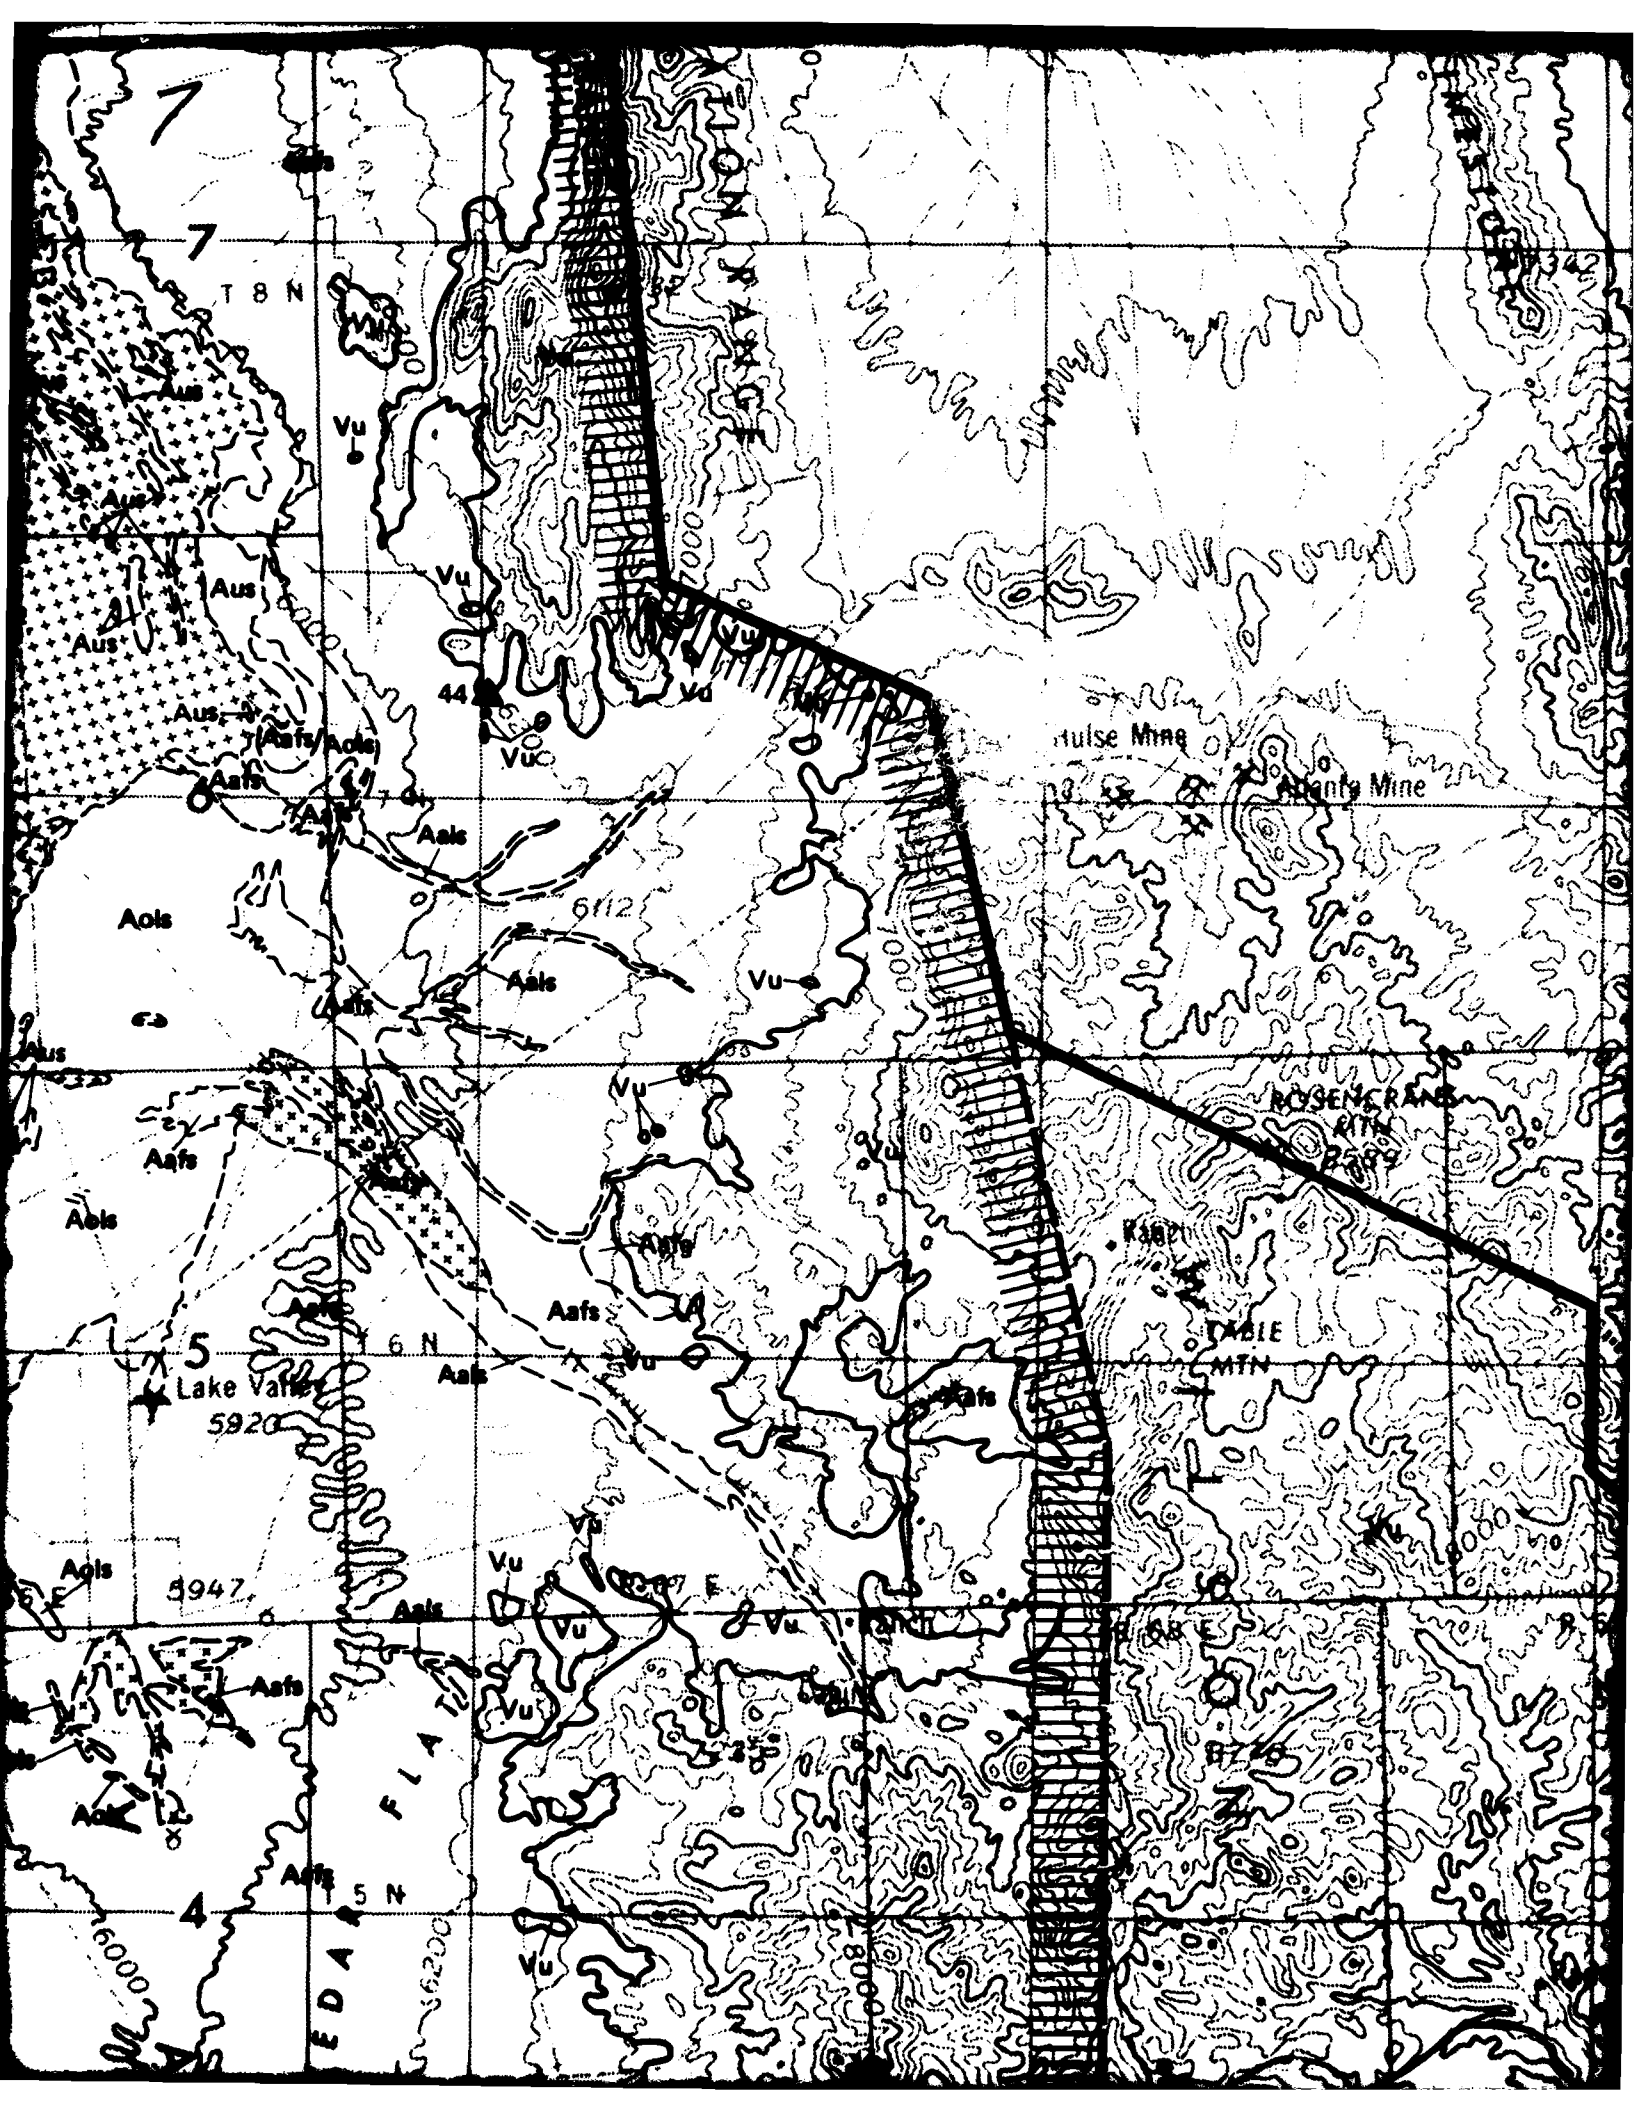

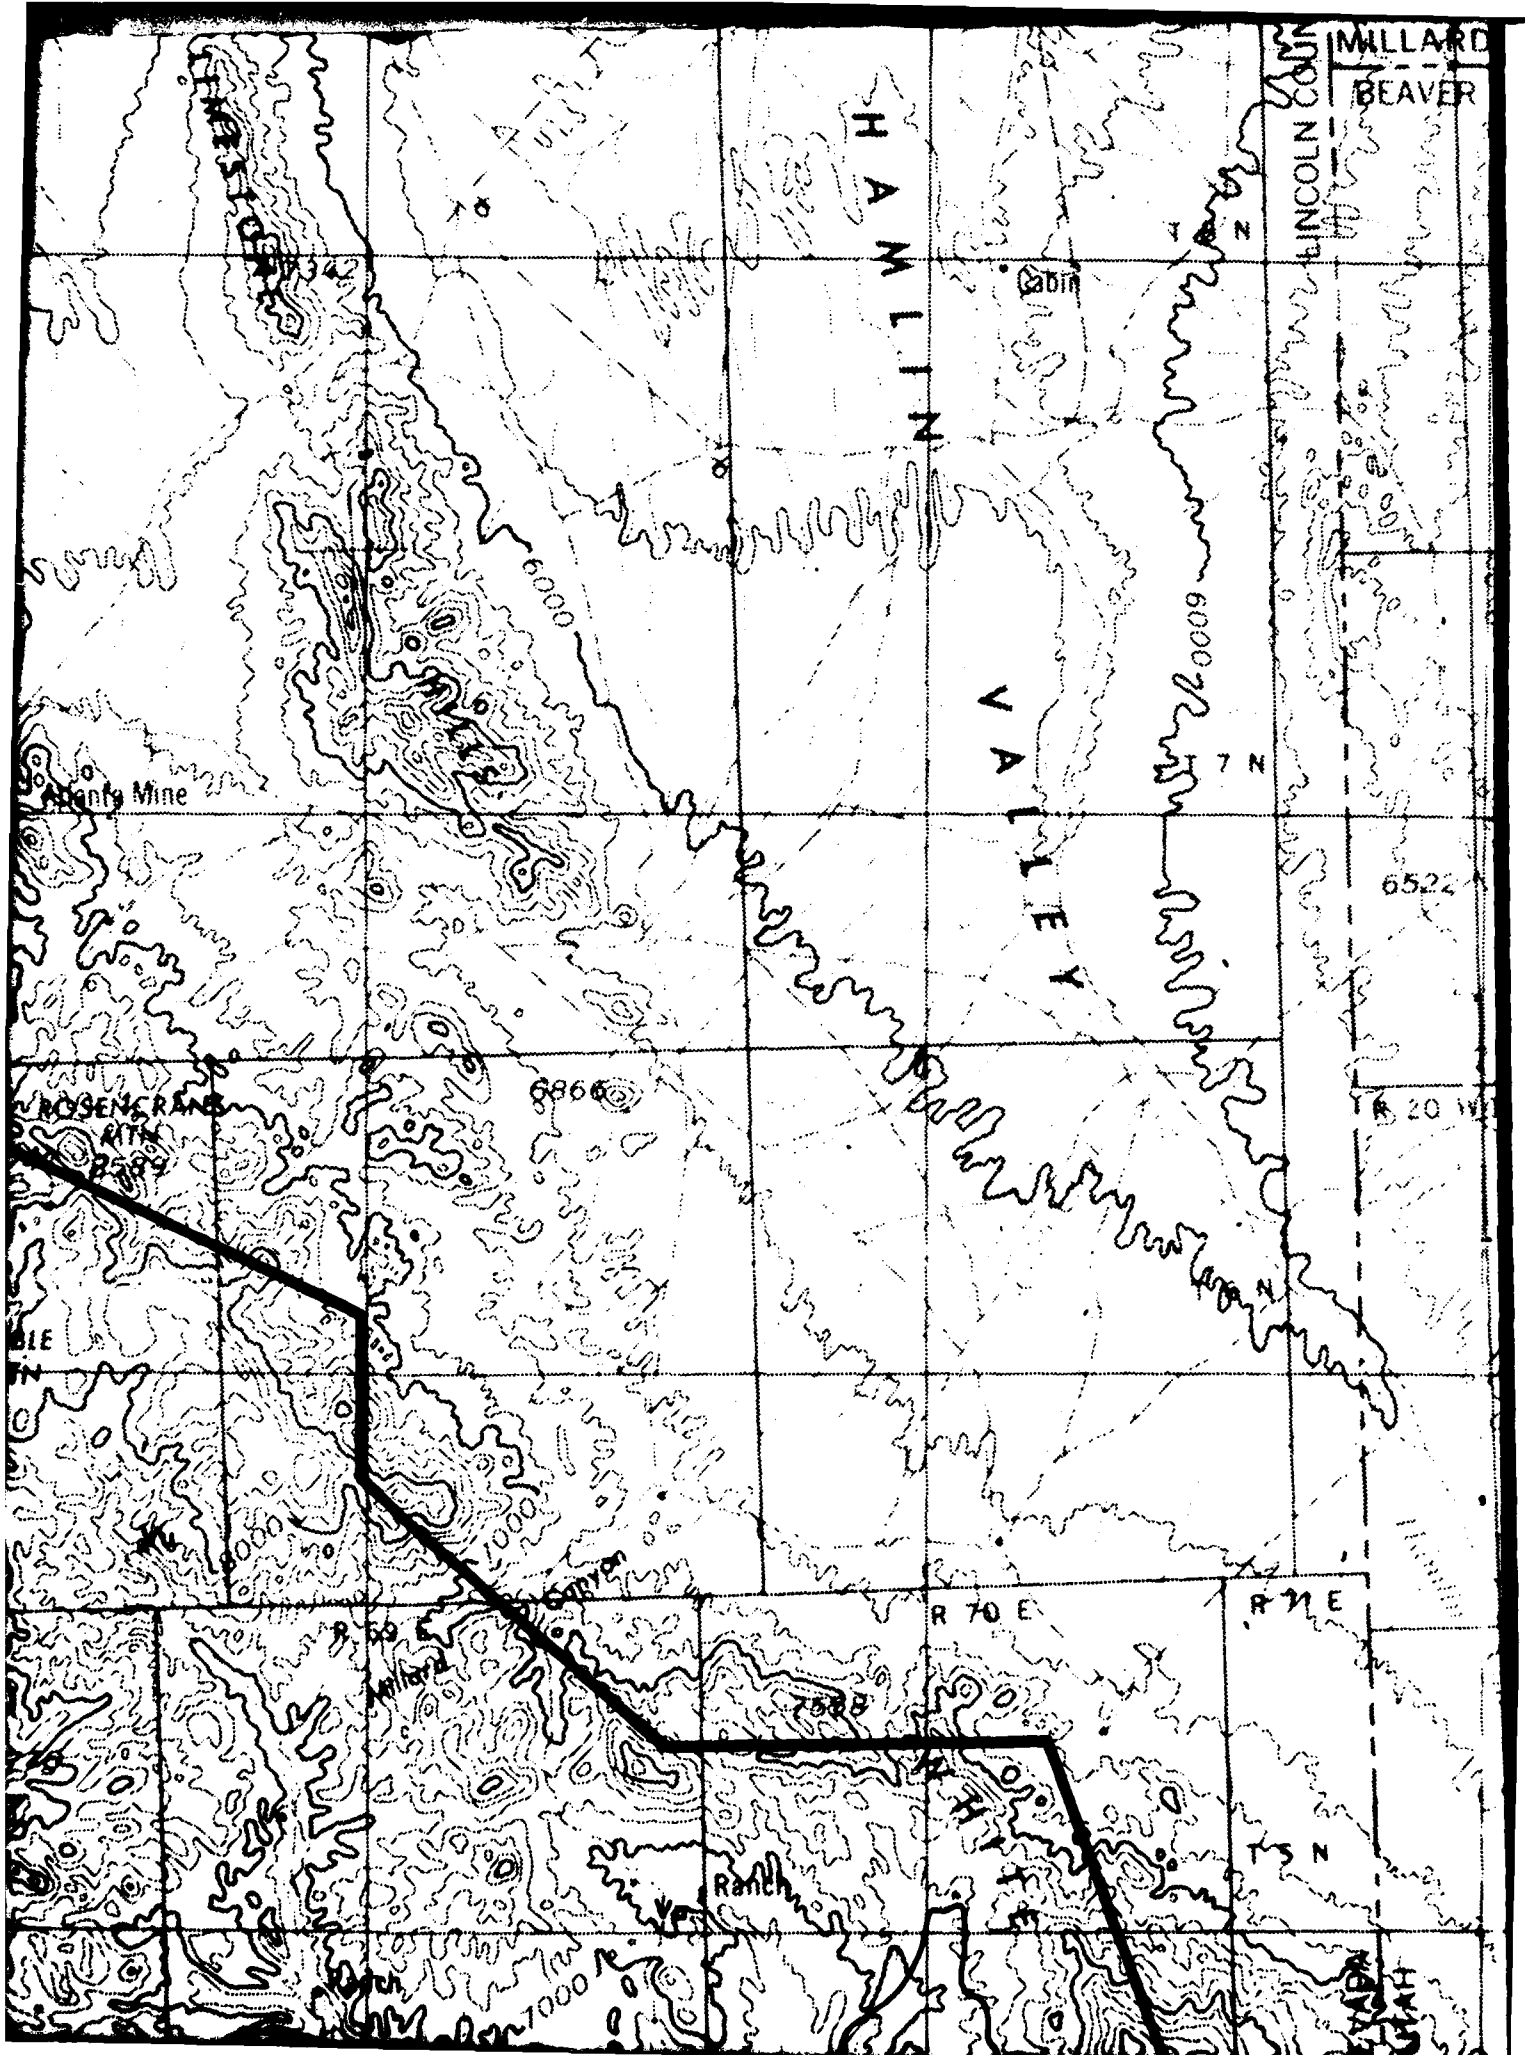

9

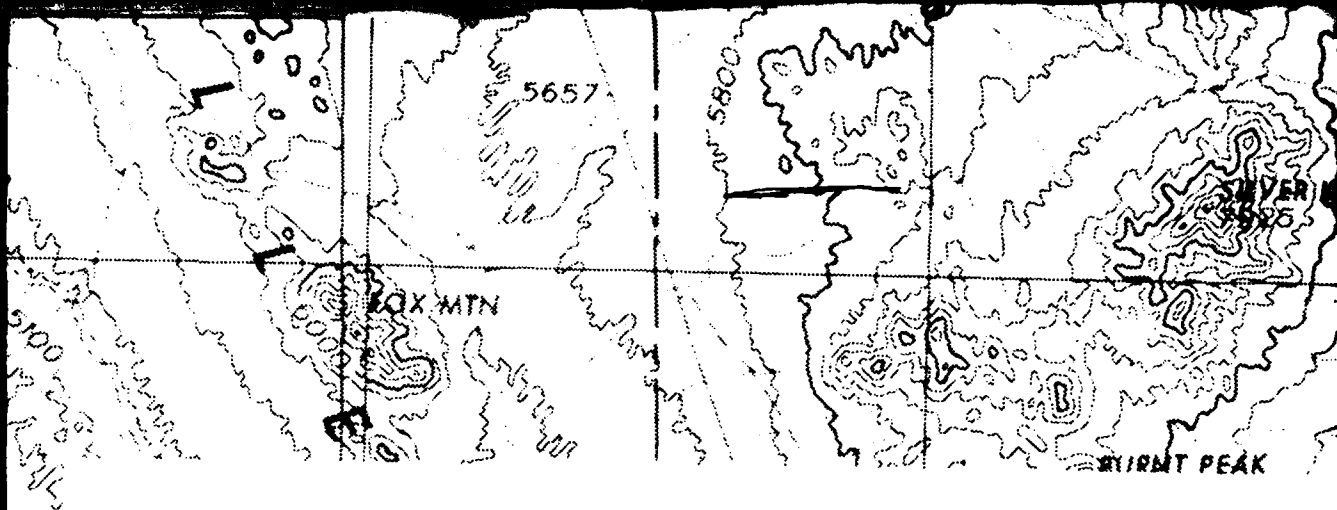

EXPLANATION

Potential Aggregate Sources

BASIN-FILL UNITS*

Aal	Stream Channel Deposits	(A1)
Aaf	Alluvial Fan Deposits	(A5)
Aol	Older Lacustrine Deposits	(A4o)
Au	Alluvial Deposits Undifferentiated	

ROCK UNITS*

Vu	Volcanic Rocks Undifferentiated	(I2 and/or I4)
Qtz	Quartzite	(M4 and/or S1)
Ls	Limestone	(S2)
Do	Dolomite	(S2)
Cau	Carbonate Rocks Undifferentiated	(S2)
Su	Sedimentary Rocks Undifferentiated	(S)


*Reference Appendix E for Symbol Explanation and Comparison


Symbols


Aafg Material type (Aaf) and Grain Size Designation (g).
Grain size designations are coarse (c) gravel (g) and
sand (s) and are assigned only in Verification Study Areas

 Geologic Contact, Dashed Where Approximate

 Approximate Concrete Aggregate and/or
Road-Base Materials Source Boundary

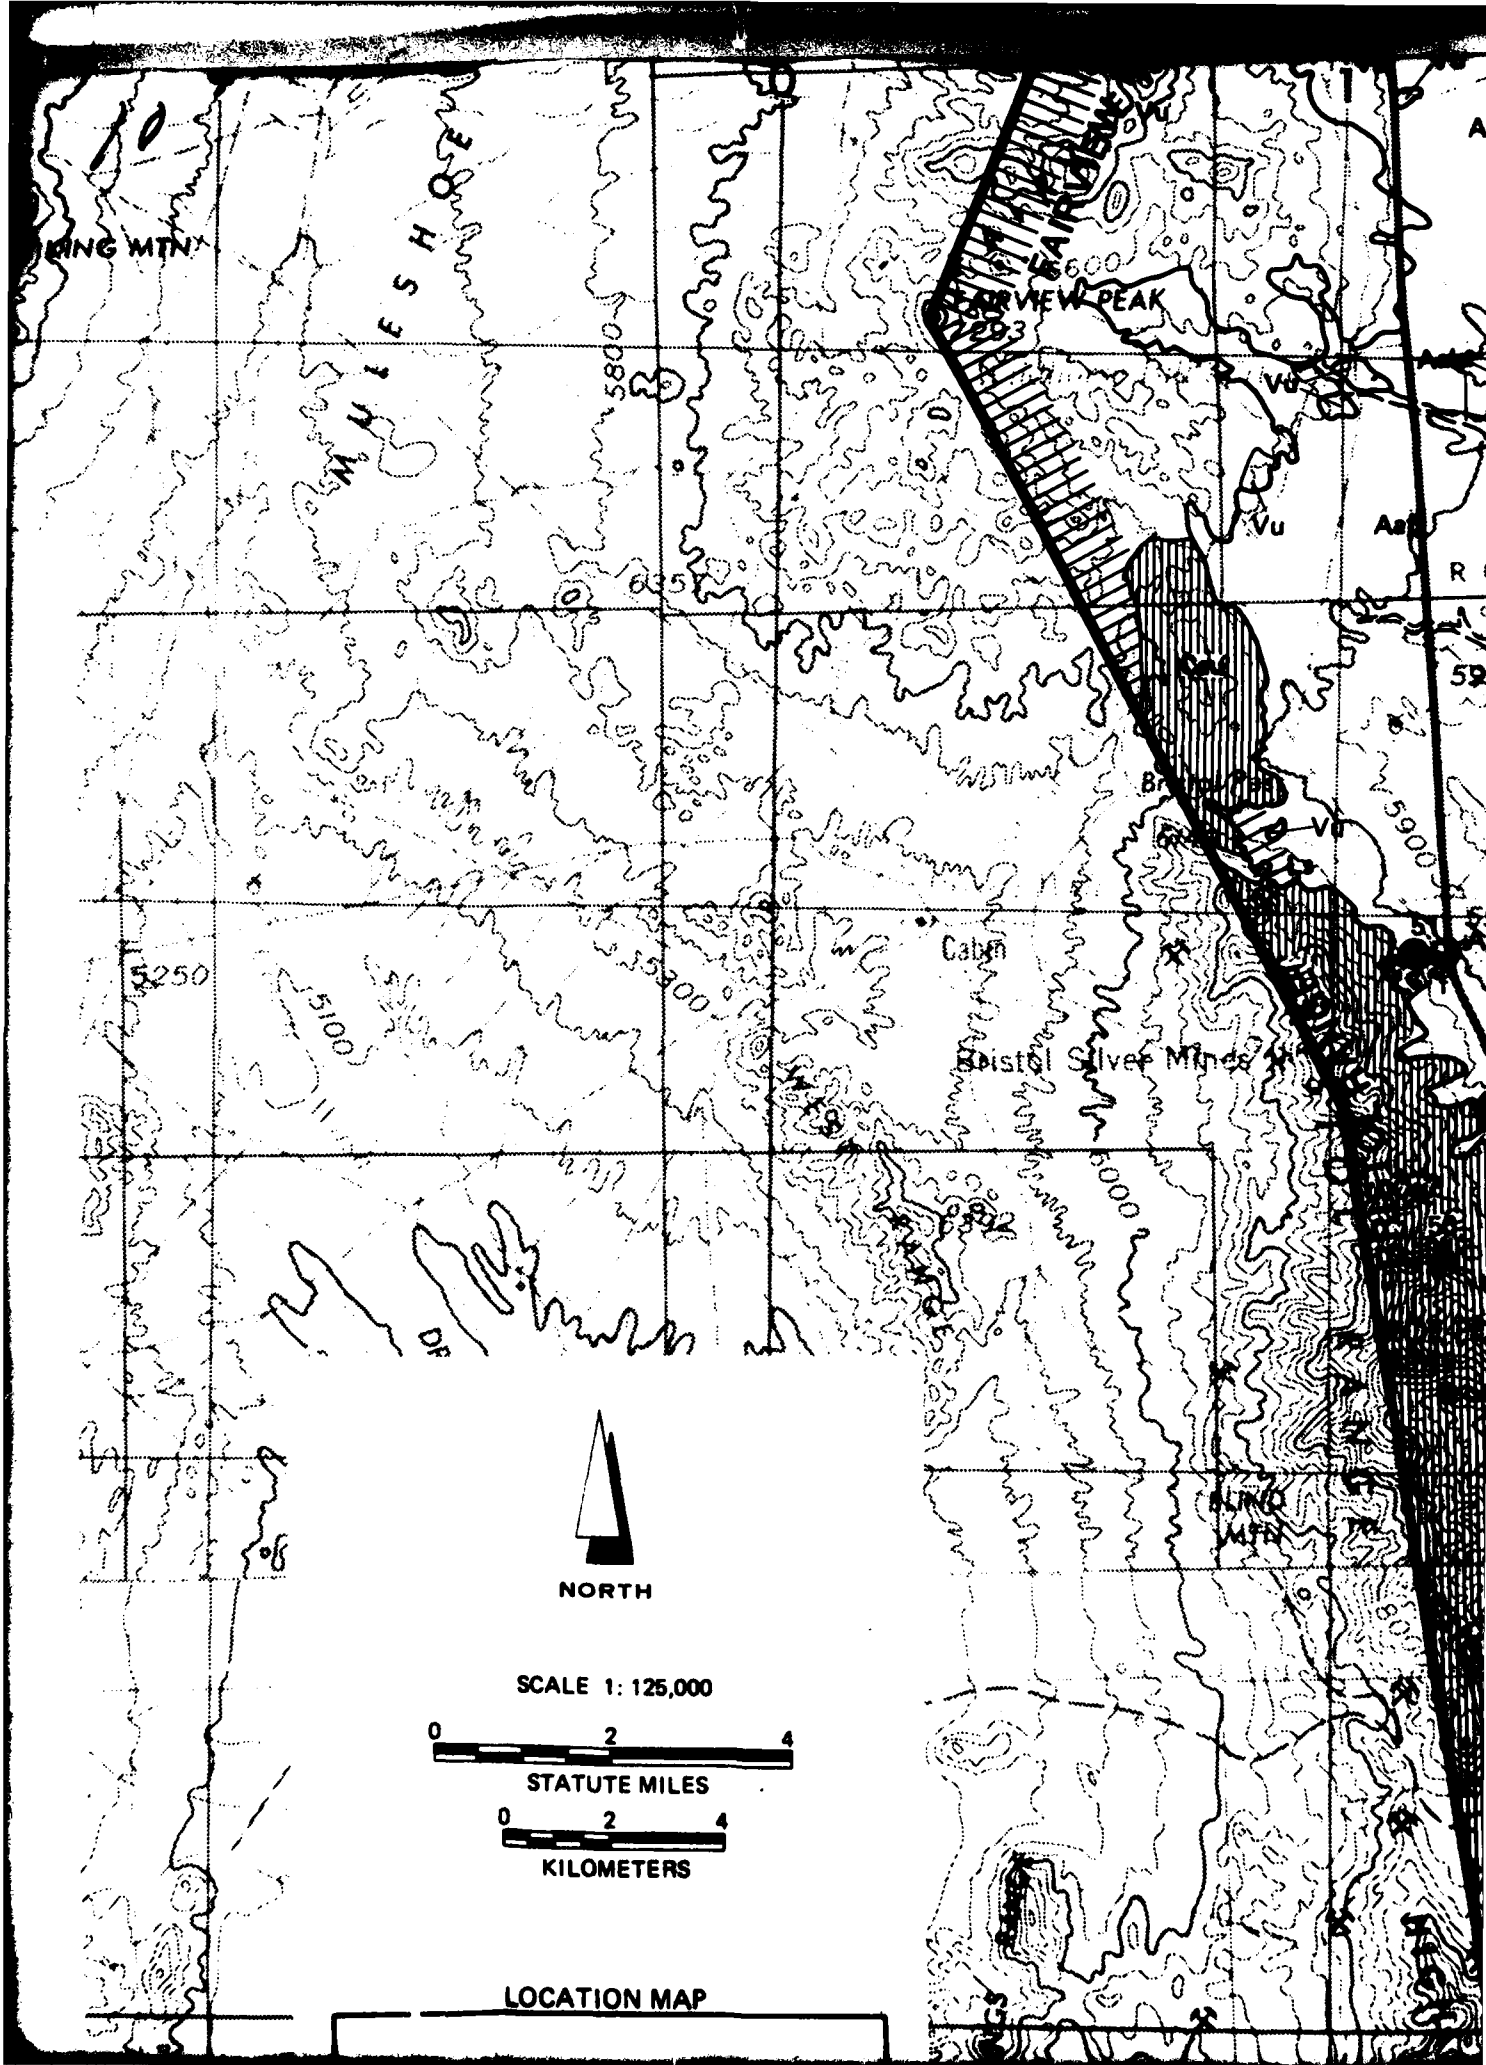

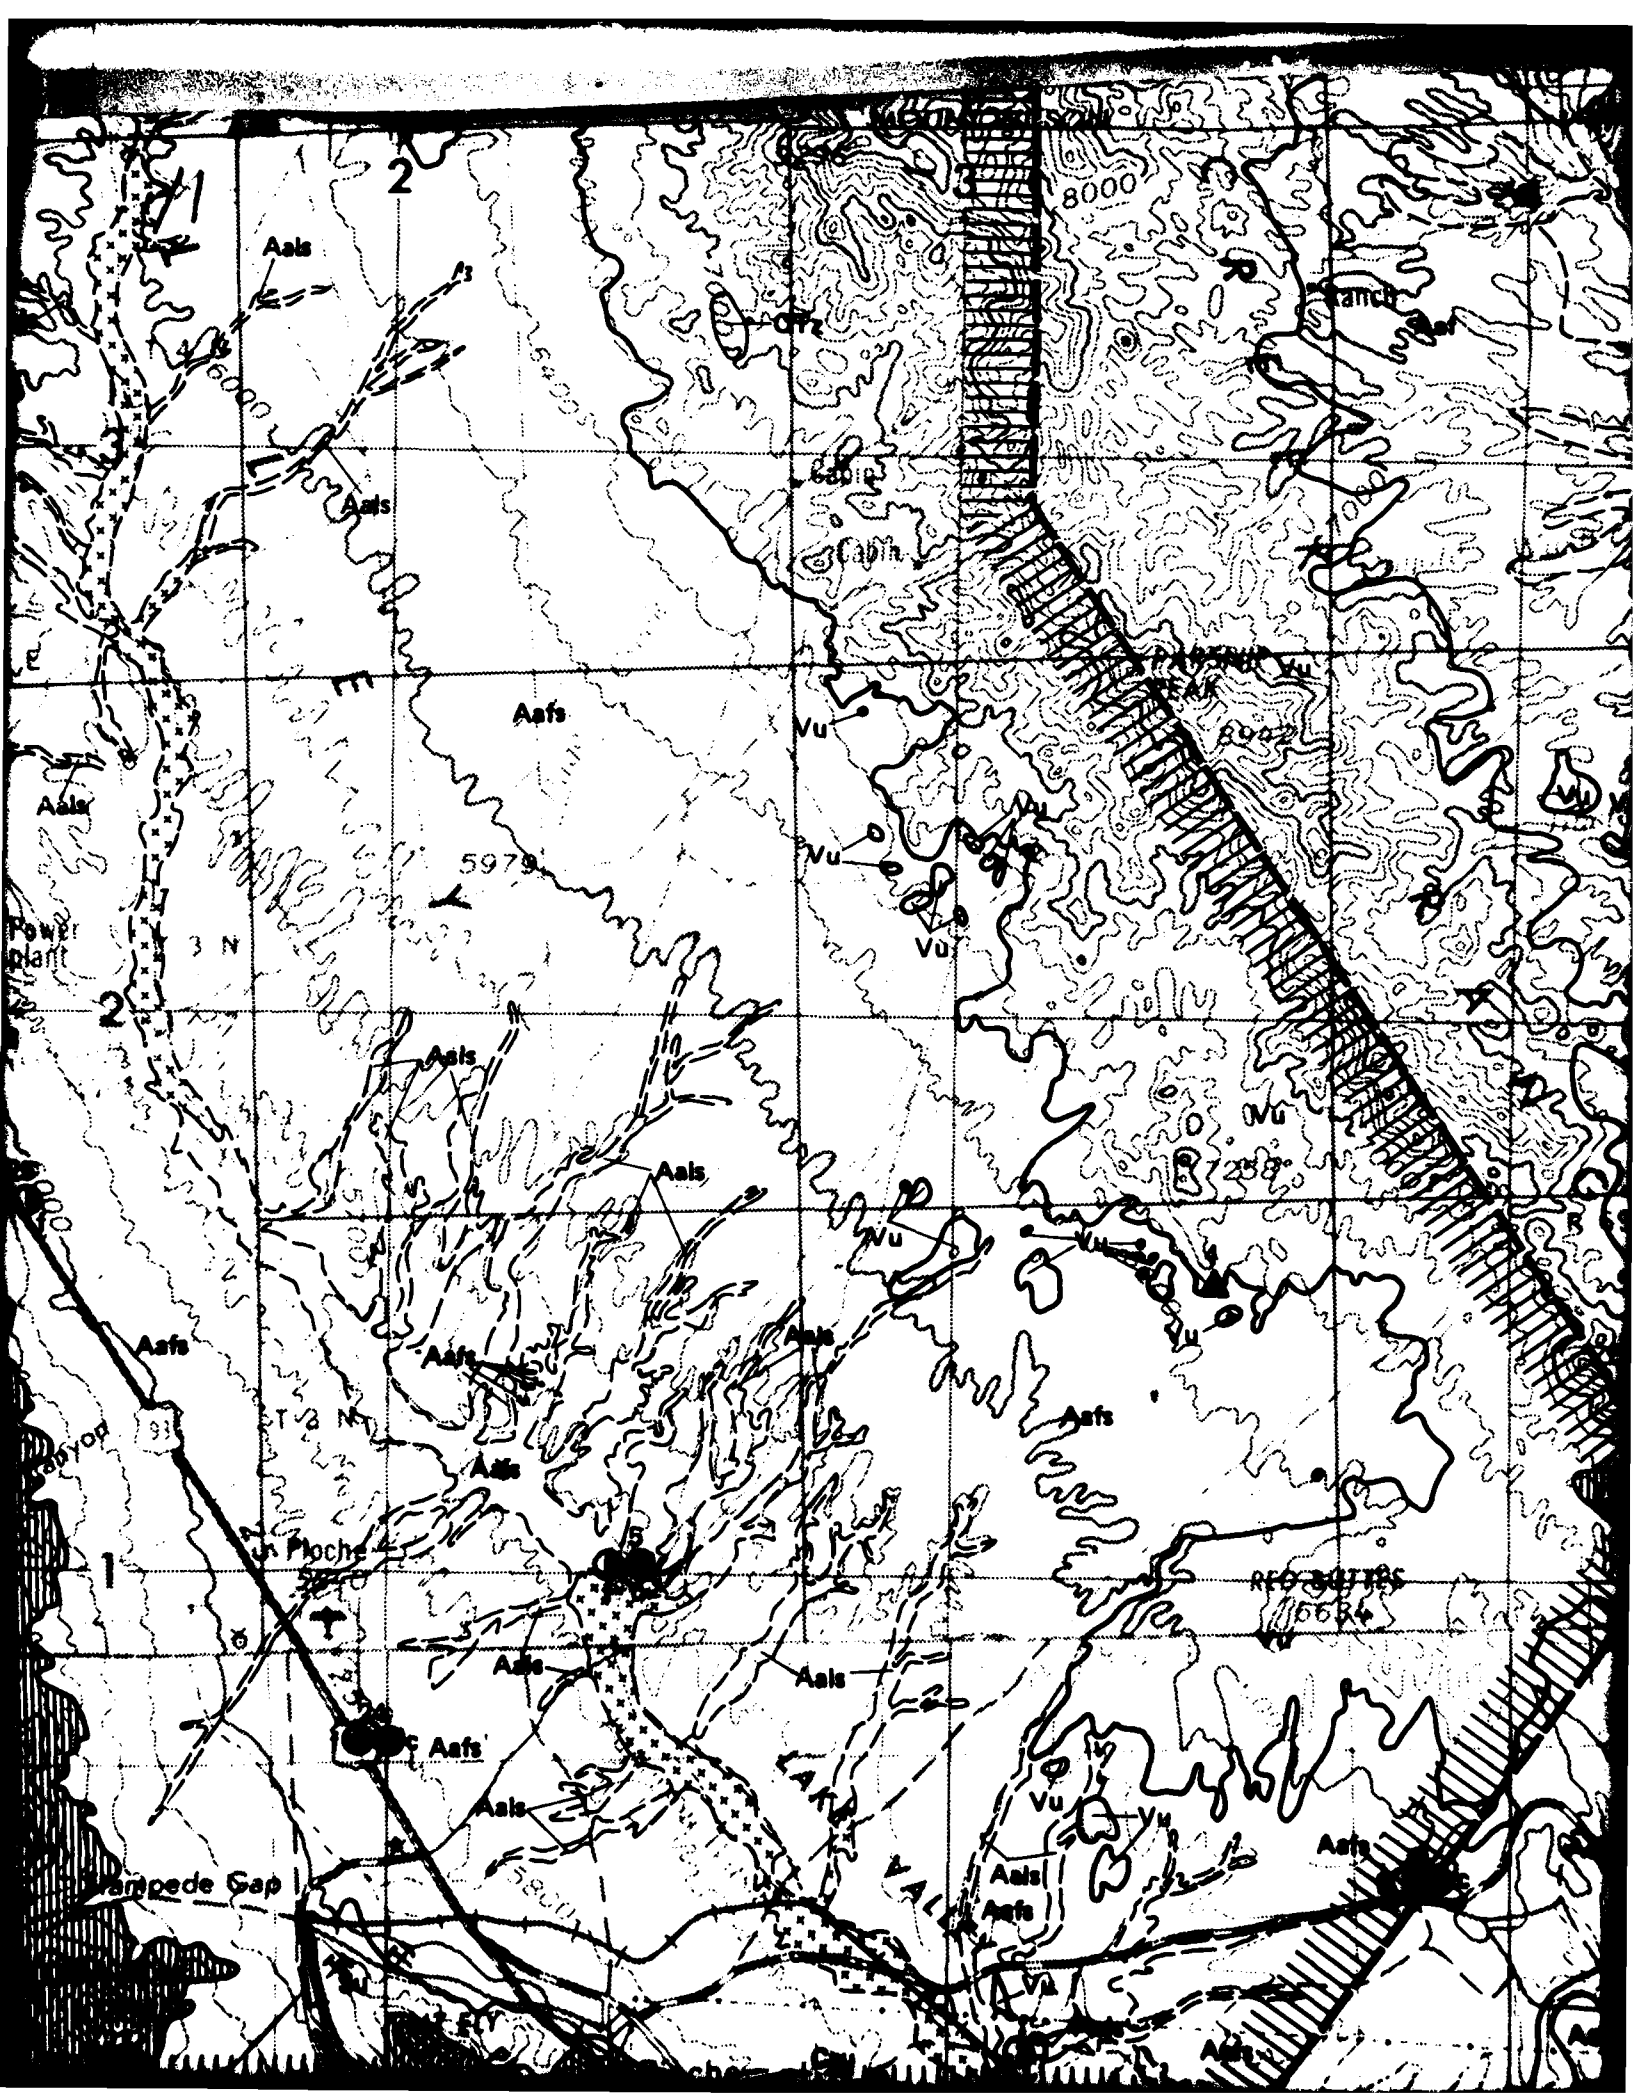

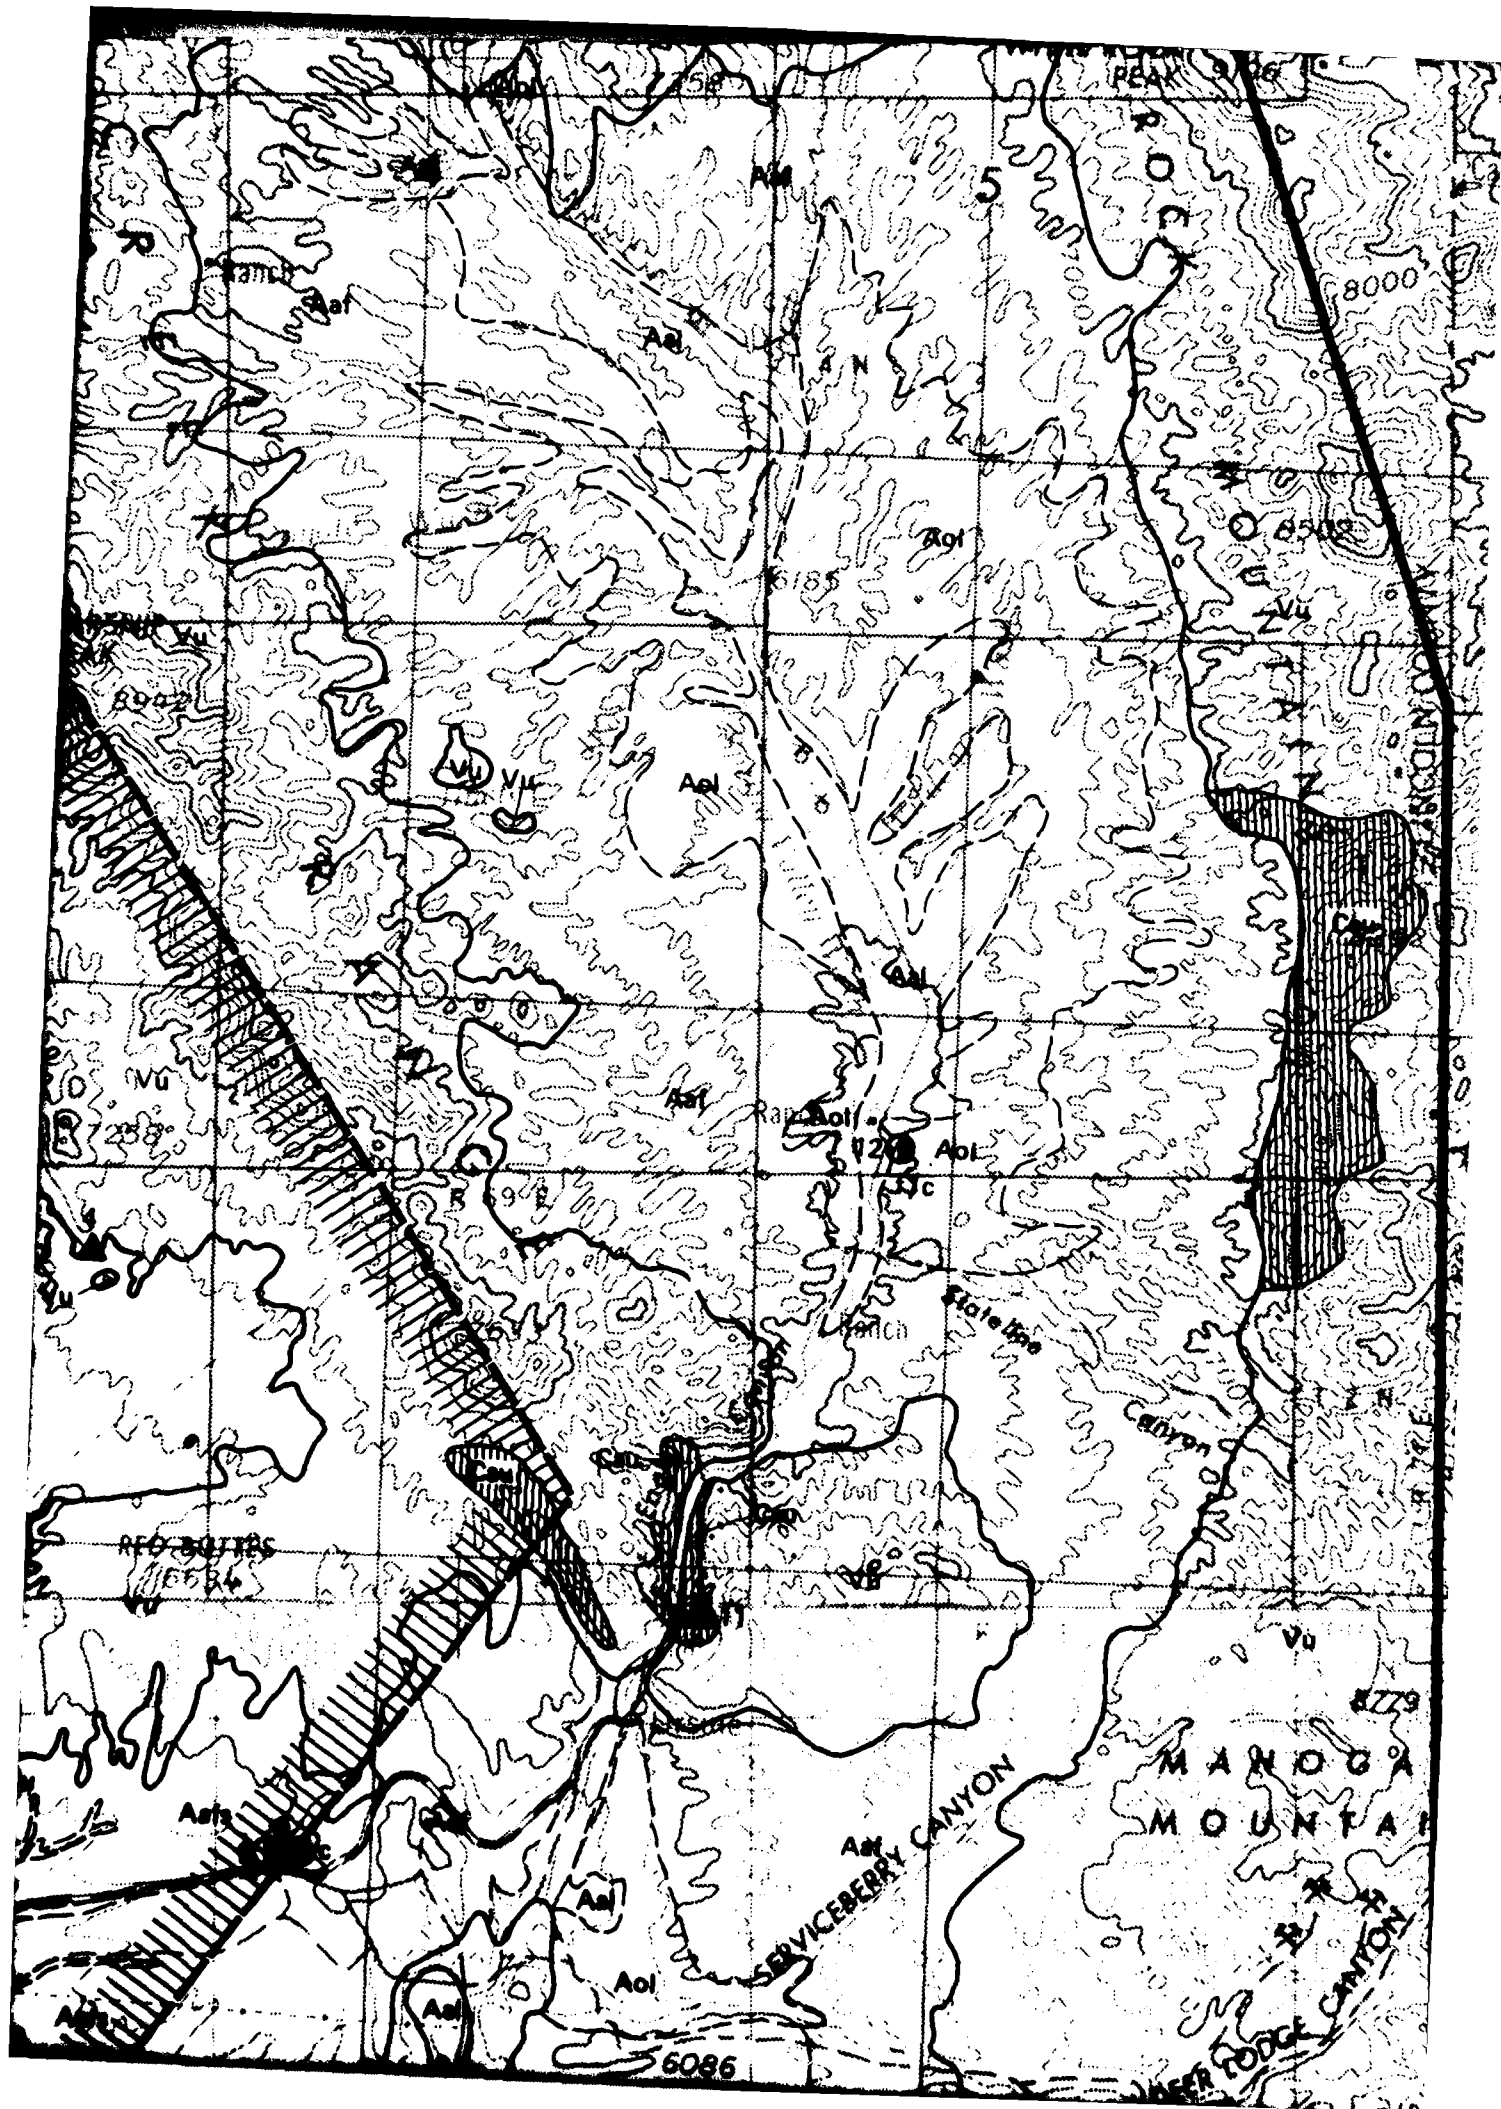

19



Verification Study Area

FUGRO NATIONAL VALLEY - SPECIFIC AGGREGATE RESOURCES
SAMPLED AND TESTED FIELD STATIONS

<u>BASIN-FILL AGGREGATE SAMPLE</u> <u>COARSE (c) AND FINE (f)</u>	<u>CRUSHED ROCK</u> <u>SAMPLE</u>	<u>CLASSIFICATION</u>
●	▲	CLASS I
①	△	CLASS II
○	△	CLASS III

NOTE: SEE CORRESPONDING MAP NUMBER IN APPENDIX A FOR DETAILED INFORMATION

CLASSIFICATION SYSTEM

BASIN-FILL SOURCES



Class I — Potentially Suitable Coarse,
Concrete Aggregate and Road-Base Material Source



Class I Potential Suitable
Concrete Aggregate and Road Base Material Source

ROCK SOURCES



Class I Potentially Suitable Crushed Rock, Coarse and Fine (Multiple Type Source),
Concrete Aggregate and Road-Base Materials Source

BASIN-FILL AND ROCK SOURCES






Class II Possibly Unsuitable Coarse, Fine and/or Crushed Rock Concrete Aggregate
Potentially Suitable Road-Base Material Source




Class III Unsuitable Coarse, Fine and /or Crushed Rock
Concrete Aggregate or Road-Base Material Source

27 FEB 81

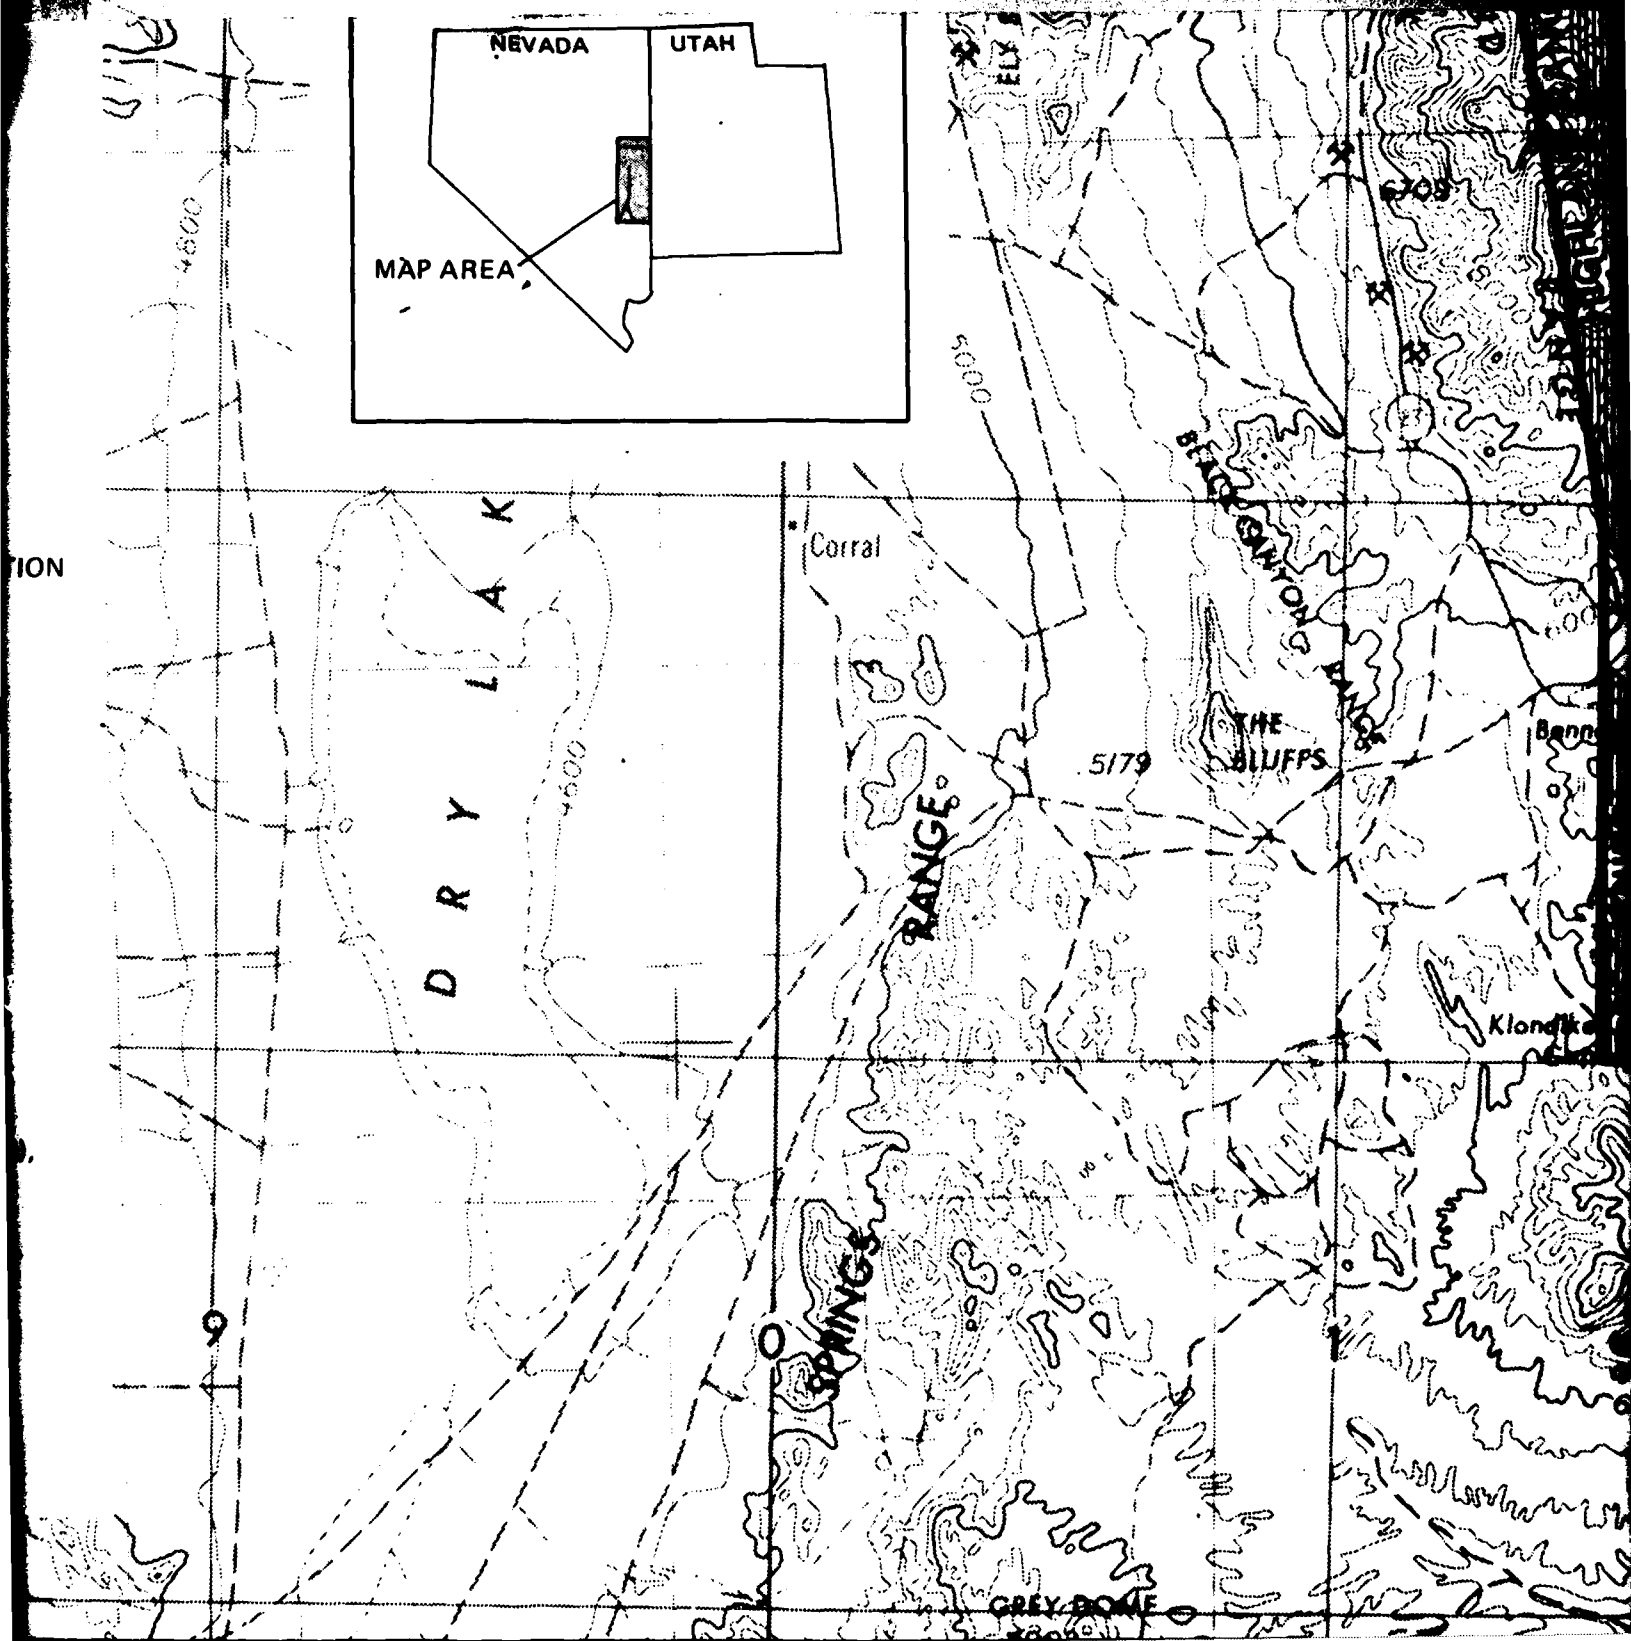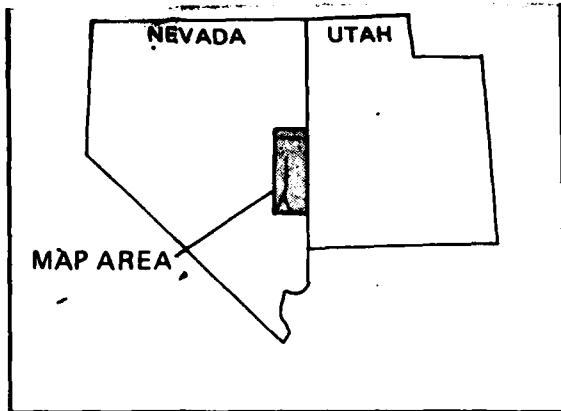

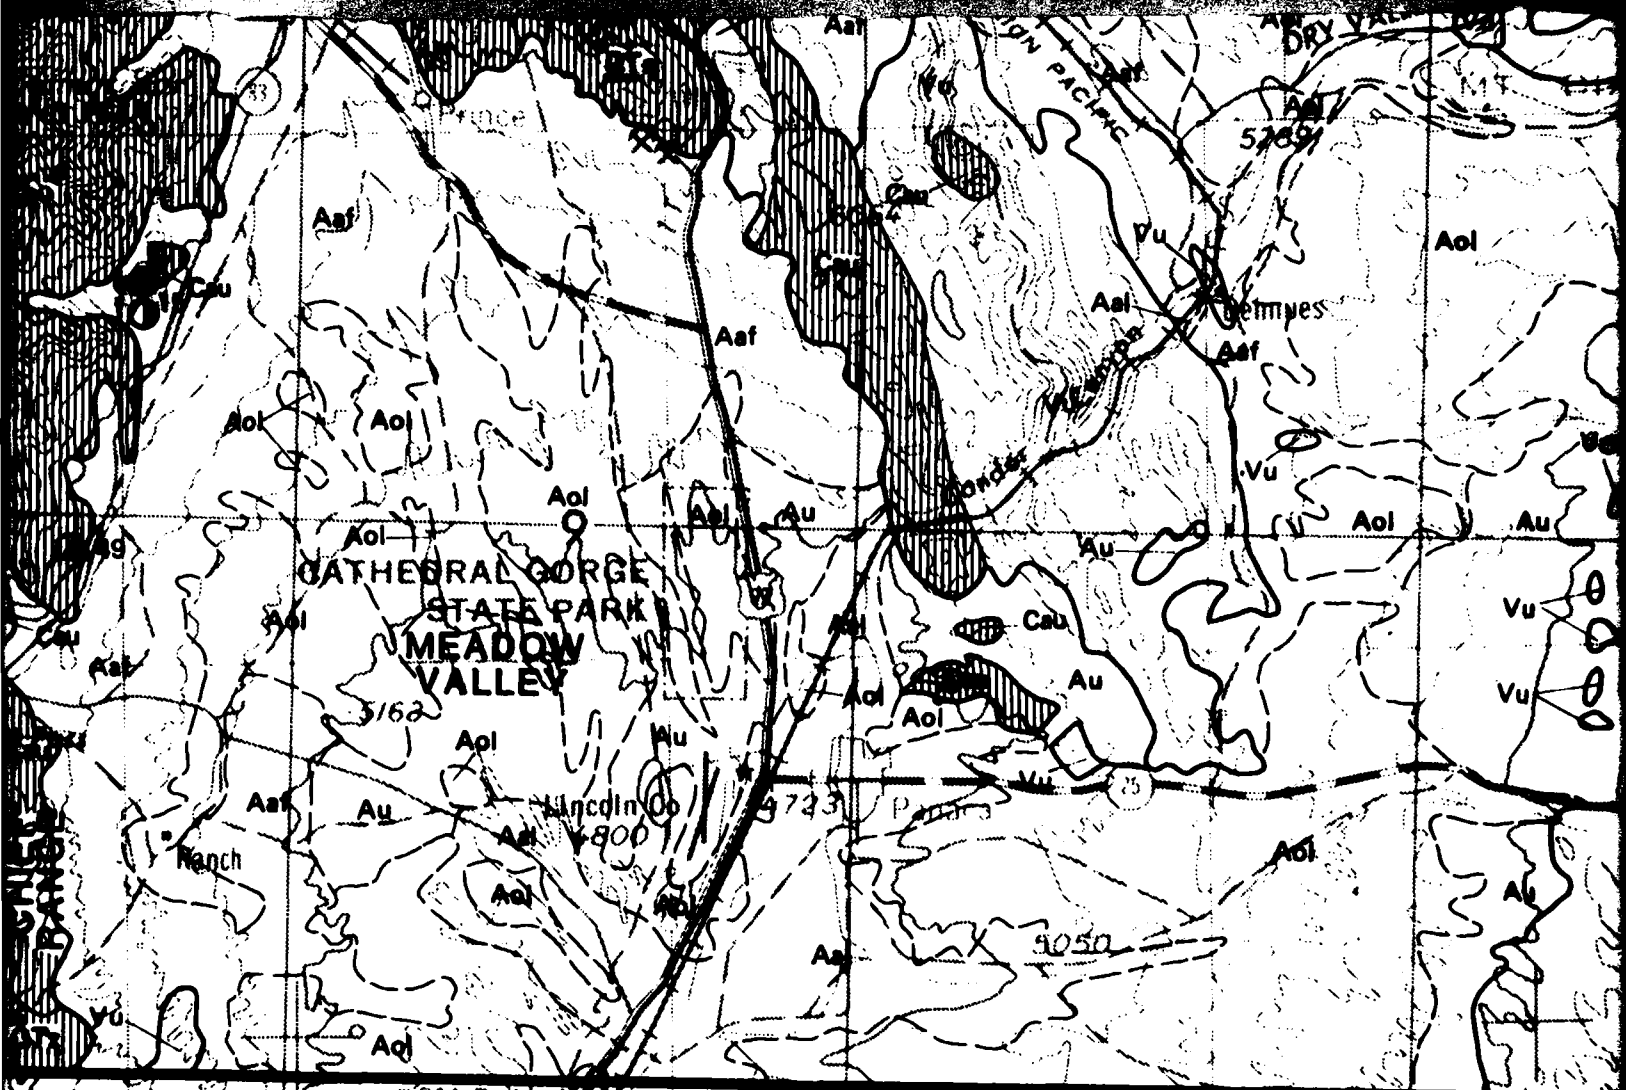

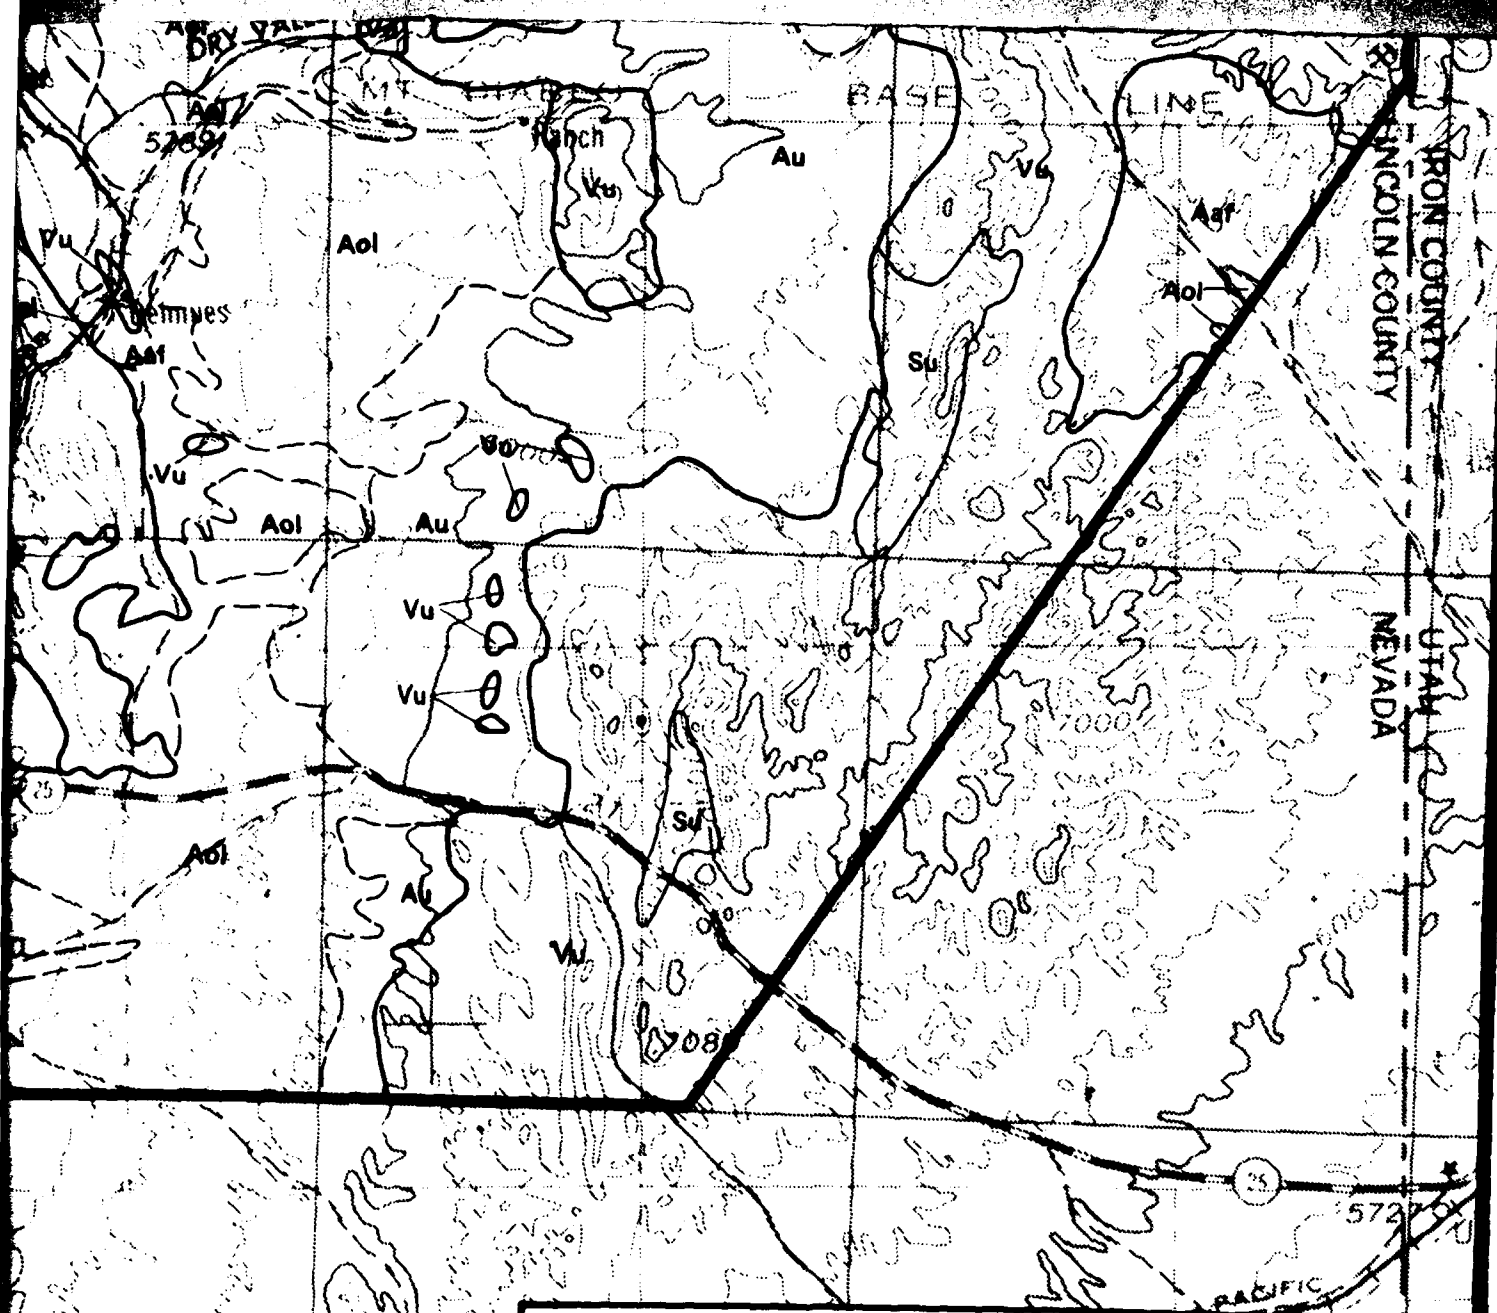

**AGGREGATE RESOURCES MAP
LAKE VALLEY, NEVADA**

**MX SITING INVESTIGATION,
DEPARTMENT OF THE AIR FORCE - BMO**

DRAWING

2

FUGRO NATIONAL, INC.

DATE
FILMED
- 8